




# OIL ANALYSIS REPORT

Sample Rating Trend

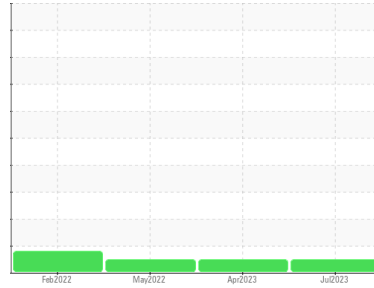

**NORMAL**



Machine Id  
**524017-905**

Component  
**Diesel Engine**

Fluid  
**PETRO CANADA DURON SHP 15W40 (46 GAL)**

## DIAGNOSIS

### Recommendation

Resample at the next service interval to monitor.

### Wear

All component wear rates are normal.

### Contamination

There is no indication of any contamination in the oil.

### Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>GFL0051014</b>	GFL0051032	GFL0051018
Sample Date	Client Info		<b>17 Jul 2023</b>	04 Apr 2023	17 May 2022
Machine Age	hrs	Client Info	<b>19414</b>	18864	17998
Oil Age	hrs	Client Info	<b>0</b>	354	531
Oil Changed	Client Info		<b>Changed</b>	Changed	Changed
Sample Status			<b>NORMAL</b>	NORMAL	NORMAL

## CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>3.0	<b>&lt;1.0</b>	<1.0	<1.0
Glycol	WC Method		<b>NEG</b>	NEG	NEG

## WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >165	<b>54</b>	33	32
Chromium	ppm	ASTM D5185m >5	<b>5</b>	2	2
Nickel	ppm	ASTM D5185m >4	<b>&lt;1</b>	<1	<1
Titanium	ppm	ASTM D5185m >2	<b>0</b>	0	0
Silver	ppm	ASTM D5185m >2	<b>0</b>	0	0
Aluminum	ppm	ASTM D5185m >20	<b>16</b>	10	2
Lead	ppm	ASTM D5185m >150	<b>4</b>	2	17
Copper	ppm	ASTM D5185m >90	<b>5</b>	7	5
Tin	ppm	ASTM D5185m >5	<b>2</b>	1	1
Antimony	ppm	ASTM D5185m	<b>---</b>	---	---
Vanadium	ppm	ASTM D5185m	<b>0</b>	0	0
Cadmium	ppm	ASTM D5185m	<b>0</b>	0	0

## ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 0	<b>8</b>	76	9
Barium	ppm	ASTM D5185m 0	<b>&lt;1</b>	0	0
Molybdenum	ppm	ASTM D5185m 60	<b>66</b>	53	66
Manganese	ppm	ASTM D5185m 0	<b>2</b>	3	<1
Magnesium	ppm	ASTM D5185m 1010	<b>975</b>	515	1108
Calcium	ppm	ASTM D5185m 1070	<b>1298</b>	1614	1354
Phosphorus	ppm	ASTM D5185m 1150	<b>1092</b>	870	1171
Zinc	ppm	ASTM D5185m 1270	<b>1346</b>	1066	1372
Sulfur	ppm	ASTM D5185m 2060	<b>3479</b>	3021	2924

## CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >35	<b>17</b>	29	4
Sodium	ppm	ASTM D5185m	<b>10</b>	16	4
Potassium	ppm	ASTM D5185m >20	<b>27</b>	29	3

## INFRA-RED



	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >7.5	<b>1.3</b>	0.7	0.9
Nitration	Abs/cm	*ASTM D7624 >20	<b>11.2</b>	7.9	13.6
Sulfation	Abs/.1mm	*ASTM D7415 >30	<b>23.3</b>	23.1	26.3

## FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	<b>19.3</b>	19.0	23.3
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	<b>7.3</b>	9.4	7.0







# OIL ANALYSIS REPORT

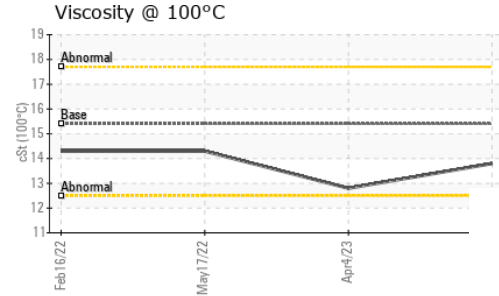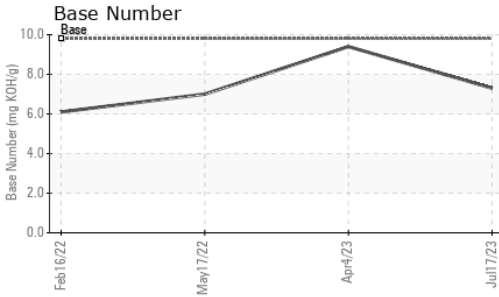

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	15.4	<b>13.8</b>	12.8	14.3

## GRAPHS

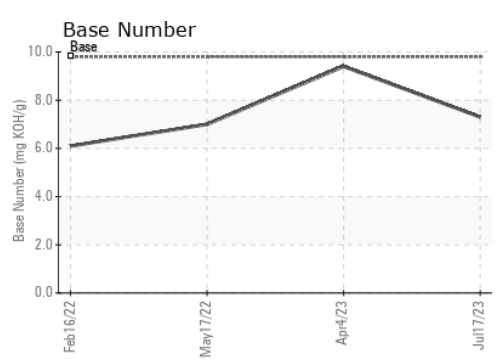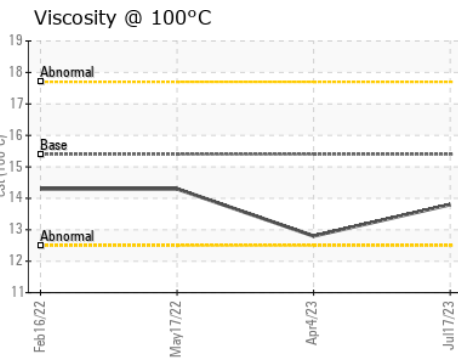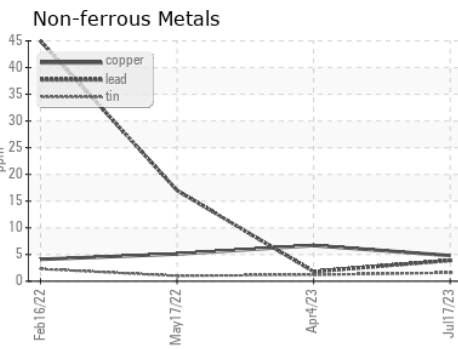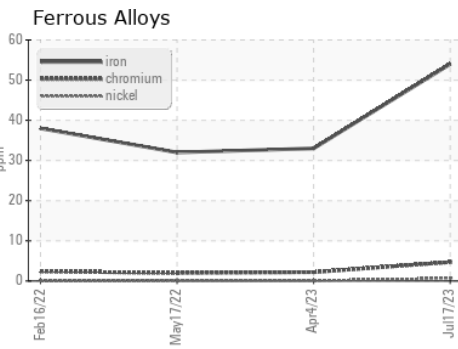

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : GFL0051014 **Received** : 21 Jul 2023  
**Lab Number** : **05904777** **Diagnosed** : 25 Jul 2023  
**Unique Number** : 10566133 **Diagnostician** : Don Baldrige  
**Test Package** : FLEET

**GFL Environmental - 632 - SWD Harrison**  
 4102 Industrail Pkwy  
 Harrison, MI  
 US 48625  
 Contact: RON TROJANEK  
 rtrojanek@gflenv.com  
 T:  
 F:

Certificate L2367  
 To discuss this sample report, contact Customer Service at 1-800-237-1369.  
 \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.  
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)