

OIL ANALYSIS REPORT

Sample Rating Trend

NORMAL

NAT CUTS [98435209 BEFORE] Machine Id LINE 3 CUBER

Component Hydraulic System Fluid AW HYDRAULIC OIL ISO 46 (--- GAL)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear


All component wear rates are normal.

Contamination

The amount and size of particulates present in the system are acceptable. There is no indication of any contamination in the oil.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.








SAMPLE INFORM	MATION	method	limit/base	current	history1	history2
Sample Number		Client Info		PCA0101629	PCA0083728	PCA0083726
Sample Date		Client Info		16 Aug 2023	20 Apr 2023	17 Apr 2023
Machine Age	hrs	Client Info		0	0	0
Oil Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		N/A	N/A	N/A
Sample Status				NORMAL	NORMAL	ATTENTION
WEAR METALS	S	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>20	5	2	4
Chromium	ppm	ASTM D5185m	>20	1	1	1
Nickel	ppm	ASTM D5185m	>20	0	<1	<1
Titanium	ppm	ASTM D5185m		0	0	0
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m	>20	2	0	0
Lead	ppm	ASTM D5185m	>20	<1	<1	<1
Copper	ppm	ASTM D5185m	>20	5	5	6
Tin	ppm	ASTM D5185m	>20	<1	<1	<1
Vanadium	ppm	ASTM D5185m		0	0	0
Cadmium	ppm	ASTM D5185m		0	0	0
ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	5	0	0	0
Barium	ppm	ASTM D5185m	5	0	0	0
Molybdenum	ppm	ASTM D5185m	5	0	0	0
Manganese	ppm	ASTM D5185m		0	0	0
Magnesium	ppm	ASTM D5185m	25	<1	0	<1
Calcium	ppm	ASTM D5185m	200	<1	0	<1
Phosphorus	ppm	ASTM D5185m	300	249	218	215
Zinc	ppm	ASTM D5185m	370	20	15	20
Sulfur	ppm	ASTM D5185m	2500	545	415	429
CONTAMINAN	TS	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>15	4	3	3
Sodium	ppm	ASTM D5185m		<1	0	0
Potassium	ppm	ASTM D5185m	>20	<1	<1	<1
FLUID CLEANL	INESS.	method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>5000	1269	258	▲ 8348
Particles >6µm		ASTM D7647	>1300	127	59	1129
Particles >14µm		ASTM D7647	>320	7	5	36
Particles >21µm		ASTM D7647	>80	2	1	2
Particles >38µm		ASTM D7647	>20	1	0	0
Particles >71µm		ASTM D7647	>4	0	0	0
Oil Cleanliness		ISO 4406 (c)	>19/17/15	17/14/10	15/13/10	<u> </u>
FLUID DEGRAD	ATION	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	0.57	0.17	0.17	0.16




OIL ANALYSIS REPORT

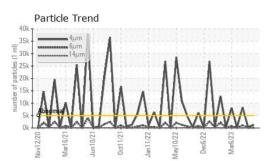

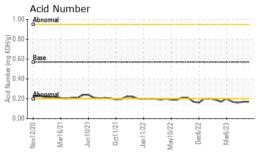


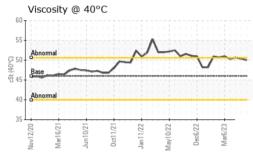



VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.05	NEG	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG	NEG
FLUID PROPE	ERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	46	50.0	50.4	50.6
SAMPLE IMAG	GES	method	limit/base	current	history1	history2
Color				•		
Bottom				(63)		

ottom

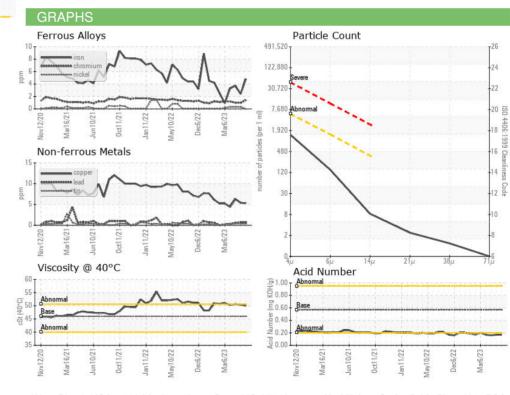

KraftHeinz - Springfield - Plant 8311 PCA Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513 Sample No. : PCA0101629 Received : 04 Oct 2023 2035 E BENNETT Lab Number : 05968932 Diagnosed : 06 Oct 2023 SPRINGFIELD, MO : 10675483 Unique Number Diagnostician : Don Baldridge US 65804 Test Package : IND 2 Contact: Service Manager Certificate L2367 To discuss this sample report, contact Customer Service at 1-800-237-1369. T:

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)