




PROBLEM SUMMARY

Sample Rating Trend

GLYCOL




Machine Id
2515
Component
Diesel Engine
Fluid
PETRO CANADA DURON SHP 15W40 (11 GAL)

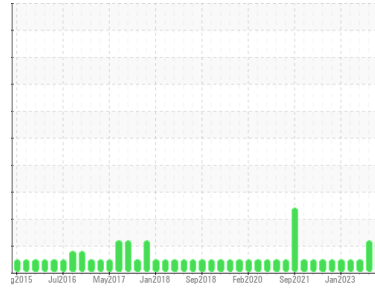

COMPONENT CONDITION SUMMARY

▲ Glycol Contamination

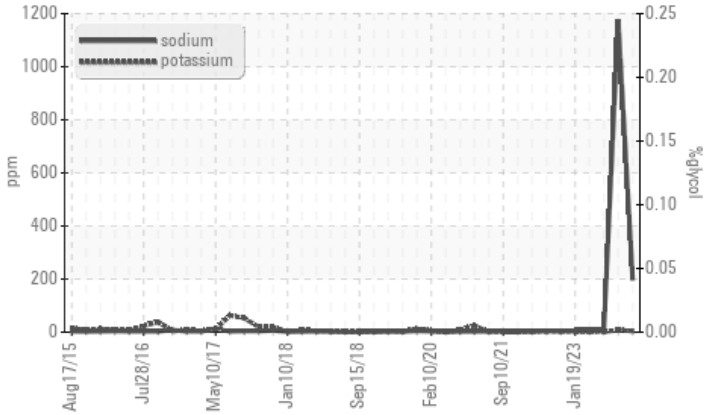

RECOMMENDATION

We advise that you check for possible coolant leak. Check for low coolant level. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

PROBLEMATIC TEST RESULTS

Sample Status			ABNORMAL	ABNORMAL	NORMAL
Sodium	ppm	ASTM D5185m	▲ 197	▲ 1176	11

Customer Id: GFL094
Sample No.: GFL0072183
Lab Number: 05985346
Test Package: FLEET



To manage this report scan the QR code

To discuss the diagnosis or test data:
Jonathan Hester +1 919-379-4092 x4092
jhester@wearcheckusa.com

To change component or sample information:
Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Fluid	---	---	?	Oil and filter change at the time of sampling has been noted.
Change Filter	---	---	?	Oil and filter change at the time of sampling has been noted.
Resample	---	---	?	We recommend an early resample to monitor this condition.
Check Glycol Access	---	---	?	We advise that you check for the source of the coolant leak.

HISTORICAL DIAGNOSIS

11 Oct 2023 Diag: Jonathan Hester

GLYCOL



We advise that you check for the source of the coolant leak. Check for low coolant level. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition. All component wear rates are normal. Sodium and/or potassium levels are high. The BN result indicates that there is suitable alkalinity remaining in the oil.

[view report](#)



11 Jul 2023 Diag: Wes Davis

NORMAL



Resample at the next service interval to monitor. All component wear rates are normal. There is no indication of any contamination in the oil. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

[view report](#)



28 Jun 2023 Diag: Wes Davis

NORMAL



Resample at the next service interval to monitor. All component wear rates are normal. There is no indication of any contamination in the oil. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.


[view report](#)





OIL ANALYSIS REPORT

Sample Rating Trend

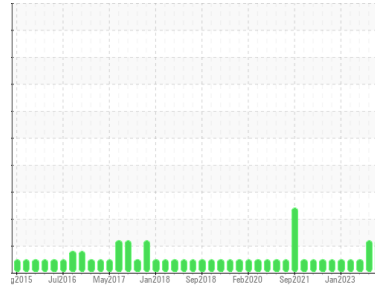

GLYCOL



Machine Id
2515

Component
Diesel Engine

Fluid
PETRO CANADA DURON SHP 15W40 (11 GAL)

DIAGNOSIS

▲ Recommendation

We advise that you check for possible coolant leak. Check for low coolant level. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

Contamination

Sodium and/or potassium levels remain high.

▲ Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil.

SAMPLE INFORMATION

method	limit/base	current	history1	history2	
Sample Number	Client Info	GFL0072183	GFL0072174	GFL0072063	
Sample Date	Client Info	17 Oct 2023	11 Oct 2023	11 Jul 2023	
Machine Age	mls	Client Info	613346	112207	26339
Oil Age	mls	Client Info	0	0	600
Oil Changed	Client Info	Changed	Changed	Changed	
Sample Status		ABNORMAL	ABNORMAL	NORMAL	

CONTAMINATION

method	limit/base	current	history1	history2
Fuel	WC Method >3.0	<1.0	<1.0	<1.0

WEAR METALS

method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185m >165	5	16	36
Chromium	ppm	ASTM D5185m >5	0	<1	1
Nickel	ppm	ASTM D5185m >4	0	<1	<1
Titanium	ppm	ASTM D5185m >2	<1	0	0
Silver	ppm	ASTM D5185m >2	0	<1	0
Aluminum	ppm	ASTM D5185m >20	2	4	3
Lead	ppm	ASTM D5185m >150	4	22	3
Copper	ppm	ASTM D5185m >90	11	47	2
Tin	ppm	ASTM D5185m >5	0	<1	<1
Vanadium	ppm	ASTM D5185m	<1	0	0
Cadmium	ppm	ASTM D5185m	0	0	0

ADDITIVES

method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185m 0	10	45	7
Barium	ppm	ASTM D5185m 0	0	0	2
Molybdenum	ppm	ASTM D5185m 60	67	99	68
Manganese	ppm	ASTM D5185m 0	0	<1	<1
Magnesium	ppm	ASTM D5185m 1010	976	873	910
Calcium	ppm	ASTM D5185m 1070	1121	1019	1154
Phosphorus	ppm	ASTM D5185m 1150	1025	1019	1026
Zinc	ppm	ASTM D5185m 1270	1279	1222	1268
Sulfur	ppm	ASTM D5185m 2060	3161	2964	3139

CONTAMINANTS

method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185m >35	9	33	10
Sodium	ppm	ASTM D5185m	▲ 197	▲ 1176	11
Potassium	ppm	ASTM D5185m >20	4	8	2
Glycol	%	*ASTM D2982	NEG	NEG	NEG

INFRA-RED




method	limit/base	current	history1	history2	
Soot %	%	*ASTM D7844 >7.5	0.2	0.3	1.4
Nitration	Abs/cm	*ASTM D7624 >20	6.5	11.1	9.8
Sulfation	Abs/.1mm	*ASTM D7415 >30	17.9	20.6	22.5

FLUID DEGRADATION

method	limit/base	current	history1	history2	
Oxidation	Abs/.1mm	*ASTM D7414 >25	13.6	15.3	16.8
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	8.7	12.6	8.4







OIL ANALYSIS REPORT

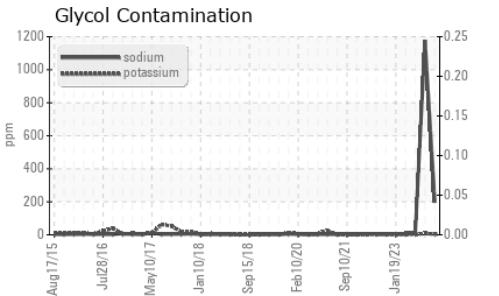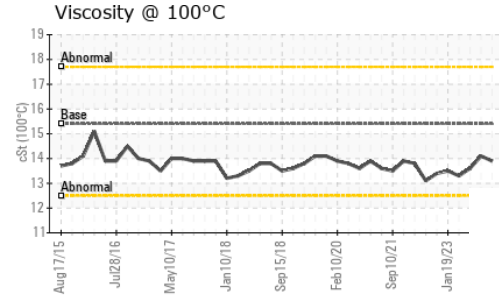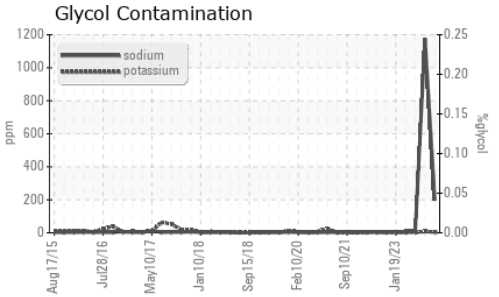

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	15.4	13.9	14.1	13.6

GRAPHS

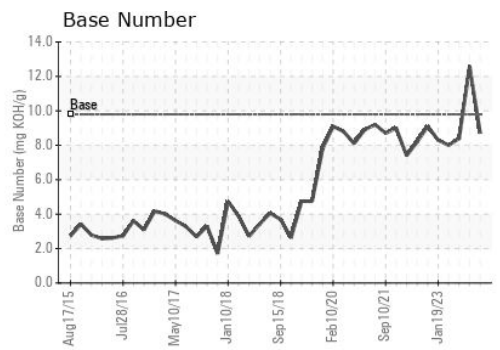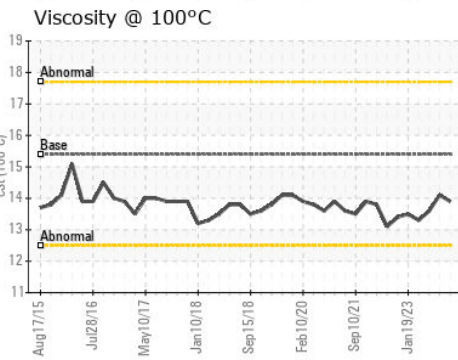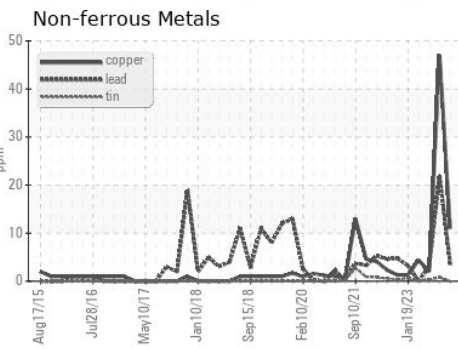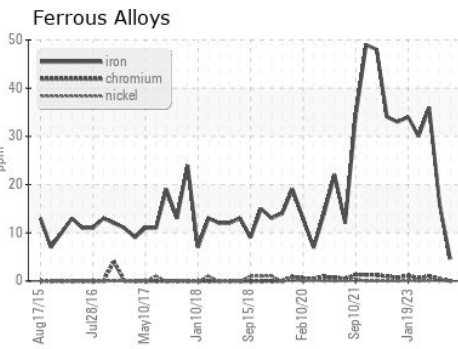

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0072183 **Received** : 20 Oct 2023
Lab Number : **05985346** **Diagnosed** : 25 Oct 2023
Unique Number : 10702641 **Diagnostician** : Jonathan Hester
Test Package : FLEET (Additional Tests: Glycol)

GFL Environmental - 094 - Cedartown
 2097 Buchanan Highway
 Cedartown, GA
 US 30125
 Contact: WILLIAM FOSTER
 william.foster@gflenv.com
 T: (800)207-6618
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)