




PROBLEM SUMMARY

Sample Rating Trend

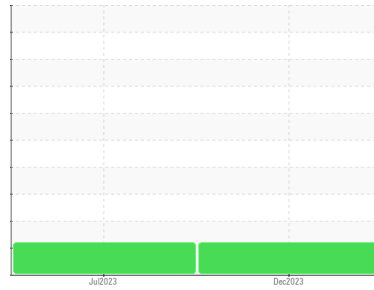


GLYCOL



Machine Id
413114
 Component
Diesel Engine
 Fluid
NOT GIVEN (--- GAL)

COMPONENT CONDITION SUMMARY

▲ Glycol Contamination

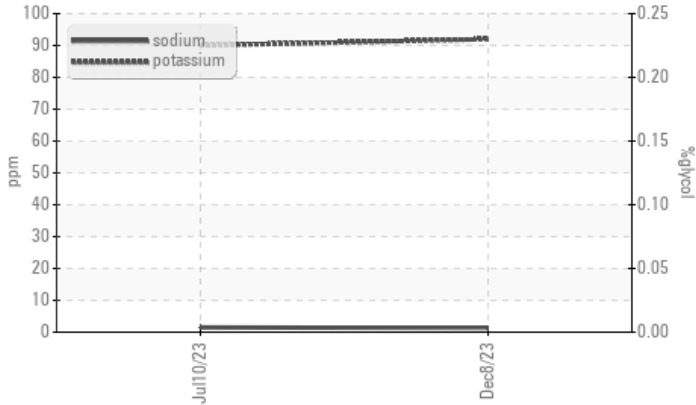

RECOMMENDATION

We advise that you check for the source of the coolant leak. Check for low coolant level. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

PROBLEMATIC TEST RESULTS

Sample Status				ABNORMAL	ABNORMAL	---
Potassium	ppm	ASTM D5185m	>20	▲ 92	▲ 90	---

Customer Id: GFL629
 Sample No.: GFL0096107
 Lab Number: 06033318
 Test Package: FLEET



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Jonathan Hester +1 919-379-4092 x4092
jhester@wearcheckusa.com

To change component or sample information:
 Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Fluid	---	---	?	Oil and filter change at the time of sampling has been noted.
Change Filter	---	---	?	Oil and filter change at the time of sampling has been noted.
Resample	---	---	?	We recommend an early resample to monitor this condition.
Check Glycol Access	---	---	?	We advise that you check for the source of the coolant leak.

HISTORICAL DIAGNOSIS

10 Jul 2023 Diag: Jonathan Hester

GLYCOL



Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor. Please specify the brand, type, and viscosity of the oil on your next sample. Metal levels are typical for a new component breaking in. Sodium and/or potassium levels are high. Fuel content negligible. Test for glycol is negative. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

view report





OIL ANALYSIS REPORT

Sample Rating Trend



GLYCOL



Machine Id
413114
 Component
Diesel Engine
 Fluid
NOT GIVEN (--- GAL)

DIAGNOSIS

▲ Recommendation

We advise that you check for the source of the coolant leak. Check for low coolant level. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

▲ Contamination

Sodium and/or potassium levels are high.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		GFL0096107	GFL0084526	---
Sample Date	Client Info		08 Dec 2023	10 Jul 2023	---
Machine Age	hrs	Client Info	1388	726	---
Oil Age	hrs	Client Info	662	726	---
Oil Changed	Client Info		Changed	Changed	---
Sample Status			ABNORMAL	ABNORMAL	---

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<1.0	1.5	---
Water	WC Method	>0.2	NEG	NEG	---

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >100	20	64	---
Chromium	ppm	ASTM D5185m >20	<1	2	---
Nickel	ppm	ASTM D5185m >4	0	<1	---
Titanium	ppm	ASTM D5185m	10	<1	---
Silver	ppm	ASTM D5185m >3	0	<1	---
Aluminum	ppm	ASTM D5185m >20	22	20	---
Lead	ppm	ASTM D5185m >40	<1	3	---
Copper	ppm	ASTM D5185m >330	5	35	---
Tin	ppm	ASTM D5185m >15	<1	3	---
Vanadium	ppm	ASTM D5185m	0	0	---
Cadmium	ppm	ASTM D5185m	0	0	---

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	132	50	---
Barium	ppm	ASTM D5185m	0	2	---
Molybdenum	ppm	ASTM D5185m	52	11	---
Manganese	ppm	ASTM D5185m	<1	7	---
Magnesium	ppm	ASTM D5185m	616	692	---
Calcium	ppm	ASTM D5185m	1378	1249	---
Phosphorus	ppm	ASTM D5185m	711	678	---
Zinc	ppm	ASTM D5185m	839	796	---
Sulfur	ppm	ASTM D5185m	3277	2971	---

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	12	45	---
Sodium	ppm	ASTM D5185m	1	2	---
Potassium	ppm	ASTM D5185m >20	▲ 92	▲ 90	---
Glycol	%	*ASTM D2982	NEG	NEG	---

INFRA-RED




	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >3	0.2	0.2	---
Nitration	Abs/cm	*ASTM D7624 >20	9.1	9.7	---
Sulfation	Abs/.1mm	*ASTM D7415 >30	20.0	21.7	---

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	14.9	17.6	---
Base Number (BN)	mg KOH/g	ASTM D2896	7.1	5.9	---







OIL ANALYSIS REPORT

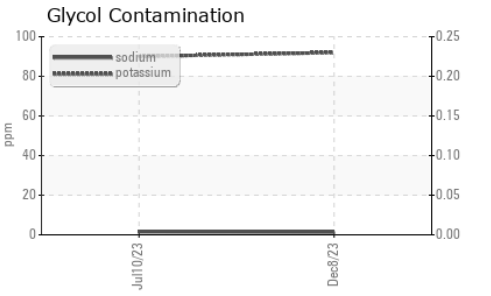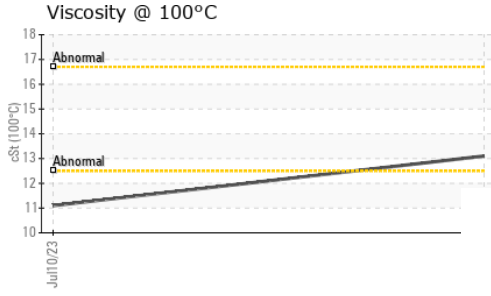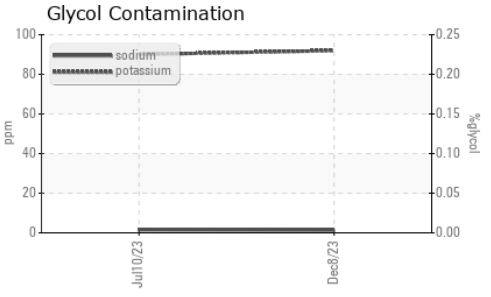

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	---
Precipitate	scalar	*Visual	NONE	NONE	---
Silt	scalar	*Visual	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---
Free Water	scalar	*Visual		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	13.1	11.1	---

GRAPHS

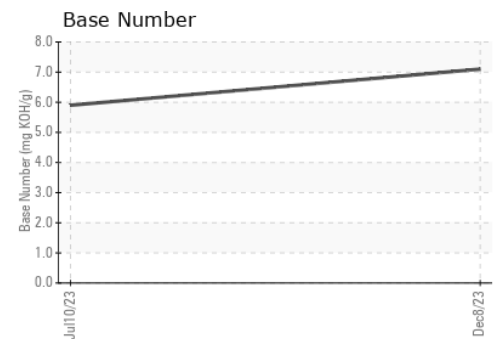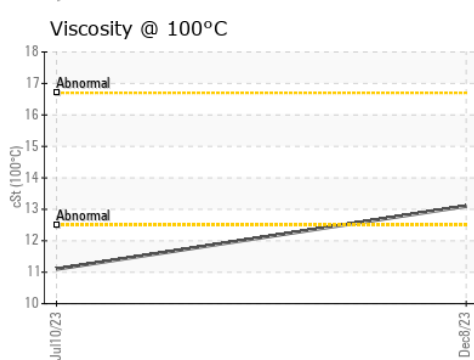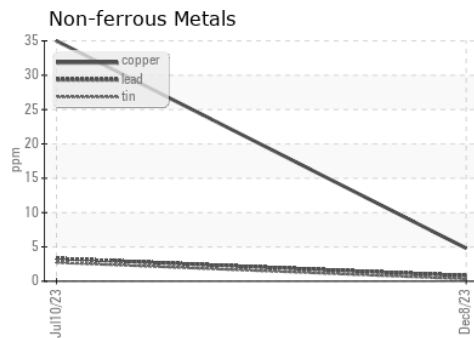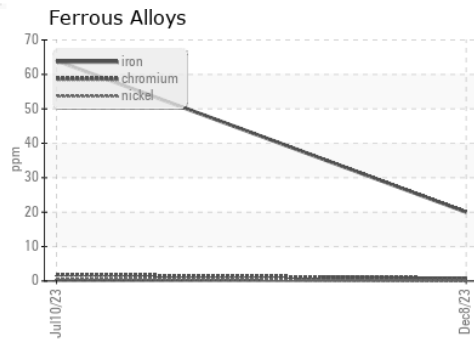

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0096107 **Received** : 13 Dec 2023
Lab Number : 06033318 **Diagnosed** : 18 Dec 2023
Unique Number : 10783109 **Diagnostician** : Jonathan Hester
Test Package : FLEET (Additional Tests: Glycol)

GFL Environmental - 629 - Northern A1
 3947 US 131 N
 Kalkaska, MI
 US 49646-8428
Contact: MITCH HERSHBERGER

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (231)624-0848
F: