

OIL ANALYSIS REPORT

Sample Rating Trend





Component Diesel Engine Fluid

PETRO CANADA DURON SHP 10W30 (--- QTS)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

Wear

Metal levels are typical for a new component breaking in.

Contamination

Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. There is no indication of any contamination in the oil.


Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

(TS)		Jul2022	Nov2022	Mar2023 Aug2023	Dec2023	
SAMPLE INFORM	MATION	method	limit/base	current	history1	history2
Sample Number		Client Info		PCA0113381	PCA0103085	PCA0094217
Sample Date		Client Info		01 Dec 2023	04 Aug 2023	10 Mar 2023
Machine Age	mls	Client Info		47696	36315	24775
Oil Age	mls	Client Info		0	0	0
Oil Changed		Client Info		Not Changd	Not Changd	Changed
Sample Status				NORMAL	NORMAL	NORMAL
CONTAMINATI	ON	method	limit/base	current	history1	history2
Fuel		WC Method	>5	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
WEAR METALS	S	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>100	36	25	37
Chromium	ppm	ASTM D5185m	>20	3	2	3
Nickel	ppm	ASTM D5185m	>4	<1	0	<1
Titanium	ppm	ASTM D5185m		0	0	<1
Silver	ppm	ASTM D5185m	>3	<1	<1	<1
Aluminum	ppm	ASTM D5185m	>20	44	25	24
Lead	ppm	ASTM D5185m	>40	0	2	0
Copper	ppm	ASTM D5185m	>330	383	135	158
Tin	ppm	ASTM D5185m	>15	2	2	3
Vanadium	ppm	ASTM D5185m		0	<1	0
Cadmium	ppm	ASTM D5185m		0	0	0
ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	2	15	19	40
Barium	ppm	ASTM D5185m	0	0	0	0
Molybdenum	ppm	ASTM D5185m	50	52	53	36
Manganese	ppm	ASTM D5185m	0	2	1	2
Magnesium	ppm	ASTM D5185m	950	839	837	495
Calcium	ppm	ASTM D5185m	1050	1257	1323	1536
Phosphorus	ppm	ASTM D5185m	995	920	923	676
Zinc	ppm	ASTM D5185m	1180	1148	1159	834
Sulfur	ppm	ASTM D5185m	2600	2605	3304	2589
	1-1-					
CONTAMINAN		method	limit/base	current	history1	history2
		method ASTM D5185m	limit/base >25	current 5	history1 4	history2 7
Silicon	TS					
Silicon Sodium	TS ppm	ASTM D5185m		5	4	7
Silicon Sodium	TS ppm ppm	ASTM D5185m ASTM D5185m	>25	5 2	4	7 3
Silicon Sodium Potassium INFRA-RED	TS ppm ppm	ASTM D5185m ASTM D5185m ASTM D5185m	>25 >20	5 2 156	4 3 95	7 3 70
Silicon Sodium Potassium INFRA-RED Soot %	TS ppm ppm ppm	ASTM D5185m ASTM D5185m ASTM D5185m method	>25 >20 limit/base	5 2 156 current	4 3 95 history1	7 3 70 history2
Silicon Sodium Potassium	TS ppm ppm ppm	ASTM D5185m ASTM D5185m ASTM D5185m method *ASTM D7844	>25 >20 limit/base >3	5 2 156 current 0.5	4 3 95 history1 0.3	7 3 70 history2 0.3
Silicon Sodium Potassium INFRA-RED Soot % Nitration	TS ppm ppm ppm % Abs/cm Abs/.1mm	ASTM D5185m ASTM D5185m ASTM D5185m *ASTM D7844 *ASTM D7624 *ASTM D7415	>25 >20 limit/base >3 >20	5 2 156 current 0.5 8.8	4 3 95 history1 0.3 6.9	7 3 70 history2 0.3 7.2
Silicon Sodium Potassium INFRA-RED Soot % Nitration Sulfation	TS ppm ppm ppm % Abs/cm Abs/.1mm	ASTM D5185m ASTM D5185m ASTM D5185m *ASTM D7844 *ASTM D7624 *ASTM D7415	>25 >20 limit/base >3 >20 >30	5 2 156 current 0.5 8.8 20.3	4 3 95 history1 0.3 6.9 19.5	7 3 70 history2 0.3 7.2 22.4



OIL ANALYSIS REPORT

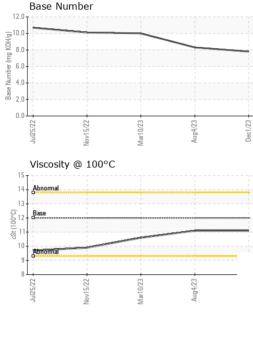





Contact/Location: MIKE LONGETTE - MILRUT