




PROBLEM SUMMARY

Sample Rating Trend

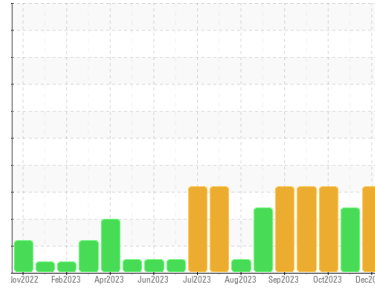


DIRT




Area
166
 Machine Id
223032-2
 Component
Diesel Engine
 Fluid
PETRO CANADA DURON SHP 15W40 (--- GAL)

COMPONENT CONDITION SUMMARY


▲ Ferrous Alloys

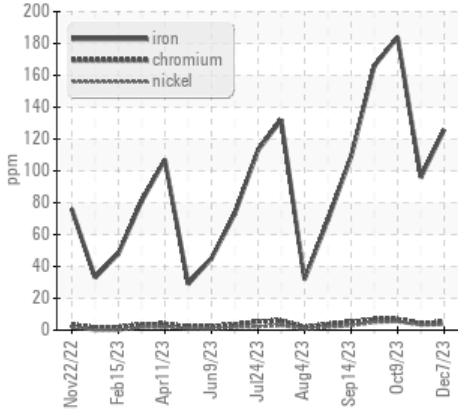

▲ Silicon (ppm)

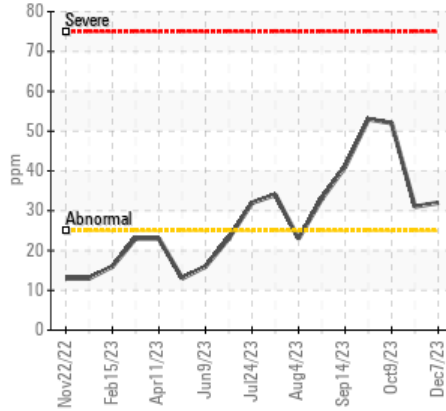

▲ Aluminum (ppm)

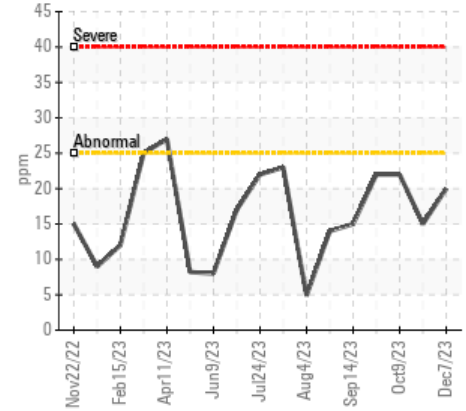

RECOMMENDATION

We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Resample at the next service interval to monitor.

PROBLEMATIC TEST RESULTS

Sample Status				ABNORMAL	ABNORMAL	ABNORMAL
Iron	ppm	ASTM D5185m	>100	▲ 126	96	▲ 184
Aluminum	ppm	ASTM D5185m	>25	▲ 20	▲ 15	▲ 22
Silicon	ppm	ASTM D5185m	>25	▲ 32	▲ 31	▲ 52

Customer Id: GFL166
 Sample No.: GFL0100241
 Lab Number: 06034365
 Test Package: FLEET



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Don Baldrige +1
don.b505@comcast.net

To change component or sample information:
 Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Check Dirt Access	---	---	?	We advise that you check the air filter, air induction system, and any areas where dirt may enter the component.

HISTORICAL DIAGNOSIS

07 Nov 2023 Diag: Don Baldrige

DIRT



We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Resample at the next service interval to monitor. All component wear rates are normal. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

[view report](#)



09 Oct 2023 Diag: Jonathan Hester

DIRT



We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor. Cylinder, crank, or cam shaft wear is indicated. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

[view report](#)



06 Oct 2023 Diag: Jonathan Hester

DIRT



We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Resample at the next service interval to monitor. Cylinder, crank, or cam shaft wear is indicated. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.


[view report](#)





OIL ANALYSIS REPORT

Sample Rating Trend

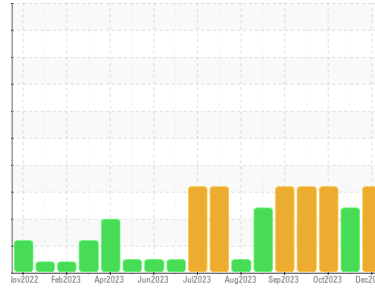

DIRT



Area
166
 Machine Id
223032-2

Component
Diesel Engine
 Fluid
PETRO CANADA DURON SHP 15W40 (--- GAL)

DIAGNOSIS

Recommendation

We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Resample at the next service interval to monitor.

Wear

Cylinder, crank, or cam shaft wear is indicated.

Contamination

Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	GFL0100241	GFL0091251	GFL0091232
Sample Date	Client Info	07 Dec 2023	07 Nov 2023	09 Oct 2023
Machine Age	hrs	19751	19632	235704
Oil Age	hrs	150	200	0
Oil Changed	Client Info	Not Chngd	Not Chngd	Changed
Sample Status		ABNORMAL	ABNORMAL	ABNORMAL

CONTAMINATION

method	limit/base	current	history1	history2
Fuel	WC Method >5	<1.0	<1.0	<1.0
Water	WC Method >0.2	NEG	NEG	NEG
Glycol	WC Method	NEG	NEG	NEG

WEAR METALS

method	limit/base	current	history1	history2
Iron	ppm ASTM D5185m >100	▲ 126	96	▲ 184
Chromium	ppm ASTM D5185m >20	5	4	7
Nickel	ppm ASTM D5185m >2	3	3	5
Titanium	ppm ASTM D5185m >2	<1	<1	<1
Silver	ppm ASTM D5185m >2	0	<1	1
Aluminum	ppm ASTM D5185m >25	▲ 20	▲ 15	▲ 22
Lead	ppm ASTM D5185m >40	<1	<1	<1
Copper	ppm ASTM D5185m >330	5	4	10
Tin	ppm ASTM D5185m >15	0	<1	<1
Vanadium	ppm ASTM D5185m	<1	<1	<1
Cadmium	ppm ASTM D5185m	0	<1	0

ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185m 0	11	6	3
Barium	ppm ASTM D5185m 0	0	<1	0
Molybdenum	ppm ASTM D5185m 60	116	98	110
Manganese	ppm ASTM D5185m 0	1	1	2
Magnesium	ppm ASTM D5185m 1010	846	910	940
Calcium	ppm ASTM D5185m 1070	1074	1055	1082
Phosphorus	ppm ASTM D5185m 1150	944	1017	985
Zinc	ppm ASTM D5185m 1270	1171	1177	1227
Sulfur	ppm ASTM D5185m 2060	2125	2816	2615

CONTAMINANTS

method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185m >25	▲ 32	▲ 31	▲ 52
Sodium	ppm ASTM D5185m	79	69	79
Potassium	ppm ASTM D5185m >20	5	6	7

INFRA-RED

method	limit/base	current	history1	history2
Soot %	% *ASTM D7844 >3	0.5	0.4	0.7
Nitration	Abs/cm *ASTM D7624 >20	9.9	8.6	10.7
Sulfation	Abs/.1mm *ASTM D7415 >30	19.0	18.3	20.0


FLUID DEGRADATION

method	limit/base	current	history1	history2
Oxidation	Abs/.1mm *ASTM D7414 >25	16.6	15.4	17.7
Base Number (BN)	mg KOH/g ASTM D2896 9.8	7.1	9.0	6.9




OIL ANALYSIS REPORT


▲ Silicon (ppm)

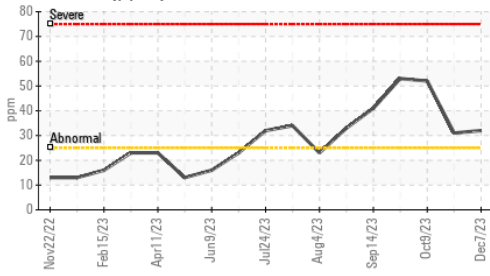


▲ Aluminum (ppm)

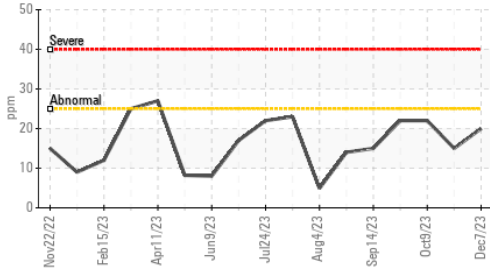


▲ Aluminum (ppm)

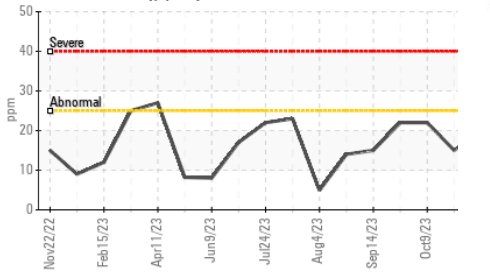

Base Number

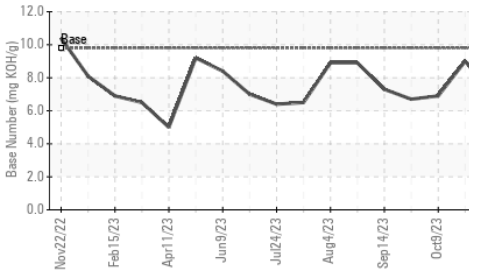

Viscosity @ 100°C

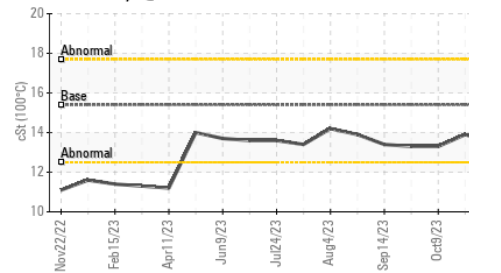

VISUAL


	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES


	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	15.4	13.5	13.9

GRAPHS


▲ Ferrous Alloys

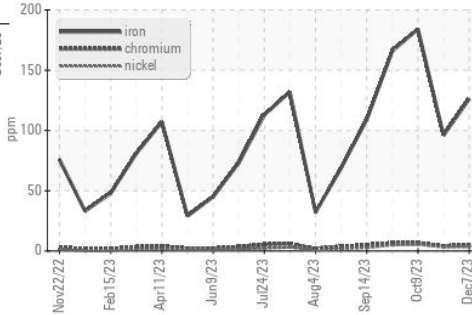


Non-ferrous Metals

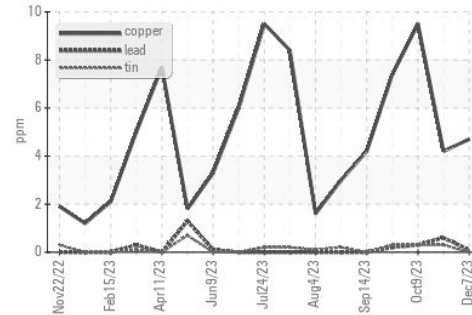

Viscosity @ 100°C

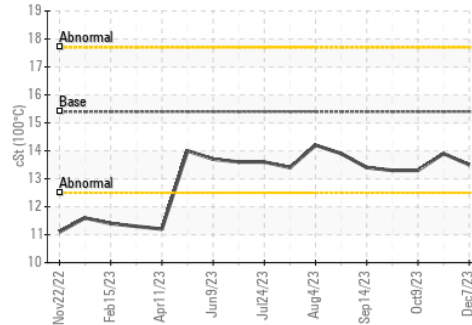

Base Number

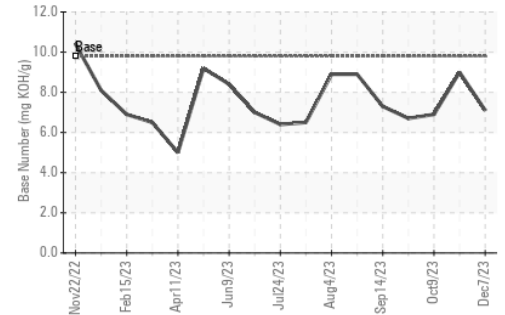

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
 Sample No. : GFL0100241
 Lab Number : 06034365
 Unique Number : 10789594
 Test Package : FLEET

GFL Environmental - 166 - Phenix City
 18 Old Brickyard Rd
 Phenix City, AL
 US 36869
 Contact: DEAN PEACE JR
 dean.peace@gflenv.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:
F: