


OIL ANALYSIS REPORT

(SPG405640) Air Gas - Tractor

Diesel Engine

PETRO CANADA DURON SHP 10W30 (11 GAL)

[Air Gas - Tractor] 314A314006

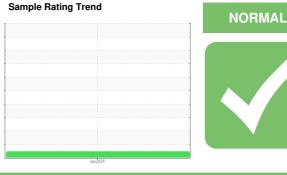

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

Metal levels are typical for a components first oil change.

Contamination

Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. There is no indication of any contamination in the oil.


Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

GAL)				Jan2024		
SAMPLE INFOR	MATION	method	limit/base	current	history1	history2
Sample Number		Client Info		PCA0096895		
Sample Date		Client Info		10 Jan 2024		
Machine Age	days	Client Info		90		
Oil Age	days	Client Info		90		
Oil Changed		Client Info		Changed		
Sample Status				NORMAL		
CONTAMINAT	ION	method	limit/base	current	history1	history2
Fuel		WC Method	>5	<1.0		
Water		WC Method	>0.2	NEG		
Glycol		WC Method		NEG		
WEAR METAL	S	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>80	35		
Chromium	ppm	ASTM D5185m	>5	3		
Nickel	ppm	ASTM D5185m	>2	<1		
Titanium	ppm	ASTM D5185m		<1		
Silver	ppm	ASTM D5185m	>3	<1		
Aluminum	ppm	ASTM D5185m	>30	22		
Lead	ppm	ASTM D5185m	>30	<1		
Copper	ppm	ASTM D5185m	>150	18		
Tin	ppm	ASTM D5185m	>5	3		
Vanadium	ppm	ASTM D5185m		<1		
Cadmium	ppm	ASTM D5185m		0		
ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	2	9		
Barium	ppm	ASTM D5185m	0	<1		
Molybdenum	ppm	ASTM D5185m	50	60		
Manganese	ppm	ASTM D5185m	0	1		
Magnesium	ppm	ASTM D5185m	950	915		
Calcium	ppm	ASTM D5185m	1050	1199		
Phosphorus	ppm	ASTM D5185m	995	980		
Zinc	ppm	ASTM D5185m	1180	1288		
Sulfur	ppm	ASTM D5185m	2600	2504		
CONTAMINAN	ITS	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>20	4		
Sodium	ppm	ASTM D5185m		4		
Potassium	ppm	ASTM D5185m	>20	40		
INFRA-RED		method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844	>3	0.7		
Nitration	Abs/cm	*ASTM D7624	>20	8.6		
Sulfation	Abs/.1mm	*ASTM D7415	>30	21.1		
FLUID DEGRAI	NOITAC	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414	>25	18.2		
Base Number (BN)	mg KOH/g	ASTM D2896		7.1		



OIL ANALYSIS REPORT

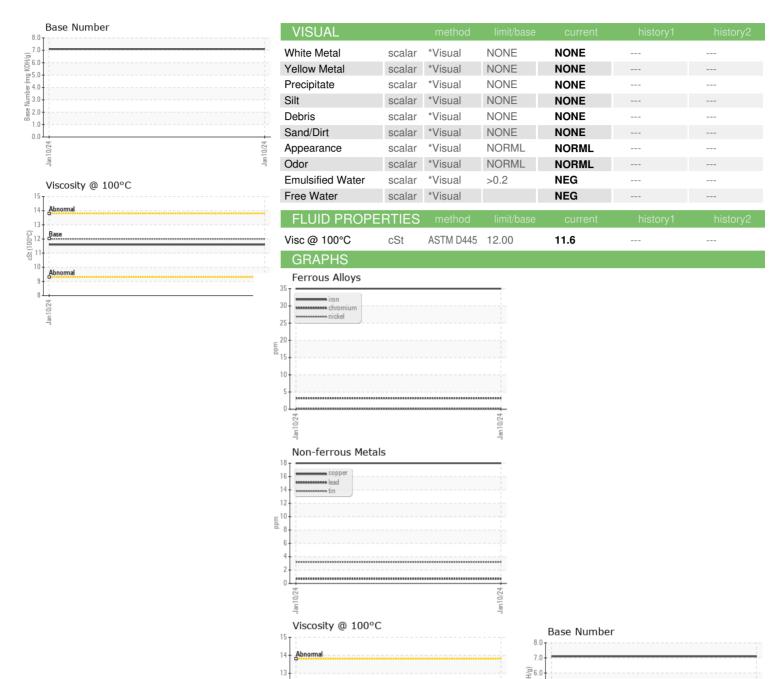





Certificate L2367

Laboratory Sample No.

Lab Number Unique Number

: PCA0096895 : 06061860 : 10833242 Test Package : FLEET

To discuss this sample report, contact Customer Service at 1-800-237-1369.

cSt (100°C)

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 : 16 Jan 2024 Recieved Diagnosed

: 17 Jan 2024 : Wes Davis Diagnostician

Transervice - Shop 3140 - Platte River 2455 S Platte River

Jumper (n 3.0

1.0 0.0

> Denver, CO US 80223 Contact: Mike Duran

mduran@transervice.com T:

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation. Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

F: