




# OIL ANALYSIS REPORT

Sample Rating Trend

**NORMAL**

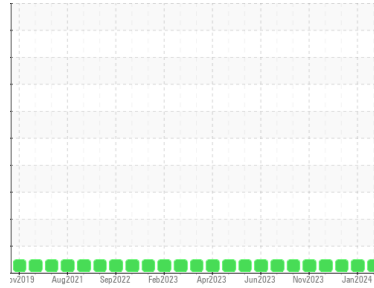

Machine Id  
**929088-205308**

Component  
**Diesel Engine**

Fluid  
**PETRO CANADA DURON SHP 15W40 (--- GAL)**

## DIAGNOSIS

### Recommendation

Resample at the next service interval to monitor.

### Wear

All component wear rates are normal.

### Contamination

There is no indication of any contamination in the oil.

### Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

## SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	<b>GFL0098354</b>	GFL0098322	GFL0098343
Sample Date	Client Info	<b>24 Jan 2024</b>	02 Jan 2024	12 Dec 2023
Machine Age	hrs	<b>12265</b>	12112	14198
Oil Age	hrs	<b>600</b>	700	150
Oil Changed	Client Info	<b>Changed</b>	Not Changd	Not Changd
Sample Status		<b>NORMAL</b>	NORMAL	NORMAL

## CONTAMINATION

method	limit/base	current	history1	history2
Fuel	WC Method >5	<b>&lt;1.0</b>	<1.0	<1.0
Water	WC Method >0.2	<b>NEG</b>	NEG	NEG
Glycol	WC Method	<b>NEG</b>	NEG	NEG

## WEAR METALS

method	limit/base	current	history1	history2
Iron	ppm ASTM D5185m >100	<b>7</b>	2	1
Chromium	ppm ASTM D5185m >20	<b>&lt;1</b>	0	0
Nickel	ppm ASTM D5185m >4	<b>0</b>	0	<1
Titanium	ppm ASTM D5185m	<b>&lt;1</b>	0	0
Silver	ppm ASTM D5185m >3	<b>0</b>	0	0
Aluminum	ppm ASTM D5185m >20	<b>&lt;1</b>	<1	1
Lead	ppm ASTM D5185m >40	<b>&lt;1</b>	0	0
Copper	ppm ASTM D5185m >330	<b>&lt;1</b>	0	0
Tin	ppm ASTM D5185m >15	<b>&lt;1</b>	0	0
Vanadium	ppm ASTM D5185m	<b>&lt;1</b>	0	0
Cadmium	ppm ASTM D5185m	<b>&lt;1</b>	0	0

## ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185m 0	<b>&lt;1</b>	<1	2
Barium	ppm ASTM D5185m 0	<b>0</b>	0	0
Molybdenum	ppm ASTM D5185m 60	<b>53</b>	57	57
Manganese	ppm ASTM D5185m 0	<b>&lt;1</b>	0	<1
Magnesium	ppm ASTM D5185m 1010	<b>972</b>	930	918
Calcium	ppm ASTM D5185m 1070	<b>986</b>	981	996
Phosphorus	ppm ASTM D5185m 1150	<b>1004</b>	1035	1041
Zinc	ppm ASTM D5185m 1270	<b>1203</b>	1229	1237
Sulfur	ppm ASTM D5185m 2060	<b>2961</b>	2997	3064

## CONTAMINANTS

method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185m >25	<b>3</b>	2	2
Sodium	ppm ASTM D5185m	<b>3</b>	2	2
Potassium	ppm ASTM D5185m >20	<b>&lt;1</b>	0	1

## INFRA-RED



method	limit/base	current	history1	history2
Soot %	% *ASTM D7844 >3	<b>0.3</b>	0.2	0.2
Nitration	Abs/cm *ASTM D7624 >20	<b>6.6</b>	5.5	5.6
Sulfation	Abs/.1mm *ASTM D7415 >30	<b>18.6</b>	17.3	17.9

## FLUID DEGRADATION

method	limit/base	current	history1	history2
Oxidation	Abs/.1mm *ASTM D7414 >25	<b>14.1</b>	13.3	13.4
Base Number (BN)	mg KOH/g ASTM D2896 9.8	<b>8.1</b>	8.7	8.5







# OIL ANALYSIS REPORT

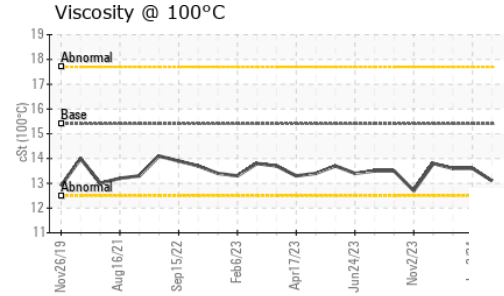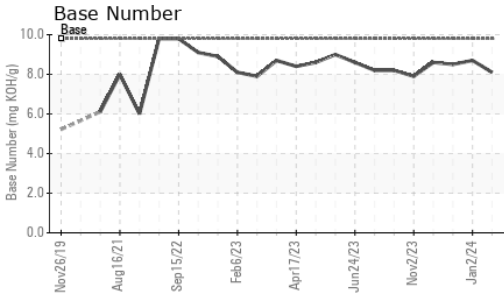

PARAMETER	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	15.4	<b>13.1</b>	13.6	13.6

## GRAPHS

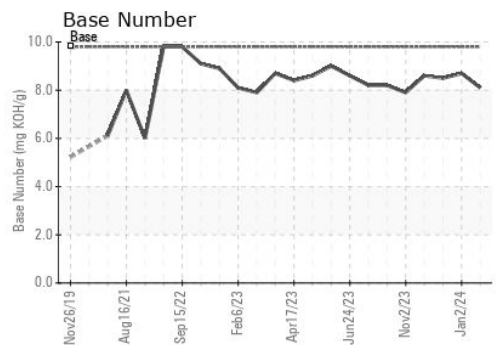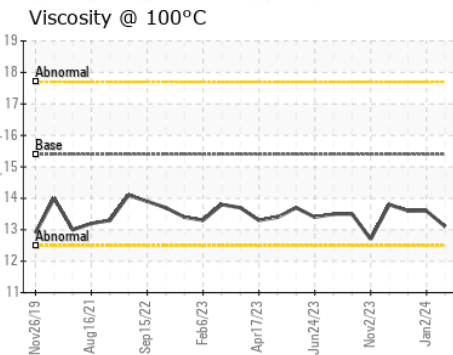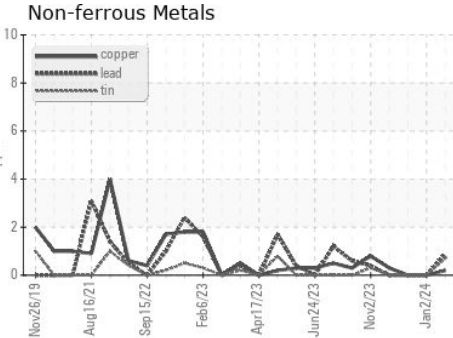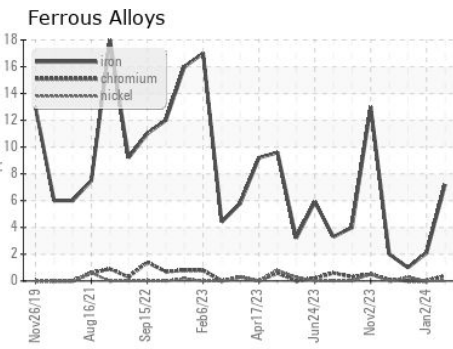

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : GFL0098354 **Received** : 31 Jan 2024  
**Lab Number** : **06075370** **Diagnosed** : 01 Feb 2024  
**Unique Number** : 10857461 **Diagnostician** : Wes Davis  
**Test Package** : FLEET

**GFL Environmental - 822 - Springfield Hauling**  
 2120 West Bennett Street  
 Springfield, MO  
 US 65807  
 Contact: Dennis Moore  
 dennis.moore@gflenv.com  
 T: (417)403-3641  
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.  
 \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.  
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)