




OIL ANALYSIS REPORT

Sample Rating Trend

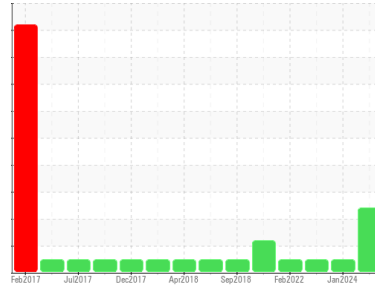

DIRT



Area
(EPI996)

Machine Id
10700

Component
Diesel Engine

Fluid
PETRO CANADA DURON SHP 15W40 (11 GAL)

DIAGNOSIS

Recommendation

We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		GFL0068820	GFL0068882	GFL0044613
Sample Date	Client Info		13 Mar 2024	13 Jan 2024	17 Jan 2023
Machine Age	hrs	Client Info	1709	1526	0
Oil Age	hrs	Client Info	0	0	0
Oil Changed	Client Info		Not Chngd	Changed	Changed
Sample Status			ABNORMAL	NORMAL	NORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>3.0	<1.0	<1.0	<1.0
Water	WC Method	>0.2	NEG	NEG	NEG
Glycol	WC Method		NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >75	55	37	61
Chromium	ppm	ASTM D5185m >5	7	6	3
Nickel	ppm	ASTM D5185m >4	0	0	0
Titanium	ppm	ASTM D5185m >2	<1	<1	2
Silver	ppm	ASTM D5185m >2	0	0	0
Aluminum	ppm	ASTM D5185m >15	10	7	10
Lead	ppm	ASTM D5185m >25	0	<1	<1
Copper	ppm	ASTM D5185m >100	3	3	36
Tin	ppm	ASTM D5185m >4	<1	0	<1
Vanadium	ppm	ASTM D5185m	0	<1	0
Cadmium	ppm	ASTM D5185m	0	0	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 0	6	3	5
Barium	ppm	ASTM D5185m 0	0	0	0
Molybdenum	ppm	ASTM D5185m 60	56	56	69
Manganese	ppm	ASTM D5185m 0	<1	<1	<1
Magnesium	ppm	ASTM D5185m 1010	924	947	809
Calcium	ppm	ASTM D5185m 1070	1010	1024	1052
Phosphorus	ppm	ASTM D5185m 1150	1011	1035	878
Zinc	ppm	ASTM D5185m 1270	1193	1224	1096
Sulfur	ppm	ASTM D5185m 2060	3037	3061	2817

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	▲ 27	17	8
Sodium	ppm	ASTM D5185m	6	6	26
Potassium	ppm	ASTM D5185m >20	<1	2	5

INFRA-RED

	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >6	0.5	0.6	1.8
Nitration	Abs/cm	*ASTM D7624 >20	7.2	7.0	10.2
Sulfation	Abs/.1mm	*ASTM D7415 >30	19.1	18.3	22.2


FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	14.6	13.5	15.7
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	8.3	8.6	8.2




OIL ANALYSIS REPORT


▲ Silicon (ppm)

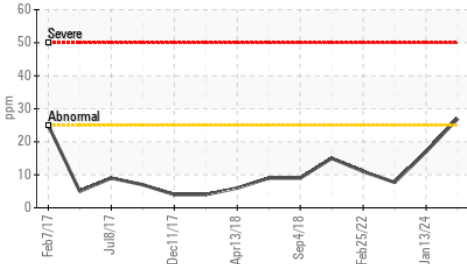


● Aluminum (ppm)

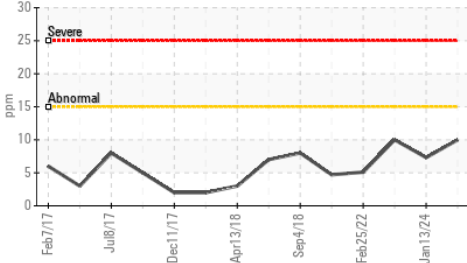

Base Number

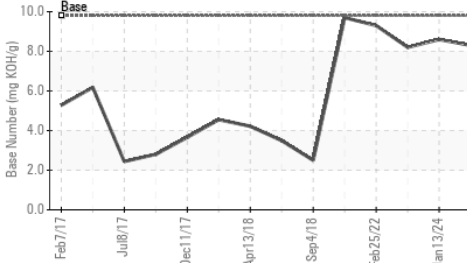

Viscosity @ 100°C

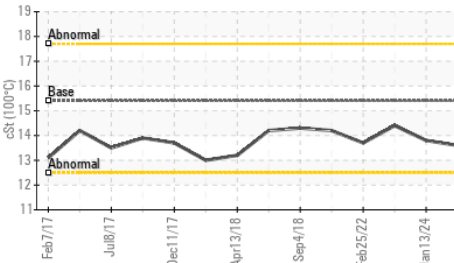


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	15.4	13.6	13.8	14.4

GRAPHS


Ferrous Alloys

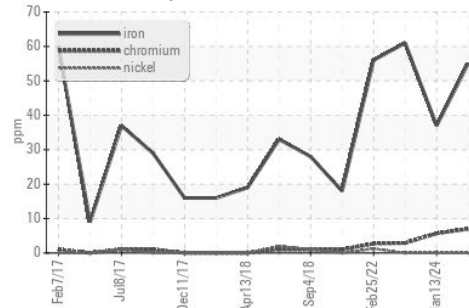


Non-ferrous Metals

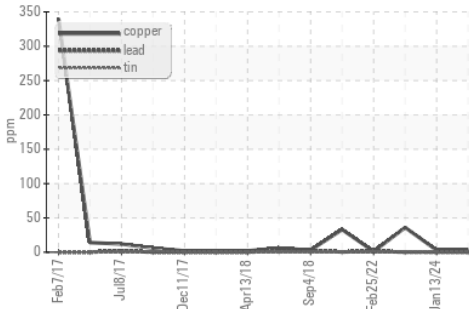

Viscosity @ 100°C

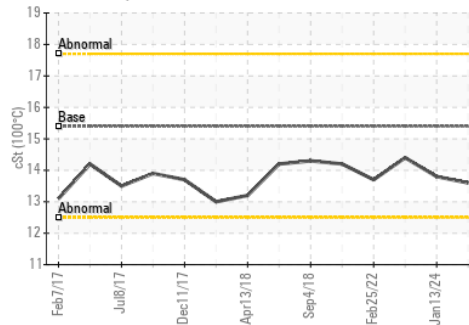

Base Number

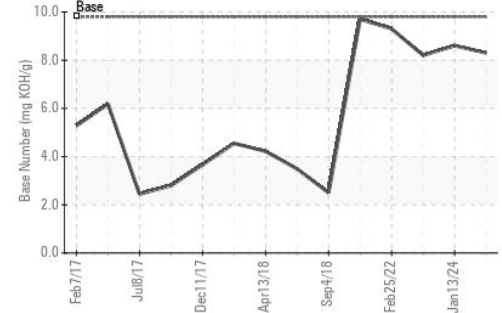

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0068820
Lab Number : 06120012
Unique Number : 10928845
Test Package : FLEET

Received : 15 Mar 2024
Tested : 18 Mar 2024
Diagnosed : 19 Mar 2024 - Don Baldrige

GFL Environmental - 072 - Americus - Transwaste
 361 McMath Mill Road
 Americus, GA
 US 31719

Contact: RICHARD HEINZERLING
 richard.heinzerling@gflenv.com

T: (229)924-3669

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

F: