




OIL ANALYSIS REPORT

Sample Rating Trend

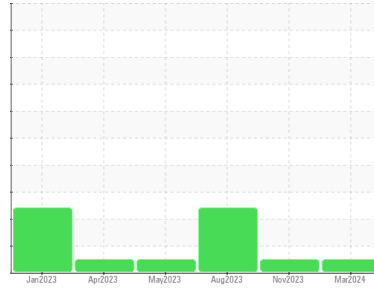

NORMAL



Machine Id
528075
 Component
Diesel Engine
 Fluid
PETRO CANADA DURON SHP 15W40 (--- GAL)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		GFL0092770	GFL0092801	GFL0080831
Sample Date	Client Info		18 Mar 2024	15 Nov 2023	28 Aug 2023
Machine Age	mls	Client Info	206043	206043	206043
Oil Age	mls	Client Info	197633	197633	206043
Oil Changed	Client Info		Not Chngd	Not Chngd	Not Chngd
Sample Status			NORMAL	NORMAL	ABNORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>3.0	<1.0	<1.0	<1.0
Water	WC Method	>0.2	NEG	NEG	NEG
Glycol	WC Method		NEG	0.0	0.0

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >120	20	54	▲ 145
Chromium	ppm	ASTM D5185m >20	1	2	3
Nickel	ppm	ASTM D5185m >5	1	0	<1
Titanium	ppm	ASTM D5185m >2	<1	<1	<1
Silver	ppm	ASTM D5185m >2	0	0	0
Aluminum	ppm	ASTM D5185m >20	2	4	6
Lead	ppm	ASTM D5185m >40	<1	<1	0
Copper	ppm	ASTM D5185m >330	10	4	4
Tin	ppm	ASTM D5185m >15	1	<1	<1
Vanadium	ppm	ASTM D5185m	0	0	0
Cadmium	ppm	ASTM D5185m	<1	0	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 0	1	8	12
Barium	ppm	ASTM D5185m 0	0	0	0
Molybdenum	ppm	ASTM D5185m 60	65	70	72
Manganese	ppm	ASTM D5185m 0	<1	<1	1
Magnesium	ppm	ASTM D5185m 1010	960	1053	1032
Calcium	ppm	ASTM D5185m 1070	1123	1165	1124
Phosphorus	ppm	ASTM D5185m 1150	922	1119	1092
Zinc	ppm	ASTM D5185m 1270	1212	1377	1286
Sulfur	ppm	ASTM D5185m 2060	2784	3561	3852

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	5	19	▲ 31
Sodium	ppm	ASTM D5185m	1	114	132
Potassium	ppm	ASTM D5185m >20	3	3	2

INFRA-RED



	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >4	0.8	0.2	0.2
Nitration	Abs/cm	*ASTM D7624 >20	8.7	4.8	4.7
Sulfation	Abs/.1mm	*ASTM D7415 >30	20.1	17.6	17.0

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	15.7	12.7	12.3
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	7.3	9.8	9.4







OIL ANALYSIS REPORT

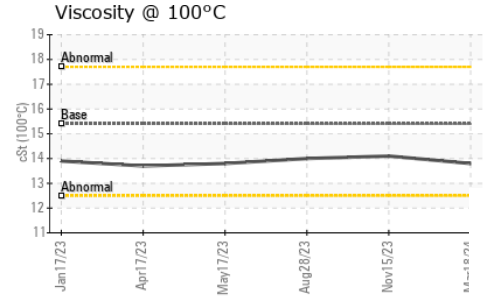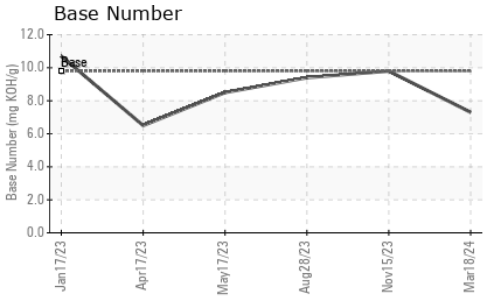

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	15.4	13.8	14.1	14.0

GRAPHS

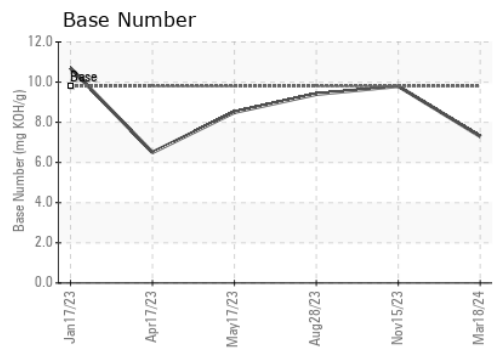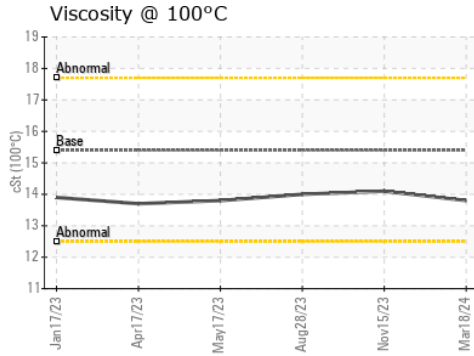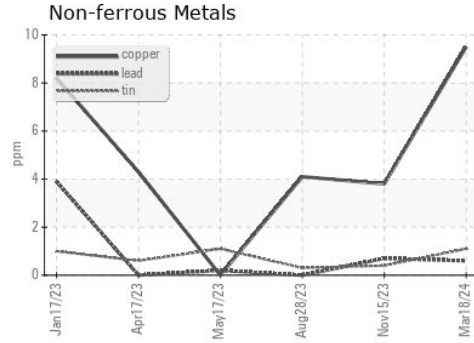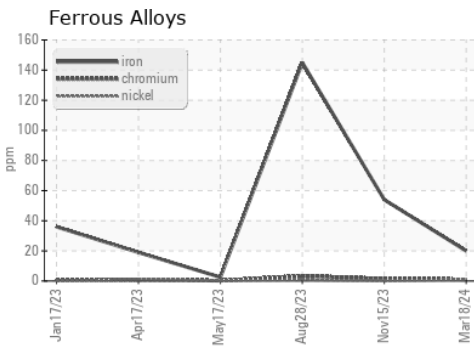

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0092770 **Received** : 01 Apr 2024
Lab Number : **06134669** **Tested** : 02 Apr 2024
Unique Number : 10954134 **Diagnosed** : 02 Apr 2024 - Wes Davis
Test Package : FLEET

GFL Environmental - 455 - Flint
 2051 W. Bristol Rd
 Flint Township, MI
 US 48507
 Contact: MARK WOMBLE
 mwomble@gflenv.com
 T: (586)825-9514
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)