


OIL ANALYSIS REPORT



Area
BEELMAN
 Machine Id
CATERPILLAR 980M BEELMAN (S/N CKRS00698)
 Component
Diesel Engine
 Fluid
DIESEL ENGINE OIL SAE 15W40 (--- GAL)

Sample Rating Trend

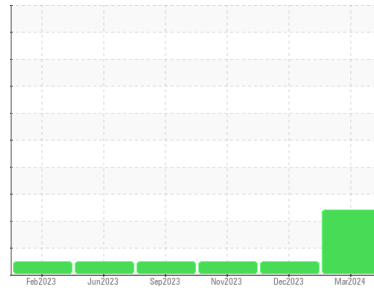

GLYCOL



DIAGNOSIS

Recommendation

We advise that you check for the source of the coolant leak. Check for low coolant level. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

Contamination

Sodium and/or potassium levels are high.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil.

| SAMPLE INFORMATION | | method | limit/base | current | history1 | history2 |
|--------------------|-------------|-------------|------------|--------------------|-------------|-------------|
| Sample Number | Client Info | | | PCA0115496 | LW0008247 | LW0007641 |
| Sample Date | Client Info | | | 28 Mar 2024 | 19 Dec 2023 | 03 Nov 2023 |
| Machine Age | hrs | Client Info | | 15210 | 14467 | 14151 |
| Oil Age | hrs | Client Info | | 15210 | 14467 | 14151 |
| Oil Changed | Client Info | | | Not Chngd | Not Chngd | Not Chngd |
| Sample Status | | | | ABNORMAL | NORMAL | NORMAL |

| CONTAMINATION | | method | limit/base | current | history1 | history2 |
|---------------|-----------|--------|------------|----------------|----------|----------|
| Fuel | WC Method | >5 | | <1.0 | <1.0 | <1.0 |
| Water | WC Method | >0.2 | | NEG | NEG | NEG |

| WEAR METALS | | method | limit/base | current | history1 | history2 |
|-------------|-----|-------------|------------|--------------|----------|----------|
| Iron | ppm | ASTM D5185m | >100 | 11 | 6 | 4 |
| Chromium | ppm | ASTM D5185m | >20 | <1 | 0 | 0 |
| Nickel | ppm | ASTM D5185m | >2 | 0 | 0 | 0 |
| Titanium | ppm | ASTM D5185m | >2 | <1 | 0 | 0 |
| Silver | ppm | ASTM D5185m | >2 | 0 | 0 | 0 |
| Aluminum | ppm | ASTM D5185m | >25 | <1 | 1 | 1 |
| Lead | ppm | ASTM D5185m | >40 | 0 | <1 | 0 |
| Copper | ppm | ASTM D5185m | >330 | 1 | 1 | <1 |
| Tin | ppm | ASTM D5185m | >15 | 0 | 0 | 0 |
| Vanadium | ppm | ASTM D5185m | | 0 | <1 | 0 |
| Cadmium | ppm | ASTM D5185m | | 0 | 0 | 0 |

| ADDITIVES | | method | limit/base | current | history1 | history2 |
|------------|-----|-------------|------------|--------------|----------|----------|
| Boron | ppm | ASTM D5185m | 250 | 13 | 18 | 29 |
| Barium | ppm | ASTM D5185m | 10 | 0 | 0 | 0 |
| Molybdenum | ppm | ASTM D5185m | 100 | 38 | 26 | 27 |
| Manganese | ppm | ASTM D5185m | | <1 | <1 | 0 |
| Magnesium | ppm | ASTM D5185m | 450 | 744 | 709 | 795 |
| Calcium | ppm | ASTM D5185m | 3000 | 1333 | 1340 | 1263 |
| Phosphorus | ppm | ASTM D5185m | 1150 | 1046 | 927 | 1007 |
| Zinc | ppm | ASTM D5185m | 1350 | 1205 | 1165 | 1259 |
| Sulfur | ppm | ASTM D5185m | 4250 | 3885 | 3223 | 3489 |


| CONTAMINANTS | | method | limit/base | current | history1 | history2 |
|--------------|-----|-------------|------------|--------------|----------|----------|
| Silicon | ppm | ASTM D5185m | >25 | 3 | 5 | 3 |
| Sodium | ppm | ASTM D5185m | >158 | ▲ 128 | 33 | 17 |
| Potassium | ppm | ASTM D5185m | >20 | ▲ 53 | 12 | 7 |
| Glycol | % | *ASTM D2982 | | NEG | NEG | NEG |

| INFRA-RED | | method | limit/base | current | history1 | history2 |
|-----------|----------|-------------|------------|-------------|----------|----------|
| Soot % | % | *ASTM D7844 | >3 | 0.2 | 0.1 | 0.1 |
| Nitration | Abs/cm | *ASTM D7624 | >20 | 9.4 | 8.1 | 7.2 |
| Sulfation | Abs/.1mm | *ASTM D7415 | >30 | 20.0 | 19.6 | 18.9 |


| FLUID DEGRADATION | | method | limit/base | current | history1 | history2 |
|-------------------|----------|-------------|------------|-------------|----------|----------|
| Oxidation | Abs/.1mm | *ASTM D7414 | >25 | 14.9 | 14.3 | 13.7 |
| Base Number (BN) | mg KOH/g | ASTM D2896 | 8.5 | 7.7 | 8.6 | 9.1 |

OIL ANALYSIS REPORT


FT-IR (Direct Trend)

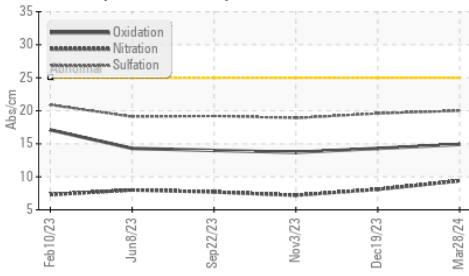


Glycol Contamination

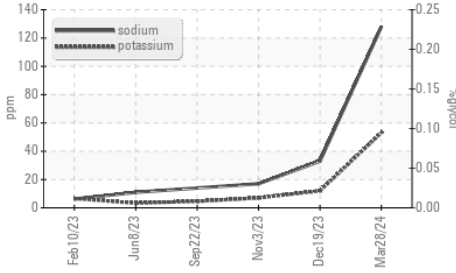


Viscosity @ 100°C

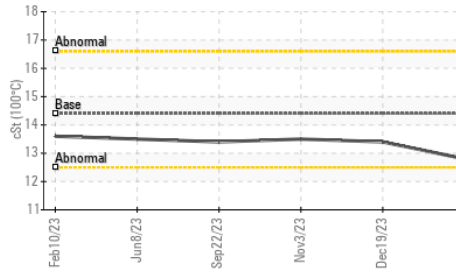

Glycol Contamination

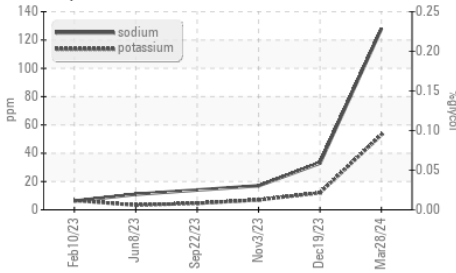









Viscosity @ 100°C

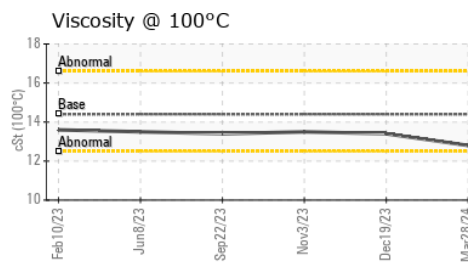

| PARAMETER | method | limit/base | current | history1 | history2 |
|------------------|--------|------------|---------|----------|----------|
| White Metal | scalar | *Visual | NONE | NONE | NONE |
| Yellow Metal | scalar | *Visual | NONE | NONE | NONE |
| Precipitate | scalar | *Visual | NONE | NONE | NONE |
| Silt | scalar | *Visual | NONE | NONE | NONE |
| Debris | scalar | *Visual | NONE | NONE | NONE |
| Sand/Dirt | scalar | *Visual | NONE | NONE | NONE |
| Appearance | scalar | *Visual | NORML | NORML | NORML |
| Odor | scalar | *Visual | NORML | NORML | NORML |
| Emulsified Water | scalar | *Visual | >0.2 | NEG | NEG |
| Free Water | scalar | *Visual | | NEG | NEG |

| PARAMETER | method | limit/base | current | history1 | history2 |
|--------------|--------|------------|---------|----------|----------|
| Visc @ 100°C | cSt | ASTM D445 | 14.4 | 12.8 | 13.4 |

GRAPHS

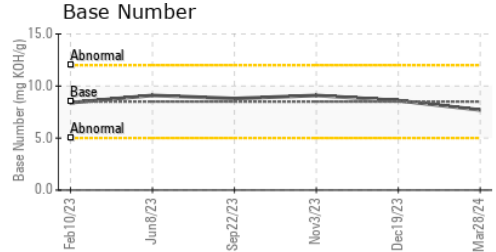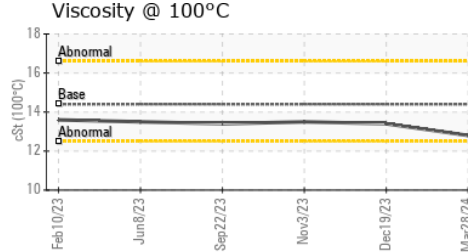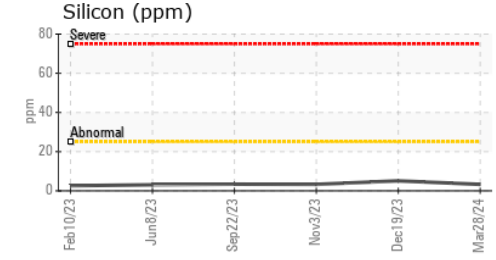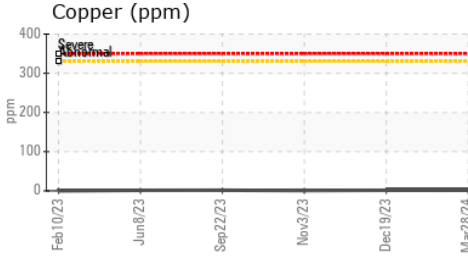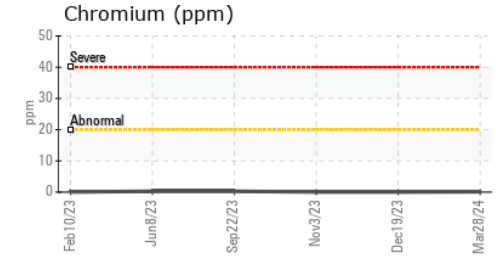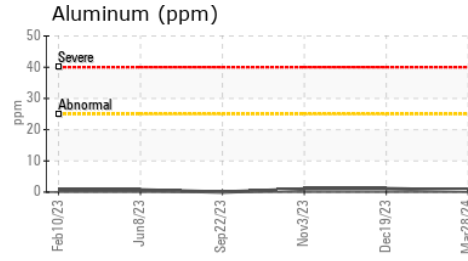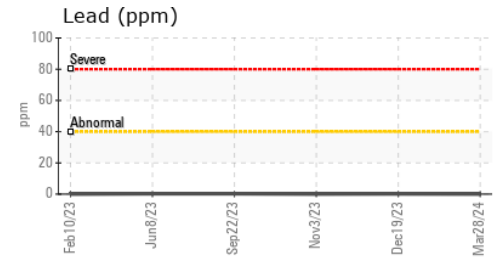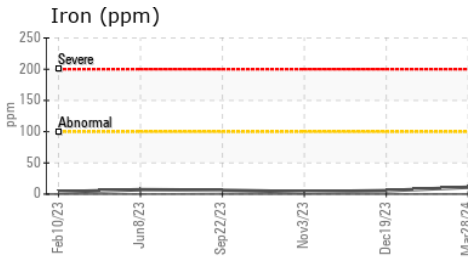

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : PCA0115496 **Received** : 02 Apr 2024
Lab Number : 06136041 **Tested** : 04 Apr 2024
Unique Number : 10955506 **Diagnosed** : 04 Apr 2024 - Jonathan Hester
Test Package : MOB 1 (Additional Tests: Glycol, TBN)

CHICAGO MACHINERY INC
 3142 EAST LINCOLN
 LYNWOOD, IL
 US 60411-7728
 Contact: Mike Korbelik
 mike@chicagomachineryinc.com
 T: (708)758-2060
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)