

Machine Id
EMPTY CAN ELEVATOR
 Component
Hydraulic System
 Fluid
MOBIL DTE 25 (180 GAL)

DIAGNOSIS

Recommendation
 We recommend you service the filters on this component. Resample at the next service interval to monitor.

Wear
 All component wear rates are normal.

Contamination
 There is a high amount of particulates present in the oil.

Fluid Condition
 The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		PCA0118385	PCA0103594	PCA0103610
Sample Date	Client Info		27 Mar 2024	01 Oct 2023	20 Sep 2023
Machine Age	hrs	Client Info	0	0	0
Oil Age	hrs	Client Info	0	0	0
Oil Changed	Client Info		N/A	N/A	N/A
Sample Status			ABNORMAL	ABNORMAL	ABNORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.05	NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185m	>20	5	2	2
Chromium	ppm	ASTM D5185m	>20	<1	0	0
Nickel	ppm	ASTM D5185m	>20	<1	0	0
Titanium	ppm	ASTM D5185m		<1	0	0
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m	>20	2	2	2
Lead	ppm	ASTM D5185m	>20	1	0	0
Copper	ppm	ASTM D5185m	>20	2	<1	<1
Tin	ppm	ASTM D5185m	>20	1	0	0
Vanadium	ppm	ASTM D5185m		<1	0	0
Cadmium	ppm	ASTM D5185m		<1	0	0

ADDITIVES

	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185m		0	0	0
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		5	5	5
Manganese	ppm	ASTM D5185m		<1	0	0
Magnesium	ppm	ASTM D5185m		4	5	5
Calcium	ppm	ASTM D5185m		100	101	101
Phosphorus	ppm	ASTM D5185m		427	407	412
Zinc	ppm	ASTM D5185m		592	637	648
Sulfur	ppm	ASTM D5185m		3036	3782	4110

CONTAMINANTS

	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185m	>15	2	1	1
Sodium	ppm	ASTM D5185m		<1	2	2
Potassium	ppm	ASTM D5185m	>20	3	2	2

FLUID CLEANLINESS


	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>10000	▲ 121091	▲ 85175	▲ 89332
Particles >6µm	ASTM D7647	>2500	▲ 67538	▲ 29653	▲ 32387
Particles >14µm	ASTM D7647	>640	▲ 4940	▲ 872	▲ 1036
Particles >21µm	ASTM D7647	>160	▲ 342	108	▲ 131
Particles >38µm	ASTM D7647	>40	0	1	1
Particles >71µm	ASTM D7647	>10	0	0	0
Oil Cleanliness	ISO 4406 (c)	>20/18/16	▲ 24/23/19	▲ 24/22/17	▲ 24/22/17

FLUID DEGRADATION


	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	0.56	0.59	0.584

OIL ANALYSIS REPORT


▲ Particle Trend

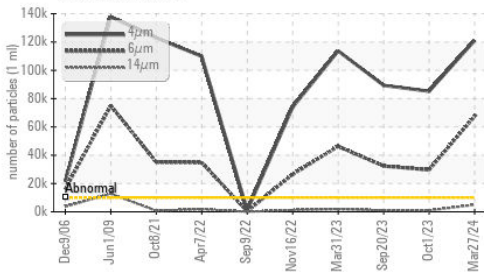


▲ Particle Trend

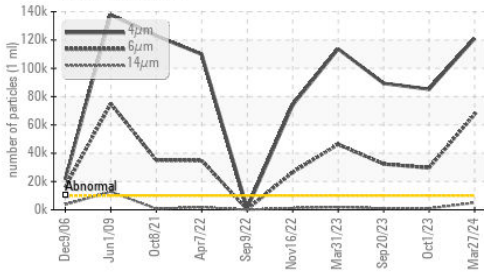

Acid Number

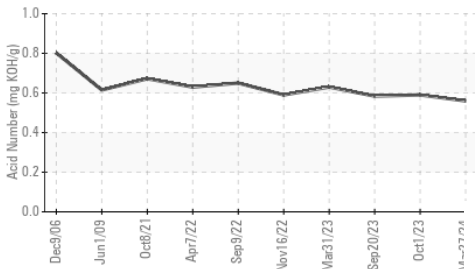


Viscosity @ 40°C

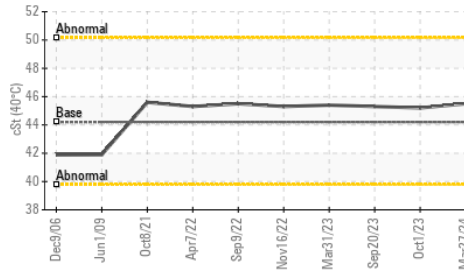

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	LIGHT	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.05	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	44.2	45.5	45.2

SAMPLE IMAGES

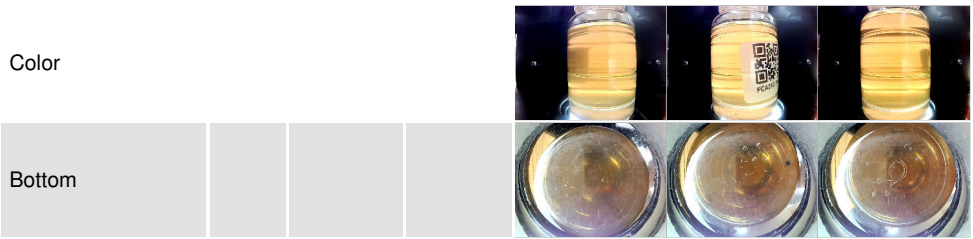


GRAPHS


Ferrous Alloys

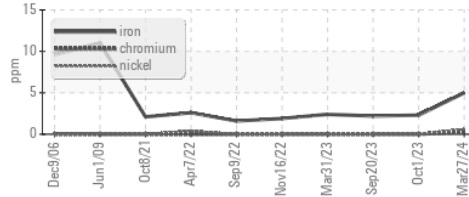


Non-ferrous Metals

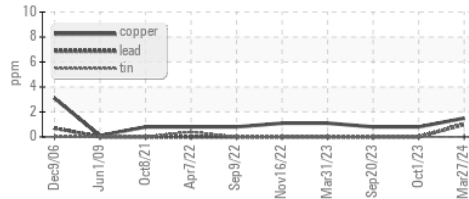


Viscosity @ 40°C

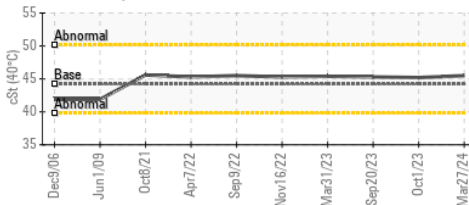

▲ Particle Count

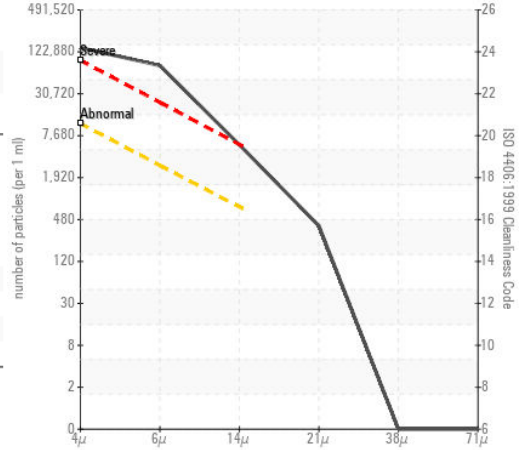

Acid Number

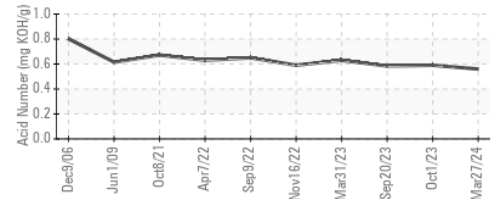

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : PCA0118385

Lab Number : 06136322

Unique Number : 10955787

Test Package : IND 2

Received : 02 Apr 2024

Tested : 03 Apr 2024

Diagnosed : 04 Apr 2024 - Don Baldrige

KraftHeinz - New Ulm - Plant 8302

2525 S BRIDGE STREET

NEW ULM, MN

US 56073

Contact: RYAN SCHMID

ryan.schmid@kraftheinz.com

T: (507)568-0338

F: (507)354-7927

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)