




OIL ANALYSIS REPORT

Sample Rating Trend

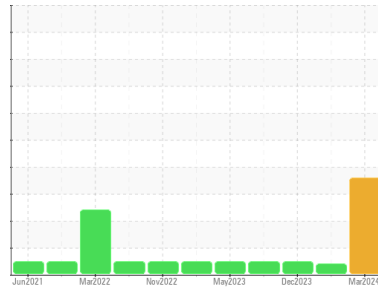

DEGRADATION



Machine Id

7812M

Component

Diesel Engine

Fluid

PETRO CANADA DURON SHP 15W40 (--- GAL)

DIAGNOSIS

▲ Recommendation

Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

Contamination

Fuel content negligible. There is no indication of any contamination in the oil.

▲ Fluid Condition

The oil viscosity is lower than normal. Additive levels indicate the addition of a different brand, or type of oil. The BN level is low. Confirm oil type.

SAMPLE INFORMATION

method	limit/base	current	history1	history2	
Sample Number	Client Info	GFL0116868	GFL0116940	GFL0107028	
Sample Date	Client Info	29 Mar 2024	21 Mar 2024	11 Dec 2023	
Machine Age	hrs	Client Info	15675	15623	15131
Oil Age	hrs	Client Info	600	600	600
Oil Changed	Client Info	Changed	Changed	N/A	
Sample Status		ABNORMAL	ATTENTION	NORMAL	

CONTAMINATION

method	limit/base	current	history1	history2	
Water	WC Method	>0.2	NEG	NEG	NEG
Glycol	WC Method		NEG	NEG	NEG

WEAR METALS

method	limit/base	current	history1	history2		
Iron	ppm	ASTM D5185m	>100	22	20	<1
Chromium	ppm	ASTM D5185m	>20	0	0	0
Nickel	ppm	ASTM D5185m	>4	0	0	<1
Titanium	ppm	ASTM D5185m		<1	0	0
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m	>20	3	2	1
Lead	ppm	ASTM D5185m	>40	1	0	<1
Copper	ppm	ASTM D5185m	>330	8	<1	0
Tin	ppm	ASTM D5185m	>15	<1	<1	0
Vanadium	ppm	ASTM D5185m		0	0	0
Cadmium	ppm	ASTM D5185m		0	0	0

ADDITIVES

method	limit/base	current	history1	history2		
Boron	ppm	ASTM D5185m	0	16	4	<1
Barium	ppm	ASTM D5185m	0	0	0	0
Molybdenum	ppm	ASTM D5185m	60	8	58	54
Manganese	ppm	ASTM D5185m	0	<1	<1	0
Magnesium	ppm	ASTM D5185m	1010	131	960	1024
Calcium	ppm	ASTM D5185m	1070	222	1055	1165
Phosphorus	ppm	ASTM D5185m	1150	457	1013	1106
Zinc	ppm	ASTM D5185m	1270	492	1284	1244
Sulfur	ppm	ASTM D5185m	2060	2200	3398	3209

CONTAMINANTS

method	limit/base	current	history1	history2		
Silicon	ppm	ASTM D5185m	>25	14	3	5
Sodium	ppm	ASTM D5185m		14	3	0
Potassium	ppm	ASTM D5185m	>20	2	<1	<1
Fuel	%	ASTM D3524	>5	0.7	1.4	<1.0

INFRA-RED






method	limit/base	current	history1	history2		
Soot %	%	*ASTM D7844	>3	0.1	0.7	0.2
Nitration	Abs/cm	*ASTM D7624	>20	3.4	9.6	5.3
Sulfation	Abs.1mm	*ASTM D7415	>30	23.4	20.8	17.9

FLUID DEGRADATION

method	limit/base	current	history1	history2		
Oxidation	Abs.1mm	*ASTM D7414	>25	19.3	17.6	13.4
Base Number (BN)	mg KOH/g	ASTM D2896	9.8	▲ 2.4	8.1	8.7







OIL ANALYSIS REPORT

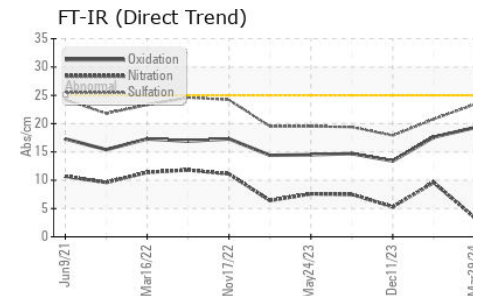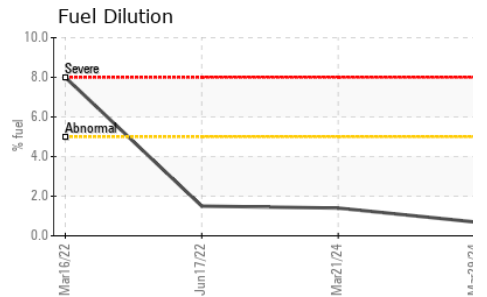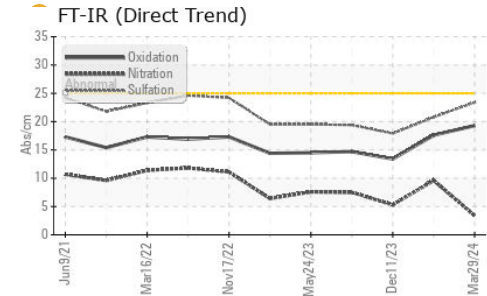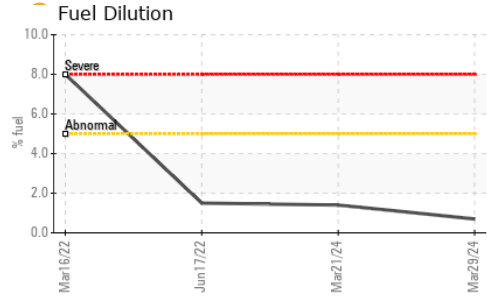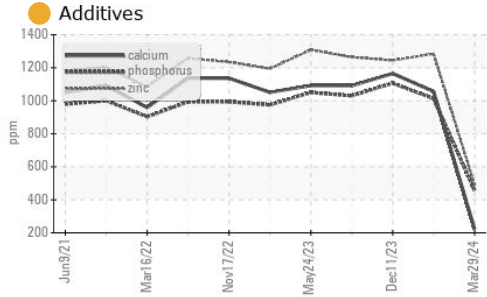

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	15.4	● 8.4	● 10.1	14.3

GRAPHS

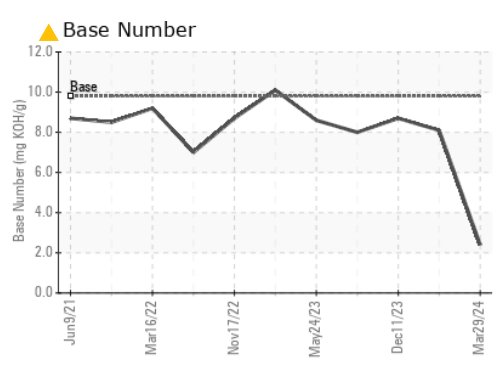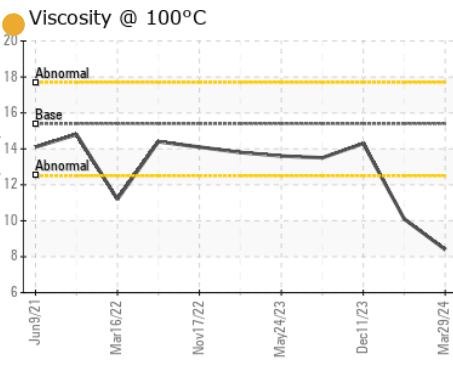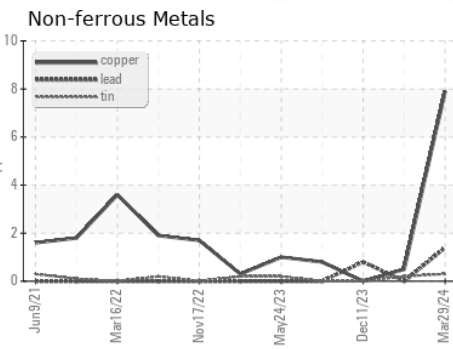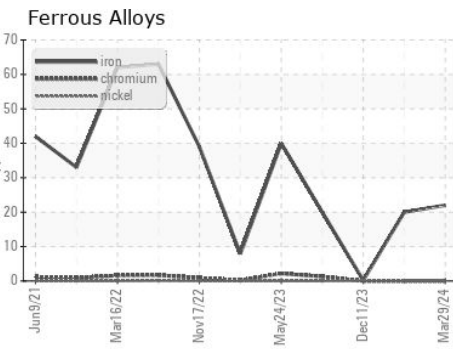

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0116868 **Received** : 03 Apr 2024
Lab Number : 06137917 **Tested** : 09 Apr 2024
Unique Number : 10962725 **Diagnosed** : 09 Apr 2024 - Jonathan Hester
Test Package : FLEET (Additional Tests: FuelDilution, PercentFuel)

GFL Environmental - 465 - Pontiac
 888 Baldwin
 Pontiac, MI
 US 48340
 Contact: Ricky Matthews
 rickymathews@gflenv.com
 T: (586)825-9514
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)