


# OIL ANALYSIS REPORT

## Sample Rating Trend



**WEAR**

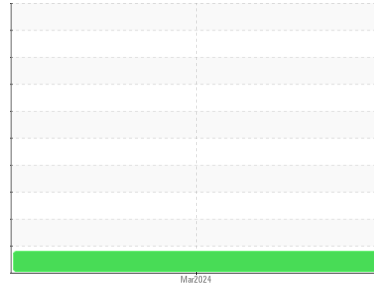

Machine Id

**638631**

Component

**Diesel Engine**

Fluid

**PETRO CANADA DURON SHP 10W30 (--- QTS)**

## DIAGNOSIS

### Recommendation

No corrective action is recommended at this time. Resample at the next service interval to monitor.

### Wear

Cylinder, crank, or cam shaft wear is indicated.

### Contamination

Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. There is no indication of any contamination in the oil.

### Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>PCA0105596</b>	---	---
Sample Date	Client Info		<b>20 Mar 2024</b>	---	---
Machine Age	mls	Client Info	<b>76732</b>	---	---
Oil Age	mls	Client Info	<b>0</b>	---	---
Oil Changed	Client Info		<b>N/A</b>	---	---
Sample Status			<b>ABNORMAL</b>	---	---

## CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<b>&lt;1.0</b>	---	---
Water	WC Method	>0.2	<b>NEG</b>	---	---
Glycol	WC Method		<b>NEG</b>	---	---

## WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >100	<b>▲ 112</b>	---	---
Chromium	ppm	ASTM D5185m >20	<b>10</b>	---	---
Nickel	ppm	ASTM D5185m >4	<b>0</b>	---	---
Titanium	ppm	ASTM D5185m	<b>1</b>	---	---
Silver	ppm	ASTM D5185m >3	<b>&lt;1</b>	---	---
Aluminum	ppm	ASTM D5185m >20	<b>101</b>	---	---
Lead	ppm	ASTM D5185m >40	<b>0</b>	---	---
Copper	ppm	ASTM D5185m >330	<b>175</b>	---	---
Tin	ppm	ASTM D5185m >15	<b>3</b>	---	---
Vanadium	ppm	ASTM D5185m	<b>0</b>	---	---
Cadmium	ppm	ASTM D5185m	<b>0</b>	---	---

## ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 2	<b>16</b>	---	---
Barium	ppm	ASTM D5185m 0	<b>0</b>	---	---
Molybdenum	ppm	ASTM D5185m 50	<b>47</b>	---	---
Manganese	ppm	ASTM D5185m 0	<b>4</b>	---	---
Magnesium	ppm	ASTM D5185m 950	<b>620</b>	---	---
Calcium	ppm	ASTM D5185m 1050	<b>1648</b>	---	---
Phosphorus	ppm	ASTM D5185m 995	<b>775</b>	---	---
Zinc	ppm	ASTM D5185m 1180	<b>925</b>	---	---
Sulfur	ppm	ASTM D5185m 2600	<b>1994</b>	---	---

## CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	<b>11</b>	---	---
Sodium	ppm	ASTM D5185m	<b>8</b>	---	---
Potassium	ppm	ASTM D5185m >20	<b>231</b>	---	---

## INFRA-RED


	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >3	<b>1.3</b>	---	---
Nitration	Abs/cm	*ASTM D7624 >20	<b>13.8</b>	---	---
Sulfation	Abs/.1mm	*ASTM D7415 >30	<b>26.1</b>	---	---

## FLUID DEGRADATION


	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	<b>28.6</b>	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	<b>5.1</b>	---	---

# OIL ANALYSIS REPORT


### ▲ Ferrous Alloys

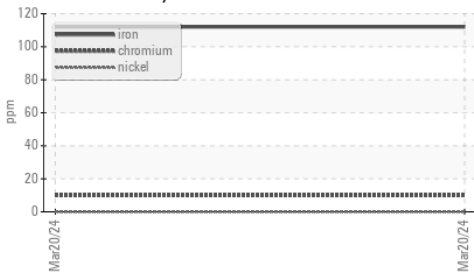


### FT-IR (Direct Trend)

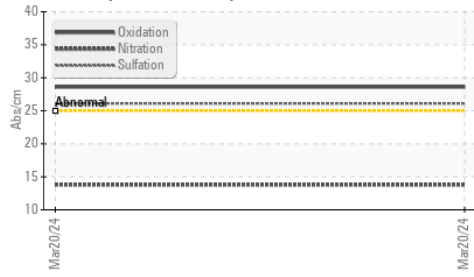


### Base Number

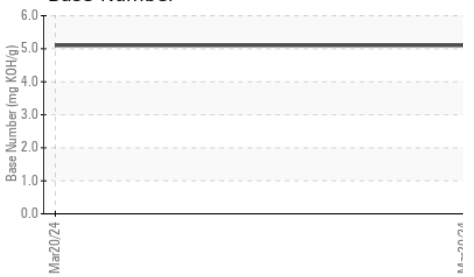

### Viscosity @ 100°C

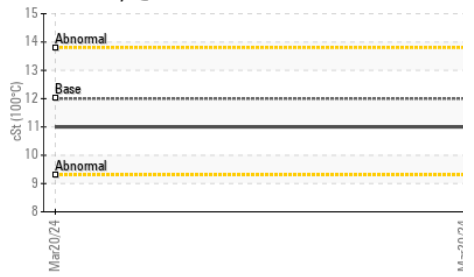

### Aluminum (ppm)

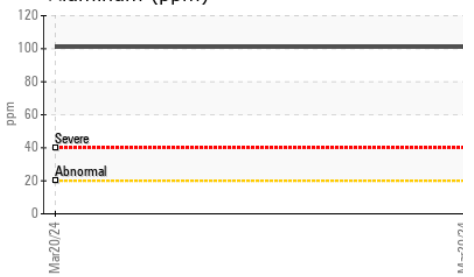


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual NONE	<b>NONE</b>	---	---
Yellow Metal	scalar	*Visual NONE	<b>NONE</b>	---	---
Precipitate	scalar	*Visual NONE	<b>NONE</b>	---	---
Silt	scalar	*Visual NONE	<b>NONE</b>	---	---
Debris	scalar	*Visual NONE	<b>NONE</b>	---	---
Sand/Dirt	scalar	*Visual NONE	<b>NONE</b>	---	---
Appearance	scalar	*Visual NORML	<b>NORML</b>	---	---
Odor	scalar	*Visual NORML	<b>NORML</b>	---	---
Emulsified Water	scalar	*Visual >0.2	<b>NEG</b>	---	---
Free Water	scalar	*Visual	<b>NEG</b>	---	---


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445 12.00	<b>11.0</b>	---	---

### GRAPHS


#### ▲ Iron (ppm)

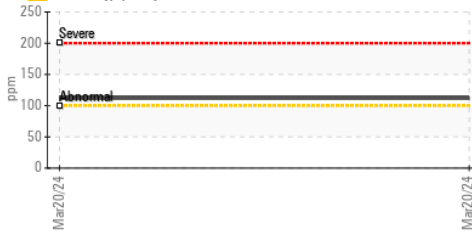


#### Lead (ppm)

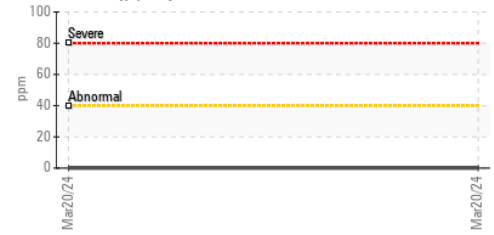


#### Aluminum (ppm)

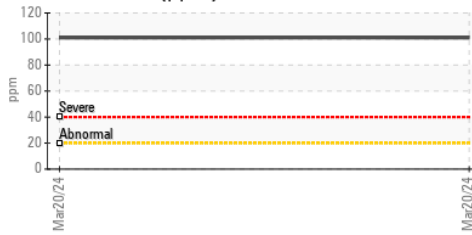


#### Chromium (ppm)

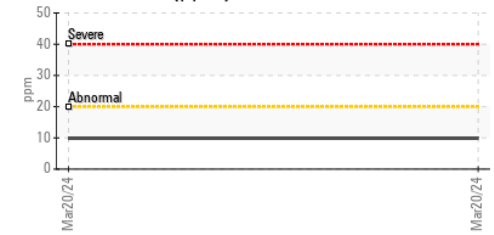


#### Copper (ppm)

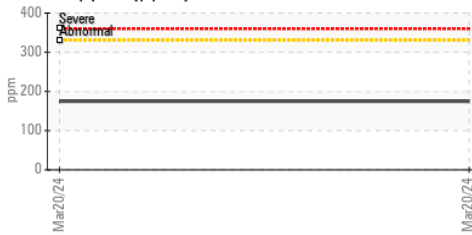


#### Silicon (ppm)

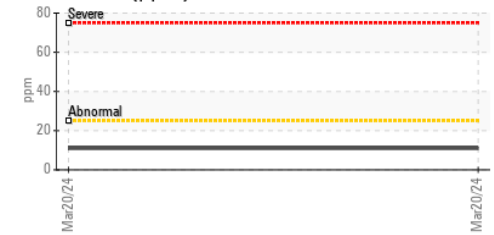

#### Viscosity @ 100°C

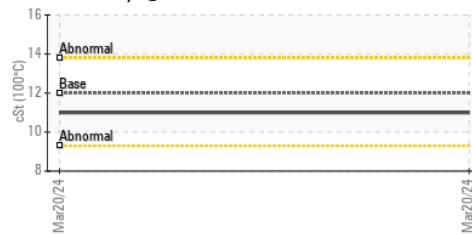

#### Base Number

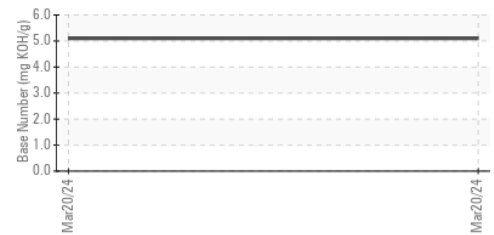

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : PCA0105596 **Received** : 15 Apr 2024  
**Lab Number** : **06148255** **Tested** : 16 Apr 2024  
**Unique Number** : 10978333 **Diagnosed** : 16 Apr 2024 - Sean Felton  
**Test Package** : MOB 1 ( Additional Tests: TBN )

**MILLER TRUCK LEASING #116**  
 1197 NORTH MAIN ROAD  
 VINELAND, NJ  
 US 08360  
 Contact: JOHN KEEN  
 jkeen@millertransgroup.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

F: (856)696-5629