




OIL ANALYSIS REPORT

Sample Rating Trend

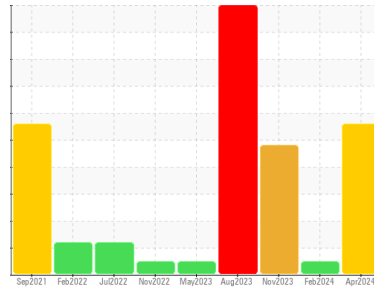

Machine Id

362M

Component

Diesel Engine

Fluid

PETRO CANADA DURON SHP 15W40 (--- GAL)

DIAGNOSIS

Recommendation

We advise that you check for the source of the coolant leak. Check for low coolant level. We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

Cylinder, crank, or cam shaft wear is indicated.

Contamination

Sodium and/or potassium levels are high. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	GFL0117687	GFL0108951	GFL0101547
Sample Date	Client Info	16 Apr 2024	29 Feb 2024	17 Nov 2023
Machine Age	hrs	5784	5635	5441
Oil Age	hrs	12409	12409	12409
Oil Changed	Client Info	Changed	Changed	Changed
Sample Status		ABNORMAL	NORMAL	ABNORMAL

CONTAMINATION

method	limit/base	current	history1	history2
Fuel	WC Method >3.0	<1.0	<1.0	<1.0
Water	WC Method >0.2	NEG	NEG	NEG

WEAR METALS

method	limit/base	current	history1	history2
Iron	ppm ASTM D5185m >90	▲ 196	19	30
Chromium	ppm ASTM D5185m >20	6	<1	2
Nickel	ppm ASTM D5185m >2	<1	<1	<1
Titanium	ppm ASTM D5185m >2	0	<1	<1
Silver	ppm ASTM D5185m >2	0	0	0
Aluminum	ppm ASTM D5185m >20	● 10	5	6
Lead	ppm ASTM D5185m >40	2	0	1
Copper	ppm ASTM D5185m >330	18	2	6
Tin	ppm ASTM D5185m >15	<1	<1	<1
Vanadium	ppm ASTM D5185m	0	0	0
Cadmium	ppm ASTM D5185m	0	0	<1

ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185m 0	36	1	10
Barium	ppm ASTM D5185m 0	2	0	9
Molybdenum	ppm ASTM D5185m 60	106	63	75
Manganese	ppm ASTM D5185m 0	3	<1	<1
Magnesium	ppm ASTM D5185m 1010	1005	892	922
Calcium	ppm ASTM D5185m 1070	1192	1040	1107
Phosphorus	ppm ASTM D5185m 1150	1067	1064	995
Zinc	ppm ASTM D5185m 1270	1379	1207	1226
Sulfur	ppm ASTM D5185m 2060	3428	3073	3105

CONTAMINANTS

method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185m >25	▲ 30	5	10
Sodium	ppm ASTM D5185m	▲ 1153	3	● 347
Potassium	ppm ASTM D5185m >20	▲ 36	3	▲ 24
Glycol	% *ASTM D2982	NEG	NEG	▲ 0.06

INFRA-RED

method	limit/base	current	history1	history2
Soot %	% *ASTM D7844 >6	1.1	0.8	0.7
Nitration	Abs/cm *ASTM D7624 >20	15.6	9.8	10.9
Sulfation	Abs/.1mm *ASTM D7415 >30	26.5	20.4	22.6


FLUID DEGRADATION

method	limit/base	current	history1	history2
Oxidation	Abs/.1mm *ASTM D7414 >25	21.3	16.5	18.5
Base Number (BN)	mg KOH/g ASTM D2896 9.8	9.6	5.5	8.1




OIL ANALYSIS REPORT


▲ Silicon (ppm)

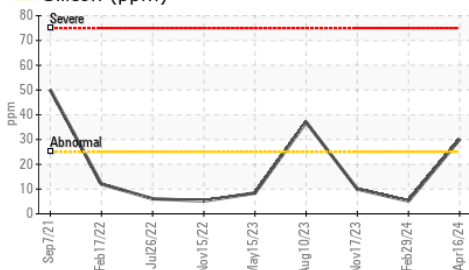


● Aluminum (ppm)

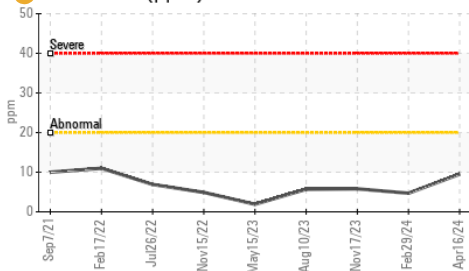


▲ FT-IR (Direct Trend)

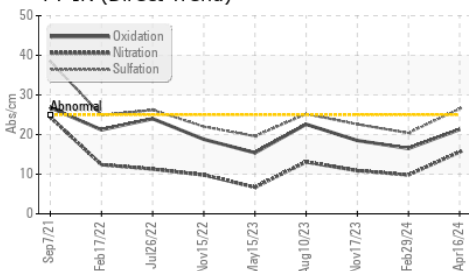

Glycol Contamination

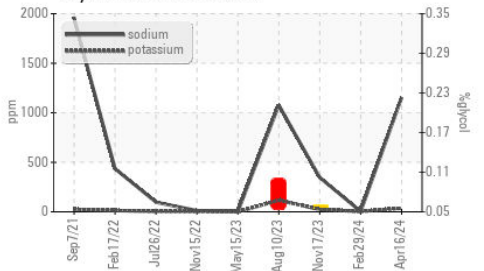

Base Number

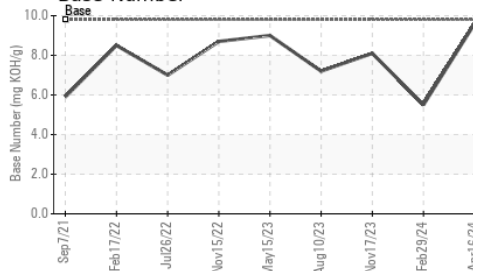

VISUAL


	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES


	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	15.4	15.2	13.4

GRAPHS


▲ Ferrous Alloys

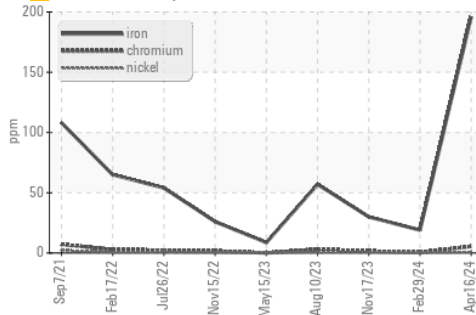


Non-ferrous Metals

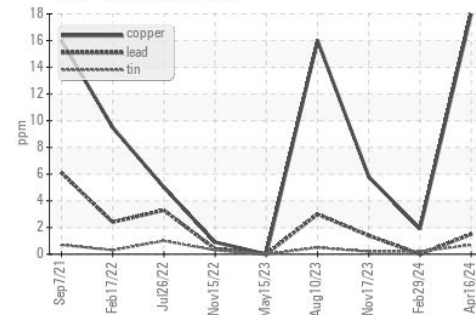

Viscosity @ 100°C

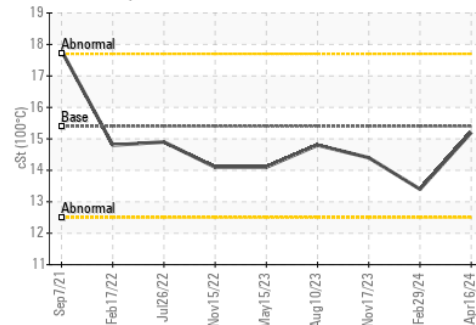

Base Number

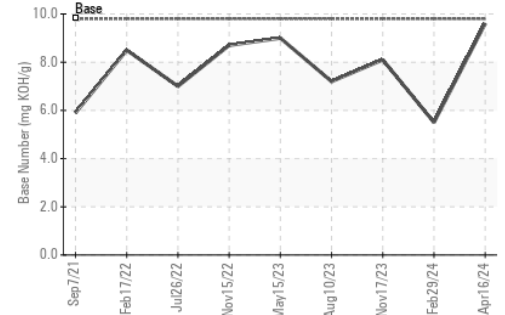

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : GFL0117687

Lab Number : 06155745

Unique Number : 10991168

Test Package : FLEET (Additional Tests: Glycol)

Received : 22 Apr 2024

Tested : 24 Apr 2024

Diagnosed : 24 Apr 2024 - Jonathan Hester

GFL Environmental - 415 - Michigan East

6200 Elmridge

Sterling Heights, MI

US 48313

Contact: Frank Wolak

fwolak@gflenv.com

T: (586)825-9514

F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)