


OIL ANALYSIS REPORT

(51468Z) Walgreens - Tractor [Walgreens - Tractor] 136A63278

Diesel Engine

PETRO CANADA DURON SHP 10W30 (11 GAL)





DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

All component wear rates are normal.

Contamination

There is no indication of any contamination in the


Fluid Condition


The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.


wall						
SAMPLE INFOR	MATION	method	limit/base	current	history1	history2
Sample Number		Client Info		PCA0093890	PCA0093922	PCA0093872
Sample Date		Client Info		19 Mar 2024	24 Oct 2023	04 May 2023
Machine Age	mls	Client Info		187402	133370	80112
Oil Age	mls	Client Info		187402	54879	0
Oil Changed		Client Info		Not Changd	N/A	Not Changd
Sample Status				NORMAL	NORMAL	NORMAL
CONTAMINAT	ION	method	limit/base	current	history1	history2
Fuel		WC Method	>5	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
WEAR METAL	S	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m	>80	21	16	32
Chromium	ppm	ASTM D5185m	>5	2	2	2
Nickel	ppm	ASTM D5185m	>2	0	<1	<1
Titanium	ppm	ASTM D5185m		3	<1	2
Silver	ppm	ASTM D5185m	>3	<1	<1	0
Aluminum	ppm	ASTM D5185m	>30	7	6	6
Lead	ppm	ASTM D5185m	>30	0	0	<1
Copper	ppm	ASTM D5185m	>150	24	54	148
Tin	ppm	ASTM D5185m	>5	<1	0	2
Vanadium	ppm	ASTM D5185m		0	<1	0
Cadmium	ppm	ASTM D5185m		0	0	0
ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	2	6	4	13
Barium	ppm	ASTM D5185m	0	0	0	0
Molybdenum	ppm	ASTM D5185m	50	63	67	57
Manganese	ppm	ASTM D5185m	0	<1	<1	2
Magnesium	ppm	ASTM D5185m	950	934	923	875
Calcium	ppm	ASTM D5185m	1050	1114	1137	1321
Phosphorus	ppm	ASTM D5185m	995	1008	935	893
Zinc	ppm	ASTM D5185m	1180	1241	1233	1151
Sulfur	ppm	ASTM D5185m	2600	2795	2469	2427
CONTAMINAN	ITS	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>20	6	4	4
Sodium	ppm	ASTM D5185m		2	0	3
Potassium	ppm	ASTM D5185m	>20	15	16	30
INFRA-RED		method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844	>3	0.7	0.5	0.5
Nitration	Abs/cm	*ASTM D7624	>20	8.4	7.8	9.0
Sulfation	Abs/.1mm	*ASTM D7415	>30	20.6	20.2	20.2
FLUID DEGRADATION method limit/base current history1 history2						
Oxidation	Abs/.1mm	*ASTM D7414	>25	17.1	16.6	17.7
Base Number (BN)	mg KOH/g	ASTM D2896		7.2	7.4	7.7
= 200 Hamber (BIV)	mg nong	. IO I III DE000			7.1	7.7



OIL ANALYSIS REPORT










VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG	NEG


	FLUID PROPE	THIES	method			History I	History∠
,	Visc @ 100°C	cSt	ASTM D445	12.00	11.4	11.3	11.1

GRAPHS







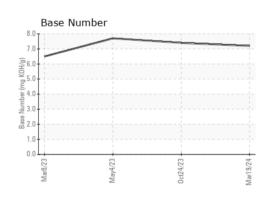





Certificate 12367

Laboratory Sample No.

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 Lab Number : 06157291 Unique Number : 10992714

: PCA0093890 Test Package : FLEET

Received : 23 Apr 2024 **Tested** Diagnosed

: 24 Apr 2024 : 24 Apr 2024 - Wes Davis

Transervice - Shop 1372 - Berkeley-Moreno Valley 17500 Perris Blvd. Moreno Valley, CA

US 92551 Contact: Ryan Cruz rcruz@transervice.com T: (951)924-7131

F: (951)924-7151

To discuss this sample report, contact Customer Service at 1-800-237-1369. * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)