




OIL ANALYSIS REPORT

Sample Rating Trend

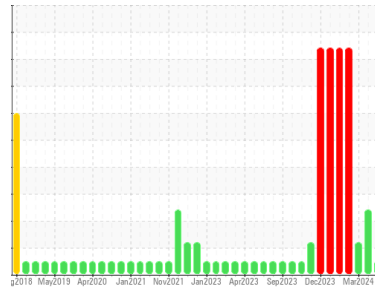

NORMAL



Machine Id
10867
 Component
Diesel Engine
 Fluid

PETRO CANADA DURON SHP 15W40 (40 GAL)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		GFL0098905	GFL0098882	GFL0098884
Sample Date	Client Info		17 Apr 2024	20 Mar 2024	14 Mar 2024
Machine Age	mls	Client Info	219035	219035	219035
Oil Age	mls	Client Info	204515	204515	204515
Oil Changed	Client Info		Not Changed	Not Changd	Not Changed
Sample Status			NORMAL	ABNORMAL	ATTENTION

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>3.0	<1.0	<1.0	<1.0
Water	WC Method	>0.2	NEG	NEG	NEG
Glycol	WC Method		NEG	NEG	0.0

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >75	9	16	13
Chromium	ppm	ASTM D5185m >5	1	<1	<1
Nickel	ppm	ASTM D5185m >4	2	<1	0
Titanium	ppm	ASTM D5185m >2	<1	<1	<1
Silver	ppm	ASTM D5185m >2	<1	<1	0
Aluminum	ppm	ASTM D5185m >15	2	3	3
Lead	ppm	ASTM D5185m >25	1	<1	0
Copper	ppm	ASTM D5185m >100	2	2	<1
Tin	ppm	ASTM D5185m >4	1	<1	0
Vanadium	ppm	ASTM D5185m	<1	<1	<1
Cadmium	ppm	ASTM D5185m	<1	<1	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 0	<1	<1	0
Barium	ppm	ASTM D5185m 0	<1	0	0
Molybdenum	ppm	ASTM D5185m 60	58	63	58
Manganese	ppm	ASTM D5185m 0	1	<1	<1
Magnesium	ppm	ASTM D5185m 1010	851	830	906
Calcium	ppm	ASTM D5185m 1070	1034	1040	1081
Phosphorus	ppm	ASTM D5185m 1150	870	917	989
Zinc	ppm	ASTM D5185m 1270	1093	1095	1234
Sulfur	ppm	ASTM D5185m 2060	2964	2821	3785

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	4	5	7
Sodium	ppm	ASTM D5185m	0	▲ 117	79
Potassium	ppm	ASTM D5185m >20	2	▲ 112	● 76

INFRA-RED

	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >6	0.4	0.2	0.2
Nitration	Abs/cm	*ASTM D7624 >20	6.1	7.5	6.8
Sulfation	Abs/.1mm	*ASTM D7415 >30	17.7	18.4	18.0


FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	12.9	14.5	13.9
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	7.8	8.1	8.2




OIL ANALYSIS REPORT


FT-IR (Direct Trend)

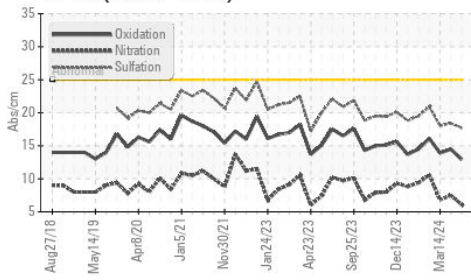

Base Number

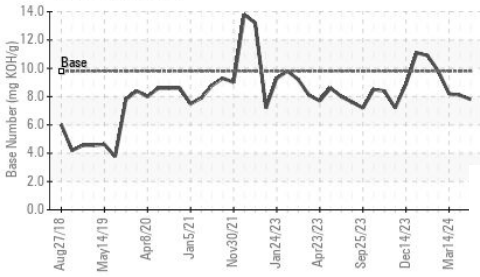

Viscosity @ 100°C

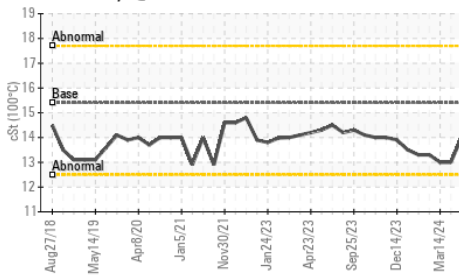


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	15.4	14.0	13.0

GRAPHS


Ferrous Alloys

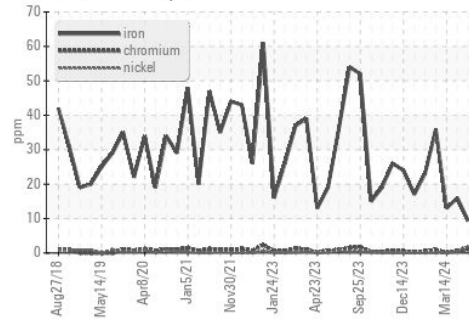


Non-ferrous Metals

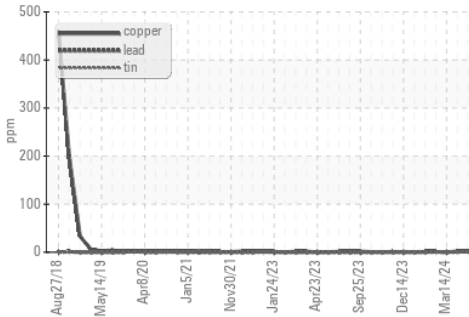

Viscosity @ 100°C

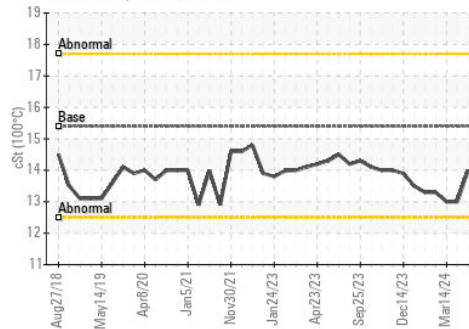

Base Number

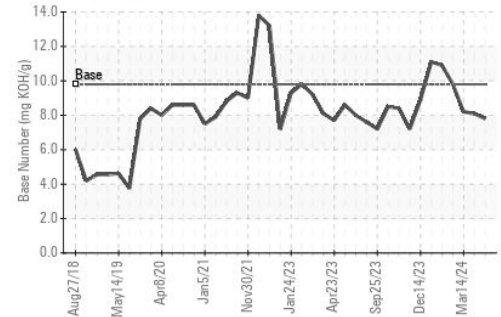

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
 Sample No. : GFL0098905
 Lab Number : 06160203
 Unique Number : 10995626
 Test Package : FLEET

Received : 25 Apr 2024
 Tested : 26 Apr 2024
 Diagnosed : 26 Apr 2024 - Wes Davis

GFL Environmental - 084 - Clarksville
 699 Jack Miller Boulevard
 Clarksville, TN
 US 37042

Contact: ROBERT THIBAUT
 robert.thibault@gflenv.com

T: (931)552-7276
 F: (931)572-9674

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)