


OIL ANALYSIS REPORT



Area
KEMP QUARRIES / RIVER VALLEY BACKBONE
 Machine Id
WL088
 Component
Rear Left Final Drive
 Fluid
MOBIL MOBILTRANS HD 50 (--- GAL)

Sample Rating Trend

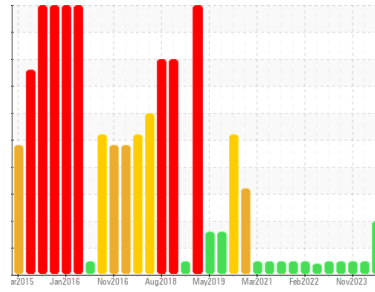

VISCOSITY



DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The oil viscosity is lower than normal. This plus the additive levels indicates the addition of a different brand, or type of oil. Confirm oil type.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		PCA0108598	PCA0069721	PCA0084822
Sample Date	Client Info		23 May 2024	30 Jan 2024	10 Nov 2023
Machine Age	hrs	Client Info	43799	43499	6716
Oil Age	hrs	Client Info	900	1200	900
Oil Changed	Client Info		Not Chngd	Changed	Not Chngd
Sample Status			ATTENTION	NORMAL	NORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.2	NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >800	31	19	22
Chromium	ppm	ASTM D5185m >10	<1	<1	<1
Nickel	ppm	ASTM D5185m >5	<1	0	<1
Titanium	ppm	ASTM D5185m >15	<1	0	<1
Silver	ppm	ASTM D5185m >2	1	0	0
Aluminum	ppm	ASTM D5185m >75	2	2	2
Lead	ppm	ASTM D5185m >10	<1	0	3
Copper	ppm	ASTM D5185m >75	5	3	4
Tin	ppm	ASTM D5185m >8	<1	0	0
Vanadium	ppm	ASTM D5185m	<1	0	0
Cadmium	ppm	ASTM D5185m	<1	0	<1

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	0	0	0
Barium	ppm	ASTM D5185m	0	5	0
Molybdenum	ppm	ASTM D5185m	2	<1	2
Manganese	ppm	ASTM D5185m	<1	0	<1
Magnesium	ppm	ASTM D5185m	21	21	21
Calcium	ppm	ASTM D5185m	501	756	988
Phosphorus	ppm	ASTM D5185m	428	513	584
Zinc	ppm	ASTM D5185m	538	618	724
Sulfur	ppm	ASTM D5185m	1477	1950	2788



CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >400	7	5	9
Sodium	ppm	ASTM D5185m	0	0	0
Potassium	ppm	ASTM D5185m >20	2	1	1

VISUAL

	method	limit/base	current	history1	history2
White Metal	scalar	*Visual NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual NONE	NONE	NONE	NONE
Precipitate	scalar	*Visual NONE	NONE	NONE	NONE
Silt	scalar	*Visual NONE	NONE	NONE	NONE
Debris	scalar	*Visual NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual NONE	NONE	NONE	NONE
Appearance	scalar	*Visual NORML	NORML	NORML	NORML
Odor	scalar	*Visual NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual >0.2	NEG	NEG	NEG
Free Water	scalar	*Visual	NEG	NEG	NEG

OIL ANALYSIS REPORT

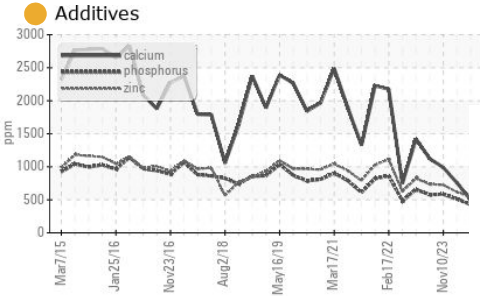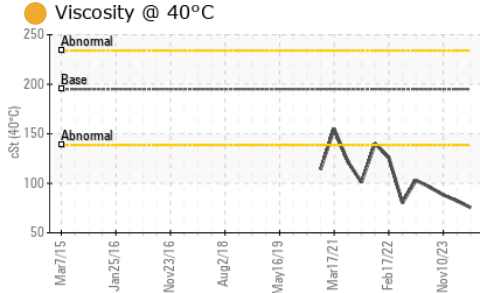









FLUID PROPERTIES

method	limit/base	current	history1	history2	
Visc @ 40°C	cSt ASTM D445	195	75.5	82.2	88.3

SAMPLE IMAGES

method	limit/base	current	history1	history2	
Color			no image	no image	no image
Bottom			no image	no image	no image

GRAPHS

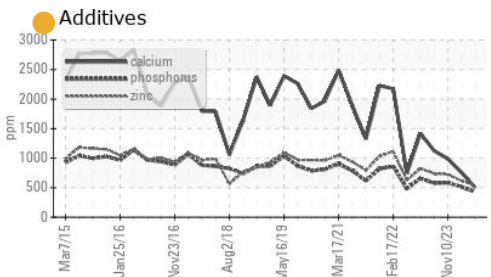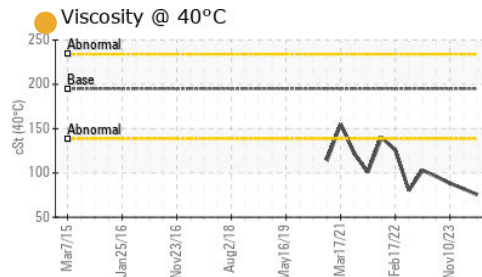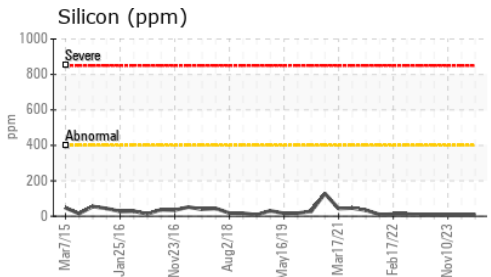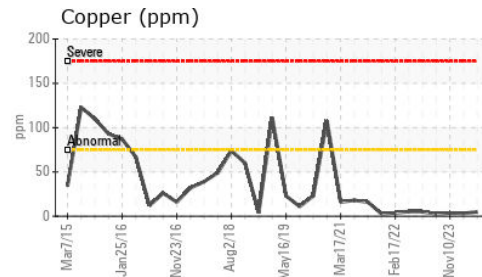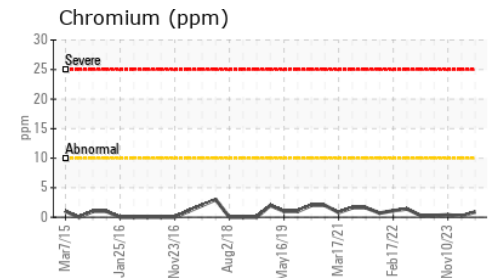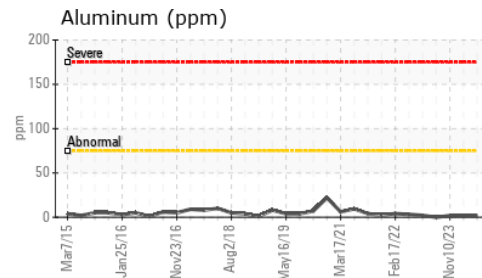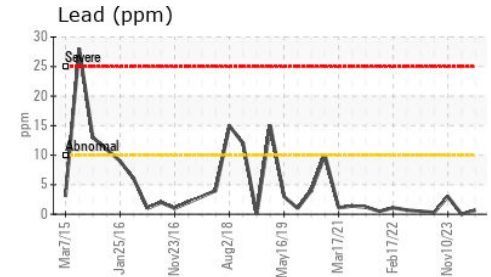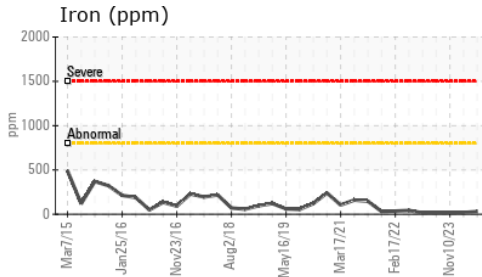

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : PCA0108598
Lab Number : 06193085
Unique Number : 11049837
Test Package : MOB 1
Received : 28 May 2024
Tested : 30 May 2024
Diagnosed : 30 May 2024 - Sean Felton

Kemp Quarries - River Valley - Backbone
 5600 S Hwy 253
 Huntington, AR
 US 72940
 Contact:
 backbone@rivervalleyquarries.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)