




PROBLEM SUMMARY

Sample Rating Trend

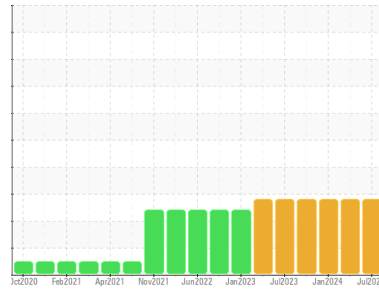

FUEL





Machine Id
427023-442

Component
Diesel Engine

Fluid
PETRO CANADA DURON SHP 15W40 (--- LTR)

COMPONENT CONDITION SUMMARY

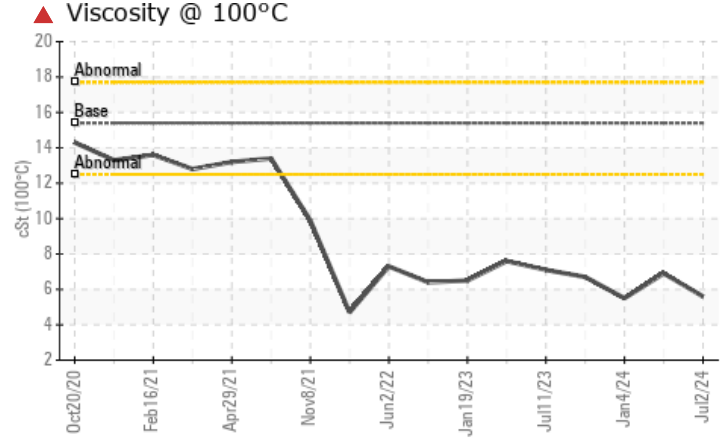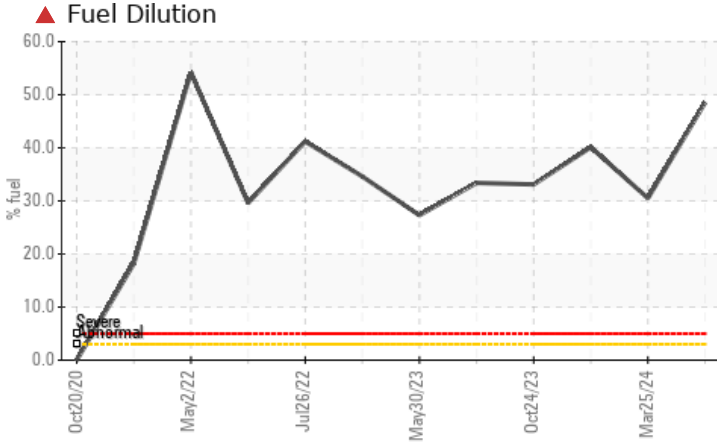

RECOMMENDATION

We advise that you check the fuel injection system. We recommend that you drain the oil from the component if this has not already been done. We recommend an early resample to monitor this condition.

PROBLEMATIC TEST RESULTS

Sample Status				SEVERE	SEVERE	SEVERE
Fuel	%	ASTM D3524	>3.0	▲ 48.5	▲ 30.5	▲ 40.1
Visc @ 100°C	cSt	ASTM D445	15.4	▲ 5.6	▲ 6.9	▲ 5.5

Customer Id: GFL650
Sample No.: GFL0120837
Lab Number: 06229556
Test Package: FLEET



To manage this report scan the QR code

To discuss the diagnosis or test data:
Wes Davis +1 905-569-8600 x223
wesd@wearcheck.ca

To change component or sample information:
Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Fluid	---	---	?	We recommend that you drain the oil from the component if this has not already been done.
Resample	---	---	?	We recommend an early resample to monitor this condition.
Check Fuel/injector System	---	---	?	We advise that you check the fuel injection system.

HISTORICAL DIAGNOSIS

FUEL



25 Mar 2024 Diag: Wes Davis

We advise that you check the fuel injection system. The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition. All component wear rates are normal. There is a high amount of fuel present in the oil. Tests confirm the presence of fuel in the oil. The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.

view report



FUEL



04 Jan 2024 Diag: Wes Davis

We advise that you check the fuel injection system. The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition. All component wear rates are normal. There is a high amount of fuel present in the oil. Tests confirm the presence of fuel in the oil. The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.

view report



FUEL



24 Oct 2023 Diag: Wes Davis

We advise that you check the fuel injection system. The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition. All component wear rates are normal. There is a high amount of fuel present in the oil. Tests confirm the presence of fuel in the oil. The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.


view report





OIL ANALYSIS REPORT

Sample Rating Trend

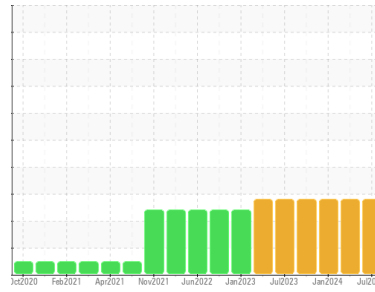

FUEL



Machine Id
427023-442

Component
Diesel Engine

Fluid
PETRO CANADA DURON SHP 15W40 (--- LTR)

DIAGNOSIS

▲ Recommendation

We advise that you check the fuel injection system. We recommend that you drain the oil from the component if this has not already been done. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

▲ Contamination

There is a high amount of fuel present in the oil. Tests confirm the presence of fuel in the oil.

▲ Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		GFL0120837	GFL0077794	GFL0077769
Sample Date	Client Info		02 Jul 2024	25 Mar 2024	04 Jan 2024
Machine Age	hrs	Client Info	538646	38070	515487
Oil Age	hrs	Client Info	38551	0	0
Oil Changed	Client Info		Not Chngd	Changed	Changed
Sample Status			SEVERE	SEVERE	SEVERE

CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.2	NEG	NEG	NEG
Glycol	WC Method		NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >120	21	4	8
Chromium	ppm	ASTM D5185m >20	<1	0	<1
Nickel	ppm	ASTM D5185m >5	0	0	<1
Titanium	ppm	ASTM D5185m >2	0	0	0
Silver	ppm	ASTM D5185m >2	0	0	0
Aluminum	ppm	ASTM D5185m >20	1	<1	2
Lead	ppm	ASTM D5185m >40	<1	0	<1
Copper	ppm	ASTM D5185m >330	4	3	10
Tin	ppm	ASTM D5185m >15	0	0	1
Vanadium	ppm	ASTM D5185m	0	0	0
Cadmium	ppm	ASTM D5185m	0	0	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 0	<1	7	4
Barium	ppm	ASTM D5185m 0	0	0	0
Molybdenum	ppm	ASTM D5185m 60	33	42	36
Manganese	ppm	ASTM D5185m 0	<1	0	<1
Magnesium	ppm	ASTM D5185m 1010	521	683	590
Calcium	ppm	ASTM D5185m 1070	611	773	657
Phosphorus	ppm	ASTM D5185m 1150	581	768	662
Zinc	ppm	ASTM D5185m 1270	675	856	781
Sulfur	ppm	ASTM D5185m 2060	1837	2560	1930

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	7	3	5
Sodium	ppm	ASTM D5185m	3	<1	2
Potassium	ppm	ASTM D5185m >20	1	0	0
Fuel	%	ASTM D3524 >3.0	▲ 48.5	▲ 30.5	▲ 40.1

INFRA-RED





	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >4	0.7	0.3	0.5
Nitration	Abs/cm	*ASTM D7624 >20	10.8	7.9	8.9
Sulfation	Abs/.1mm	*ASTM D7415 >30	19.7	16.2	17.0

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	17.7	12.7	13.4
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	4.5	7.5	5.2







OIL ANALYSIS REPORT

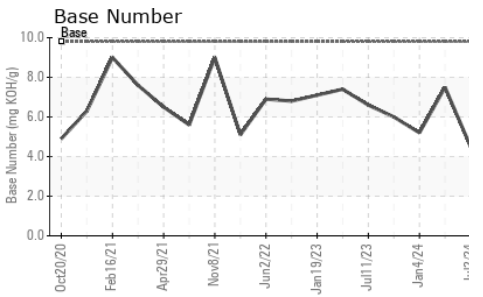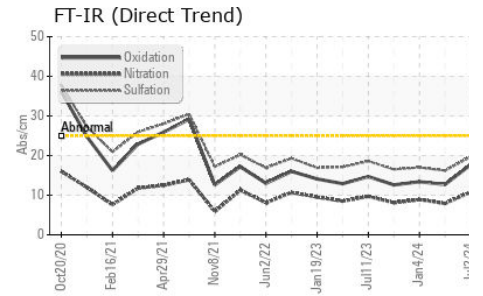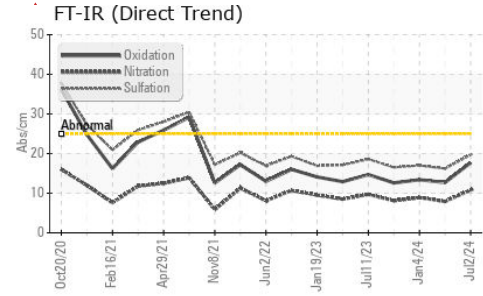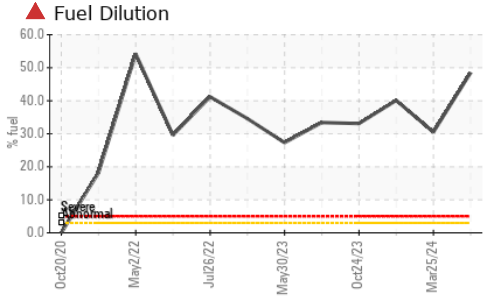

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	15.4	▲ 5.6	▲ 6.9

GRAPHS

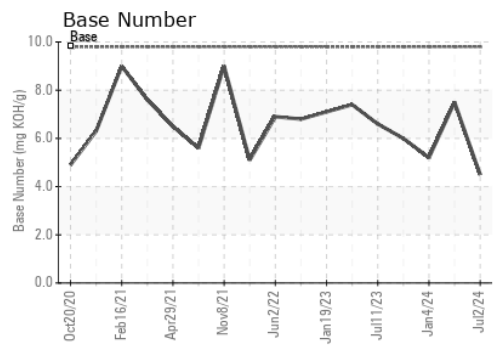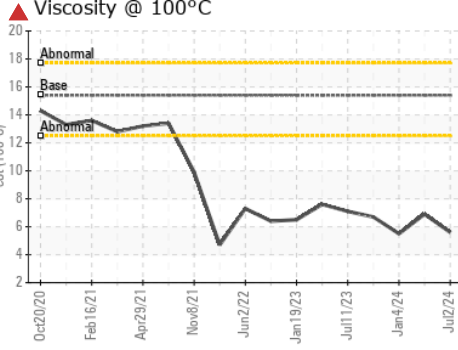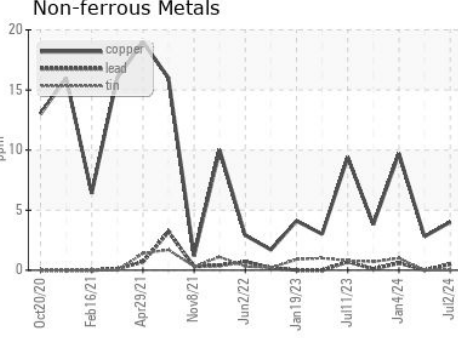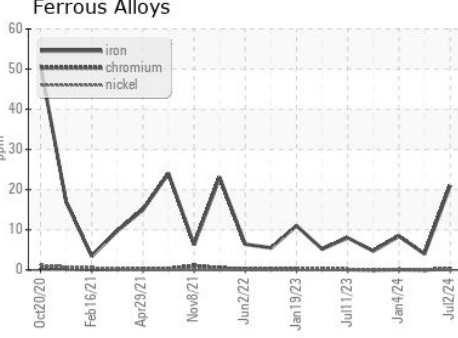

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0120837 **Received** : 05 Jul 2024
Lab Number : 06229556 **Tested** : 10 Jul 2024
Unique Number : 11113049 **Diagnosed** : 10 Jul 2024 - Wes Davis
Test Package : FLEET (Additional Tests: PercentFuel)

GFL Environmental - 650 - West Point Hauling
 7825 Parham Landing Road
 West Point, VA
 US 23181
 Contact: Jason Smith
 jasonsmith@gflenv.com
 T: (804)843-9288
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)