




# OIL ANALYSIS REPORT

Sample Rating Trend

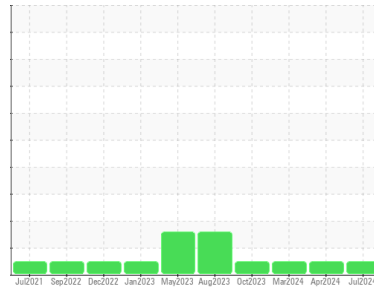

**NORMAL**



Machine Id  
**727025-594**  
 Component  
**Diesel Engine**  
 Fluid  
**PETRO CANADA DURON SHP 15W40 (--- GAL)**

## DIAGNOSIS

### Recommendation

Resample at the next service interval to monitor. ( Customer Sample Comment: Pm completed )

### Wear

All component wear rates are normal.

### Contamination

There is no indication of any contamination in the oil.

### Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>GFL0116303</b>	GFL0116240	GFL0101610
Sample Date	Client Info		<b>02 Jul 2024</b>	30 Apr 2024	07 Mar 2024
Machine Age	hrs	Client Info	<b>15066</b>	14760	14506
Oil Age	hrs	Client Info	<b>593</b>	287	590
Oil Changed	Client Info		<b>Changed</b>	Changed	Changed
Sample Status			<b>NORMAL</b>	NORMAL	NORMAL

## CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>3.0	<b>&lt;1.0</b>	<1.0	<1.0
Water	WC Method	>0.2	<b>NEG</b>	NEG	NEG
Glycol	WC Method		<b>NEG</b>	NEG	NEG

## WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >120	<b>12</b>	9	7
Chromium	ppm	ASTM D5185m >20	<b>0</b>	<1	0
Nickel	ppm	ASTM D5185m >5	<b>&lt;1</b>	<1	2
Titanium	ppm	ASTM D5185m >2	<b>0</b>	<1	0
Silver	ppm	ASTM D5185m >2	<b>0</b>	0	0
Aluminum	ppm	ASTM D5185m >20	<b>2</b>	2	3
Lead	ppm	ASTM D5185m >40	<b>&lt;1</b>	<1	0
Copper	ppm	ASTM D5185m >330	<b>&lt;1</b>	<1	2
Tin	ppm	ASTM D5185m >15	<b>0</b>	0	<1
Vanadium	ppm	ASTM D5185m	<b>0</b>	0	0
Cadmium	ppm	ASTM D5185m	<b>0</b>	0	0

## ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 0	<b>7</b>	2	0
Barium	ppm	ASTM D5185m 0	<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185m 60	<b>55</b>	65	61
Manganese	ppm	ASTM D5185m 0	<b>&lt;1</b>	<1	<1
Magnesium	ppm	ASTM D5185m 1010	<b>913</b>	972	914
Calcium	ppm	ASTM D5185m 1070	<b>1175</b>	1150	1073
Phosphorus	ppm	ASTM D5185m 1150	<b>1029</b>	1063	1028
Zinc	ppm	ASTM D5185m 1270	<b>1284</b>	1242	1222
Sulfur	ppm	ASTM D5185m 2060	<b>3357</b>	3444	3104

## CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	<b>6</b>	5	7
Sodium	ppm	ASTM D5185m	<b>3</b>	2	3
Potassium	ppm	ASTM D5185m >20	<b>1</b>	0	1

## INFRA-RED

	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >4	<b>0.5</b>	0.4	0.6
Nitration	Abs/cm	*ASTM D7624 >20	<b>8.2</b>	8.0	9.7
Sulfation	Abs/.1mm	*ASTM D7415 >30	<b>19.9</b>	19.3	21.1


## FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	<b>15.3</b>	14.7	16.8
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	<b>7.2</b>	8.2	5.7




# OIL ANALYSIS REPORT


FT-IR (Direct Trend)

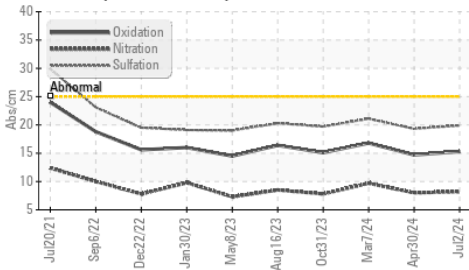

Base Number

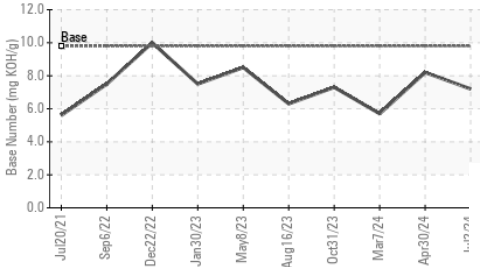

Viscosity @ 100°C

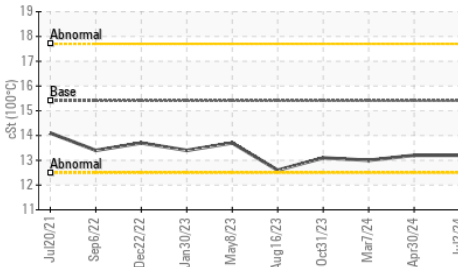


PARAMETER	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


PARAMETER	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	15.4	13.2	13.0

## GRAPHS


Ferrous Alloys

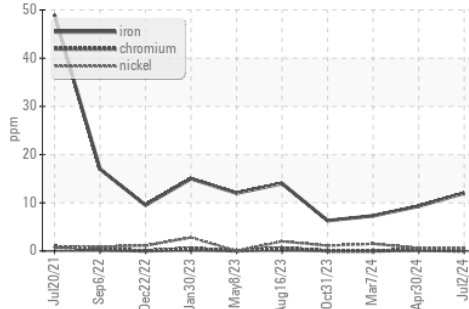


Non-ferrous Metals

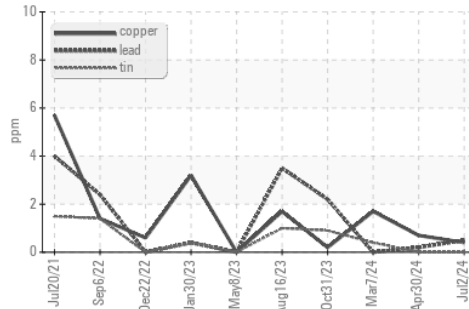

Viscosity @ 100°C

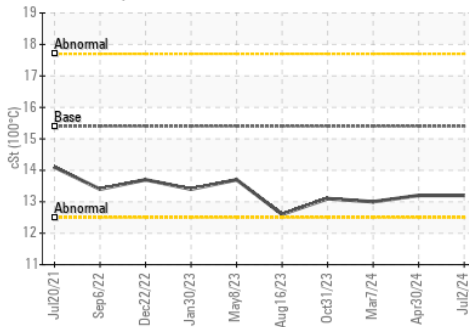

Base Number

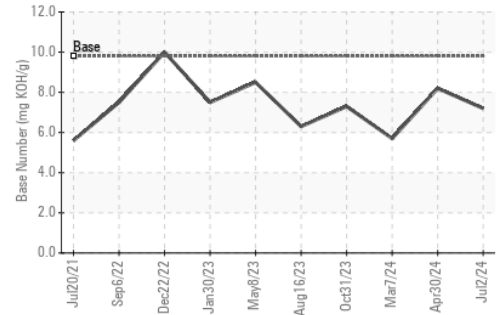

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
 Sample No. : GFL0116303  
 Lab Number : 06229599  
 Unique Number : 11113092  
 Test Package : FLEET

GFL Environmental - 625 - Harrison Hauling  
 2480 S Clare Ave  
 Clare, MI  
 US 48617

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

Contact: Glenda Standen  
 gstanden@gflenv.com

T:  
 F: