




PROBLEM SUMMARY



Sample Rating Trend

ADDITIVES

Machine Id
[N617QX] BOMBARDIER CRJ700 N617QX
 Component
2 Hydraulic System
 Fluid
SKYDROL LD-4 (--- GAL)

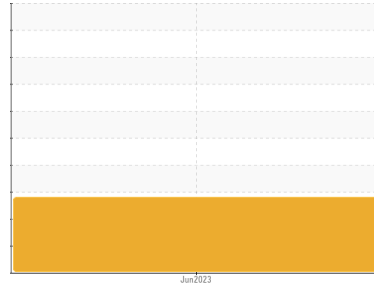

COMPONENT CONDITION SUMMARY

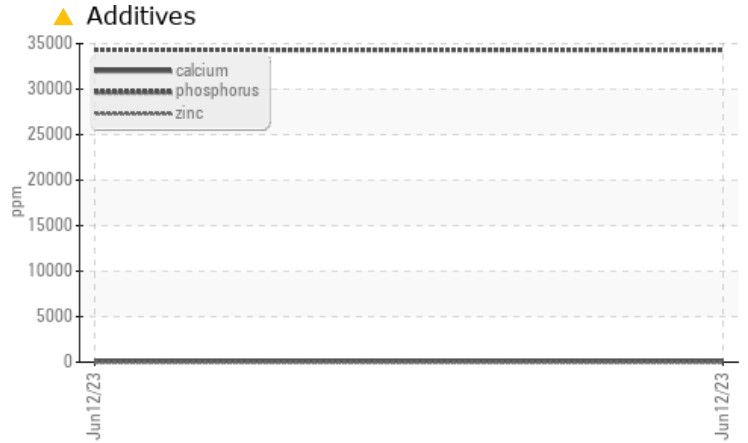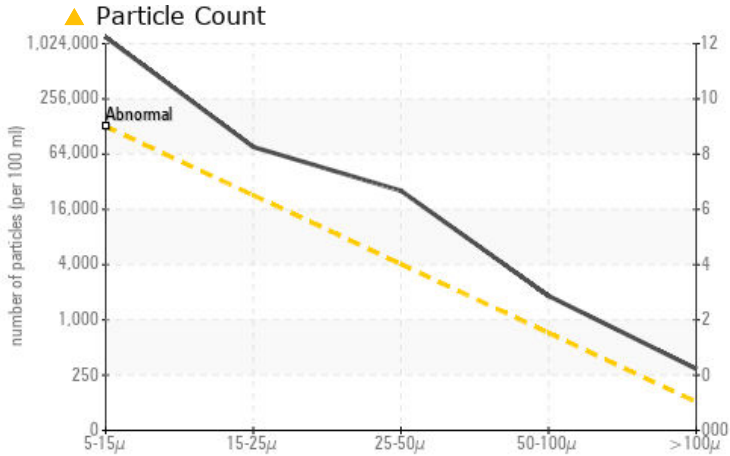

RECOMMENDATION

We advise that you perform a filter service, and use off-line filtration to improve the cleanliness of the system fluid. Confirm the source of the lubricant being utilized for top-up/fill. We recommend an early resample to monitor this condition. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.

PROBLEMATIC TEST RESULTS

Sample Status				ABNORMAL	---	---
Calcium	ppm	ASTM D5185(m)	0	▲ 119	---	---
Sulfur	ppm	ASTM D5185(m)	1900	▲ 544	---	---
Particles 5-15µm	count	NAS 1638	>128000	▲ 1203320	---	---
Particles 15-25µm	count	NAS 1638	>22800	▲ 76680	---	---
Particles 25-50µm	count	NAS 1638	>4050	▲ 25554	---	---
Particles 50-100µm	count	NAS 1638	>720	▲ 1827	---	---
Particles >100µm	count	NAS 1638	>128	▲ 293	---	---

Customer Id: SMABRI
 Sample No.: WC0813447
 Lab Number: 02564571
 Test Package: AVI 3



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Kevin Marson +1 (289)291-4644 x4644
Kevin.Marson@wearcheck.com

To change component or sample information:
 Gloria Gonzalez +1 (289)291-4643 x4643
gloria.gonzalez@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Filter	---	---	?	We advise that you perform a filter service, and use off-line filtration to improve the cleanliness of the system fluid.
Resample	---	---	?	We recommend an early resample to monitor this condition.
Information Required	---	---	?	NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.
Check Fluid Source	---	---	?	Confirm the source of the lubricant being utilized for top-up/fill.
Filter Fluid	---	---	?	We advise that you perform a filter service, and use off-line filtration to improve the cleanliness of the system fluid.


HISTORICAL DIAGNOSIS



OIL ANALYSIS REPORT

Sample Rating Trend

ADDITIVES

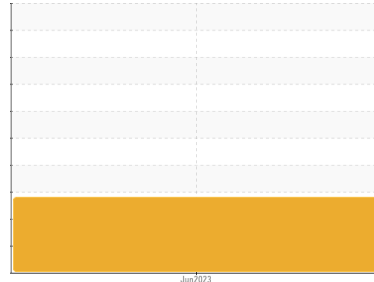

Machine Id
[N617QX] BOMBARDIER CRJ700 N617QX
 Component
2 Hydraulic System
 Fluid
SKYDROL LD-4 (--- GAL)

DIAGNOSIS

Recommendation

We advise that you perform a filter service, and use off-line filtration to improve the cleanliness of the system fluid. Confirm the source of the lubricant being utilized for top-up/fill. We recommend an early resample to monitor this condition. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.

Wear

All component wear rates are normal. The direct-reading & analytical ferrographic results are normal indicating no abnormal wear in the system.

Contaminants

There is a moderate amount of particulates (2 to 100 microns in size) present in the oil. The water content is negligible.

Oil Condition

Additive levels indicate the addition of a different brand, or type of oil. The AN level is acceptable for this fluid. The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	WC0813447	---	---
Sample Date	Client Info	12 Jun 2023	---	---
TSN	hrs Client Info	37533	---	---
TSO	hrs Client Info	0	---	---
Oil Age	hrs Client Info	0	---	---
Oil Changed	Client Info	Not Chngd	---	---
Sample Status		ABNORMAL	---	---

WEAR METALS

method	limit/base	current	history1	history2
Iron	ppm ASTM D5185(m) >20	1	---	---
Chromium	ppm ASTM D5185(m) >10	<1	---	---
Nickel	ppm ASTM D5185(m) >10	<1	---	---
Titanium	ppm ASTM D5185(m)	0	---	---
Silver	ppm ASTM D5185(m)	0	---	---
Aluminum	ppm ASTM D5185(m) >10	<1	---	---
Lead	ppm ASTM D5185(m) >20	<1	---	---
Copper	ppm ASTM D5185(m) >20	2	---	---
Tin	ppm ASTM D5185(m) >10	0	---	---
Antimony	ppm ASTM D5185(m)	<1	---	---
Vanadium	ppm ASTM D5185(m)	0	---	---
Beryllium	ppm ASTM D5185(m)	0	---	---
Cadmium	ppm ASTM D5185(m)	2	---	---

ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185(m) 0	<1	---	---
Barium	ppm ASTM D5185(m) 0	0	---	---
Molybdenum	ppm ASTM D5185(m) 0	0	---	---
Manganese	ppm ASTM D5185(m)	<1	---	---
Magnesium	ppm ASTM D5185(m) 0	<1	---	---
Calcium	ppm ASTM D5185(m) 0	▲ 119	---	---
Phosphorus	ppm ASTM D5185(m) 20000	34315	---	---
Zinc	ppm ASTM D5185(m) 0	7	---	---
Sulfur	ppm ASTM D5185(m) 1900	▲ 544	---	---
Lithium	ppm ASTM D5185(m)	<1	---	---

CONTAMINANTS






method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185(m) >15	2	---	---
Sodium	ppm ASTM D5185(m)	8	---	---
Potassium	ppm ASTM D5185(m) >20	31	---	---
Water	% ASTM D6304* >0.6	0.210	---	---
ppm Water	ppm ASTM D6304* >6000	2104.5	---	---

FLUID CLEANLINESS

method	limit/base	current	history1	history2
Particles 5-15µm	count NAS 1638 >128000	▲ 1203320	---	---
Particles 15-25µm	count NAS 1638 >22800	▲ 76680	---	---
Particles 25-50µm	count NAS 1638 >4050	▲ 25554	---	---
Particles 50-100µm	count NAS 1638 >720	▲ 1827	---	---
Particles >100µm	count NAS 1638 >128	▲ 293	---	---
NAS 1638	Class NAS 1638 >9	>12	---	---



OIL ANALYSIS REPORT

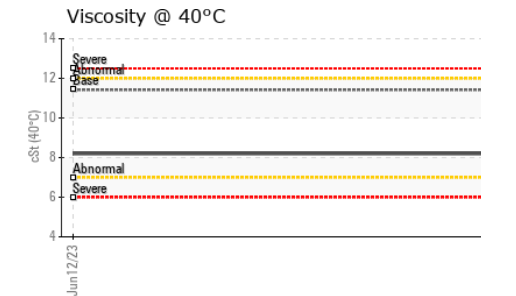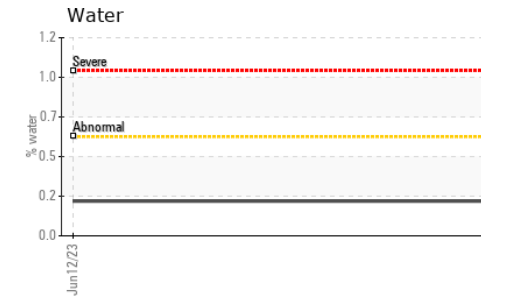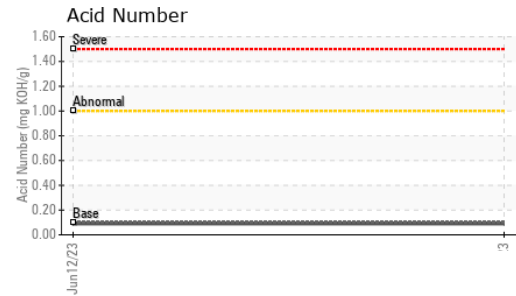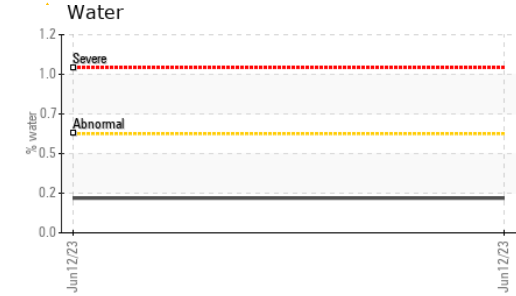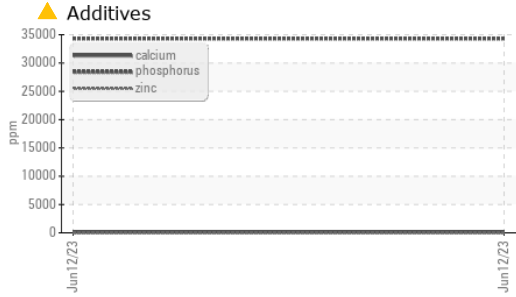

FLUID DEGRADATION	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974*	0.10	0.09	---






VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	---
Yellow Metal	scalar	Visual*	NONE	NONE	---
Precipitate	scalar	Visual*	NONE	NONE	---
Silt	scalar	Visual*	NONE	NONE	---
Debris	scalar	Visual*	NONE	NONE	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---
Appearance	scalar	Visual*	NORML	NORML	---
Odor	scalar	Visual*	NORML	NORML	---
Emulsified Water	scalar	Visual*	>0.6	NEG	---
Free Water	scalar	Visual*		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	11.42	8.2	---

SAMPLE IMAGES

	method	limit/base	current	history1	history2
Color				<i>no image</i>	<i>no image</i>
Bottom				<i>no image</i>	<i>no image</i>

GRAPHS

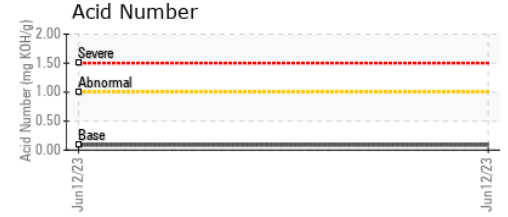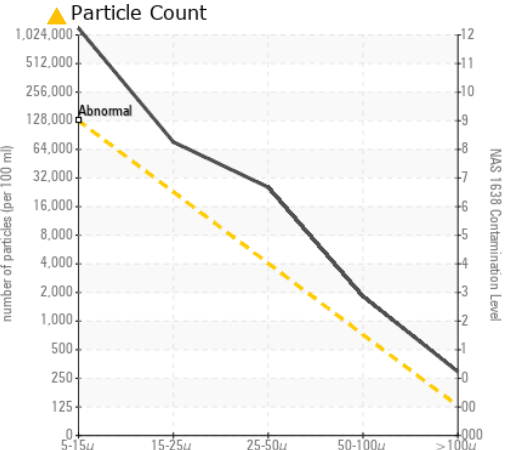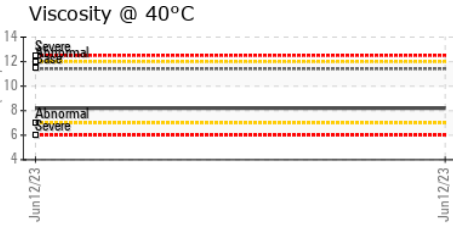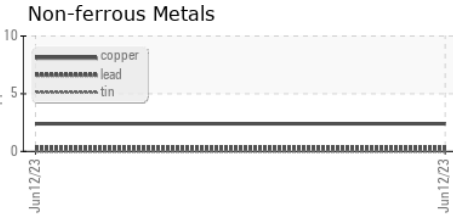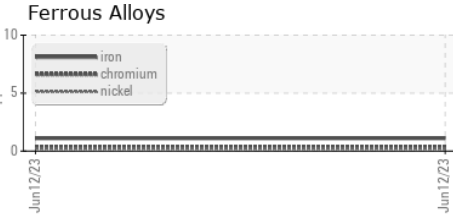




Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0813447 **Received** : 15 Jun 2023
Lab Number : 02564571 **Diagnosed** : 20 Jun 2023
Unique Number : 5593612 **Diagnostician** : Kevin Marson
Test Package : AVI 3 (Additional Tests: KF, PrtCount)

SMART AVIATION
 775 COUNTY ROAD 64
 BRIGHTON, ON
 CA K0K 1H0
 Contact: Mark Rinaldi
 mark.rinaldi@smartams.ca
 T: (343)645-4361
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.

FERROGRAPHY REPORT

Machine Id
[N617QX] BOMBARDIER CRJ700 N617QX
 Component
2 Hydraulic System
 Fluid
SKYDROL LD-4 (--- GAL)

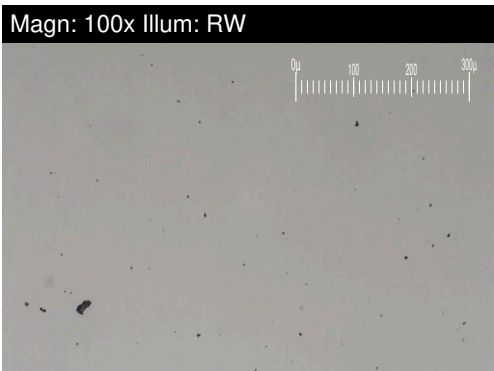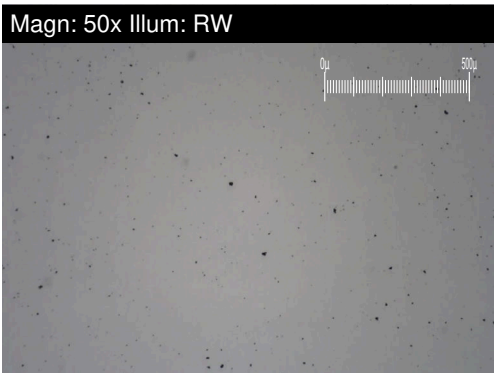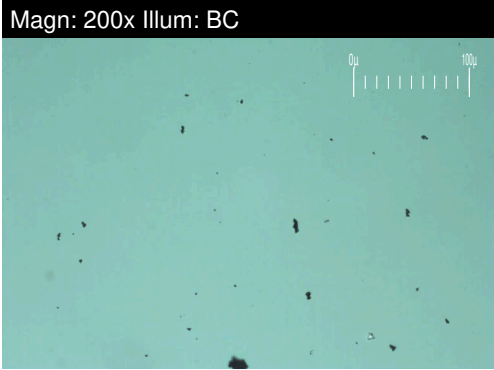


DR-FERROGRAPHY		method	limit/base	current	history1	history2
Large Particles		DR-Ferr*		4.2	---	---
Small Particles		DR-Ferr*		3.9	---	---
Total Particles		DR-Ferr*	>---	8.1	---	---
Large Particles Percentage	%	DR-Ferr*		3.7	---	---
Severity Index		DR-Ferr*		1	---	---

FERROGRAPHY		method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*		1		
Ferrous Sliding	Scale 0-10	ASTM D7684*				
Ferrous Cutting	Scale 0-10	ASTM D7684*				
Ferrous Rolling	Scale 0-10	ASTM D7684*		1		
Ferrous Break-in	Scale 0-10	ASTM D7684*				
Ferrous Spheres	Scale 0-10	ASTM D7684*				
Ferrous Black Oxides	Scale 0-10	ASTM D7684*				
Ferrous Red Oxides	Scale 0-10	ASTM D7684*				
Ferrous Corrosive	Scale 0-10	ASTM D7684*				
Ferrous Other	Scale 0-10	ASTM D7684*				
Nonferrous Rubbing	Scale 0-10	ASTM D7684*				
Nonferrous Sliding	Scale 0-10	ASTM D7684*				
Nonferrous Cutting	Scale 0-10	ASTM D7684*				
Nonferrous Rolling	Scale 0-10	ASTM D7684*				
Nonferrous Other	Scale 0-10	ASTM D7684*				
Carbonaceous Material	Scale 0-10	ASTM D7684*				
Lubricant Degradation	Scale 0-10	ASTM D7684*				
Sand/Dirt	Scale 0-10	ASTM D7684*		1		
Fibres	Scale 0-10	ASTM D7684*				
Spheres	Scale 0-10	ASTM D7684*				
Other	Scale 0-10	ASTM D7684*		2		

WEAR

All component wear rates are normal. The direct-reading & analytical ferrographic results are normal indicating no abnormal wear in the system.

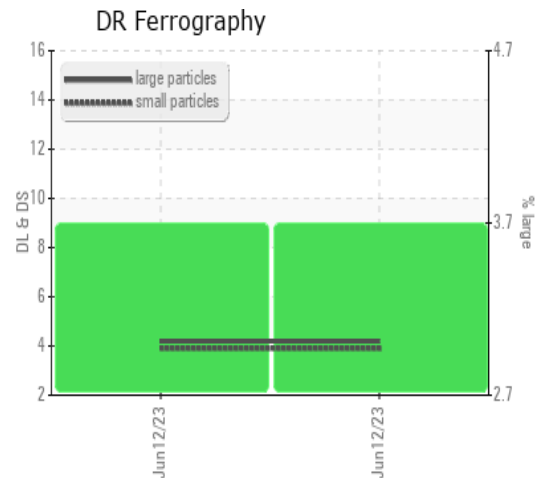

This page left intentionally blank