




# OIL ANALYSIS REPORT

Sample Rating Trend

**NORMAL**

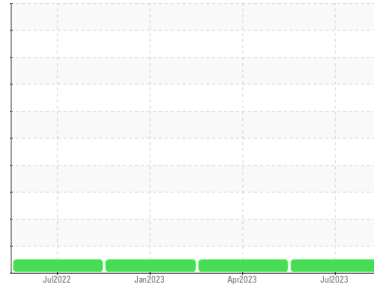

Area  
**Main Engine #3**  
 Machine Id  
**Main Engine #3 Sump**  
 Component  
**Left Main Engine**  
 Fluid  
**CASTROL MHP 154 (--- GAL)**

## DIAGNOSIS

### Recommendation

Resample at the next service interval to monitor.  
 NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.

### Wear

All component wear rates are normal. The direct-reading & analytical ferrographic results are normal indicating no abnormal wear in the system.

### Contaminants

There is no indication of any contamination in the oil.

### Oil Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			<b>WC0810859</b>	WC0763457	WC0763467
Sample Date	Client Info			<b>26 Jul 2023</b>	09 Apr 2023	29 Jan 2023
Machine Age	hrs	Client Info		<b>0</b>	0	0
Oil Age	hrs	Client Info		<b>0</b>	0	0
Oil Changed	Client Info			<b>N/A</b>	N/A	N/A
Sample Status				<b>NORMAL</b>	NORMAL	NORMAL

CONTAMINATION		method	limit/base	current	history1	history2
Fuel	WC Method		>4.0	<b>&lt;1.0</b>	<1.0	<1.0
Glycol	WC Method			<b>NEG</b>	NEG	NEG

WEAR METALS		method	limit/base	current	history1	history2
PQ		ASTM D8184*		<b>0</b>	0	0
Iron	ppm	ASTM D5185(m)	>75	<b>4</b>	4	3
Chromium	ppm	ASTM D5185(m)	>8	<b>0</b>	0	0
Nickel	ppm	ASTM D5185(m)	>2	<b>0</b>	<1	<1
Titanium	ppm	ASTM D5185(m)	>3	<b>0</b>	<1	<1
Silver	ppm	ASTM D5185(m)	>2	<b>0</b>	0	0
Aluminum	ppm	ASTM D5185(m)	>15	<b>2</b>	2	2
Lead	ppm	ASTM D5185(m)	>18	<b>0</b>	0	0
Copper	ppm	ASTM D5185(m)	>80	<b>1</b>	2	1
Tin	ppm	ASTM D5185(m)	>14	<b>0</b>	<1	0
Antimony	ppm	ASTM D5185(m)		<b>0</b>	0	<1
Vanadium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Beryllium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Cadmium	ppm	ASTM D5185(m)		<b>0</b>	0	0




ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)		<b>2</b>	2	2
Barium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185(m)		<b>&lt;1</b>	<1	<1
Manganese	ppm	ASTM D5185(m)		<b>&lt;1</b>	<1	<1
Magnesium	ppm	ASTM D5185(m)		<b>26</b>	27	28
Calcium	ppm	ASTM D5185(m)		<b>5383</b>	5644	5695
Phosphorus	ppm	ASTM D5185(m)		<b>940</b>	956	983
Zinc	ppm	ASTM D5185(m)		<b>1000</b>	1005	1006
Sulfur	ppm	ASTM D5185(m)		<b>10008</b>	10253	10193
Lithium	ppm	ASTM D5185(m)		<b>&lt;1</b>	<1	<1

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	>20	<b>9</b>	6	9
Sodium	ppm	ASTM D5185(m)	>75	<b>1</b>	1	1
Potassium	ppm	ASTM D5185(m)	>20	<b>&lt;1</b>	2	<1

INFRA-RED		method	limit/base	current	history1	history2
Soot %	%	ASTM D7844*	>2	<b>0</b>	0	0
Nitration	Abs/cm	ASTM D7624*	>20	<b>8.2</b>	8.7	6.0
Sulfation	Abs.1mm	ASTM D7415*	>30	<b>13.9</b>	13.7	14.2



# OIL ANALYSIS REPORT



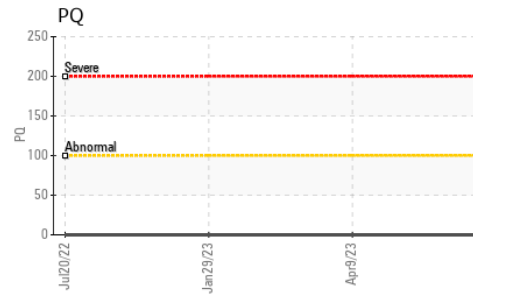
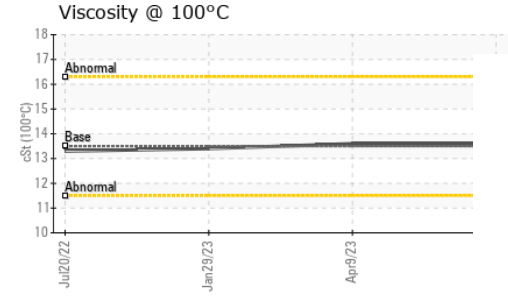
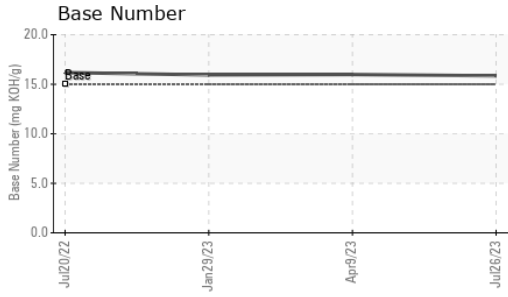


FLUID DEGRADATION		method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	ASTM D7414*	>25	<b>6.4</b>	7.1	5.7
Base Number (BN)	mg KOH/g	ASTM D2896*	15.0	<b>15.85</b>	15.98	15.94

VISUAL		method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.1	<b>NEG</b>	NEG	NEG
Free Water	scalar	Visual*		<b>NEG</b>	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D7279(m)	13.5	<b>13.6</b>	13.6	13.4

## GRAPHS

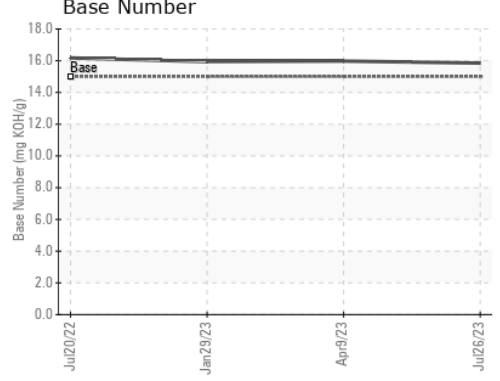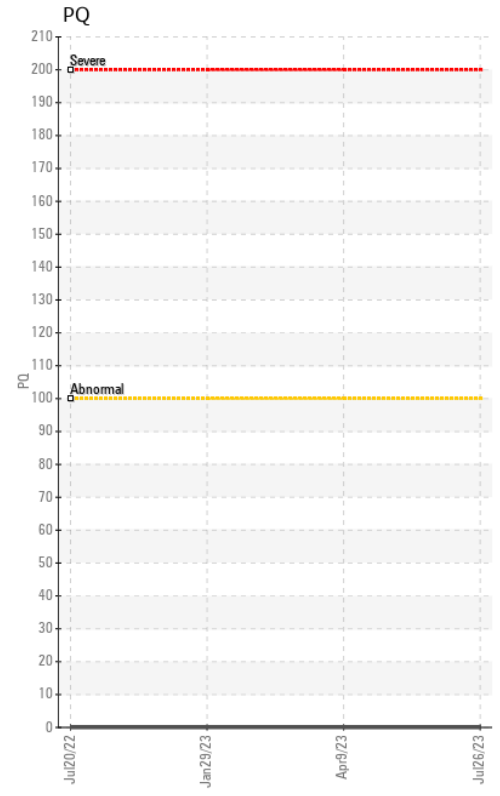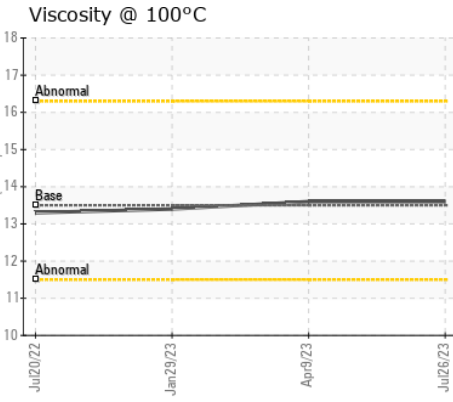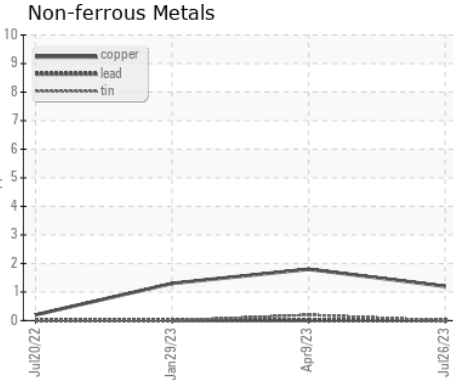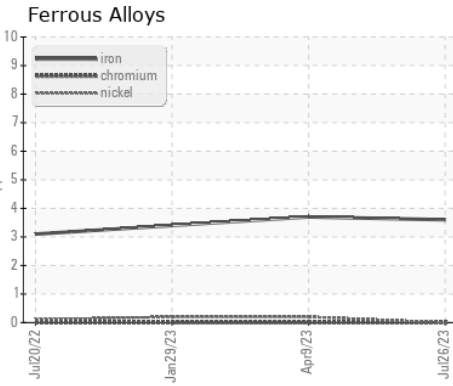

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : WC0810859  
**Lab Number** : **02575872**  
**Unique Number** : 5628932  
**Test Package** : MAR 3




**Canadian Coast Guard**  
 CCGS Vincent Massey, 101 Boul. Champlain  
 Quebec, QC  
 CA G1K 7Y7  
 Contact: Vincent Massey  
 vincentmasseyse@ccgs-ngcc.gc.ca  
 T: (418)573-7423  
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.



# FERROGRAPHY REPORT

Area  
**Main Engine #3**  
 Machine Id  
**Main Engine #3 Sump**  
 Component  
**Left Main Engine**  
 Fluid  
**CASTROL MHP 154 (--- GAL)**

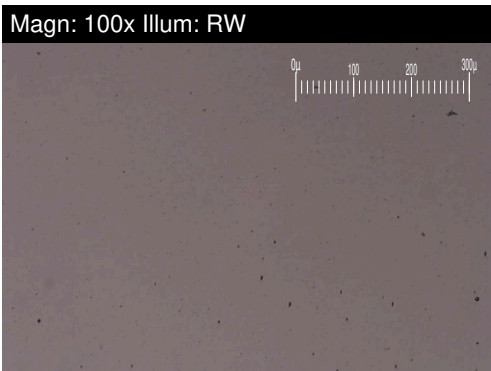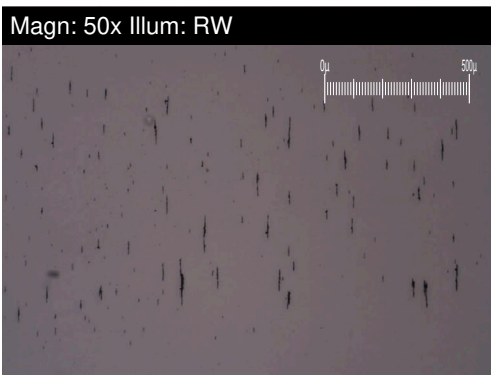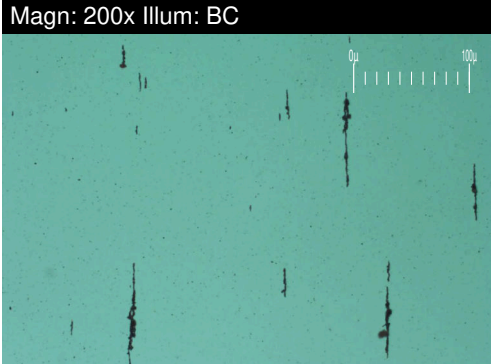


DR-FERROGRAPHY		method	limit/base	current	history1	history2
Large Particles		DR-Ferr*		<b>3.6</b>	4.9	5.1
Small Particles		DR-Ferr*		<b>1.8</b>	3.5	4.2
Total Particles		DR-Ferr*	>---	<b>5.4</b>	8.4	9.3
Large Particles Percentage	%	DR-Ferr*		<b>33.3</b>	16.7	9.7
Severity Index		DR-Ferr*		<b>6</b>	7	5

FERROGRAPHY		method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*		<b>2</b>	1	2
Ferrous Sliding	Scale 0-10	ASTM D7684*				
Ferrous Cutting	Scale 0-10	ASTM D7684*				
Ferrous Rolling	Scale 0-10	ASTM D7684*		<b>1</b>	1	1
Ferrous Break-in	Scale 0-10	ASTM D7684*				
Ferrous Spheres	Scale 0-10	ASTM D7684*				
Ferrous Black Oxides	Scale 0-10	ASTM D7684*		<b>1</b>		
Ferrous Red Oxides	Scale 0-10	ASTM D7684*				
Ferrous Corrosive	Scale 0-10	ASTM D7684*				
Ferrous Other	Scale 0-10	ASTM D7684*				
Nonferrous Rubbing	Scale 0-10	ASTM D7684*				
Nonferrous Sliding	Scale 0-10	ASTM D7684*				
Nonferrous Cutting	Scale 0-10	ASTM D7684*				
Nonferrous Rolling	Scale 0-10	ASTM D7684*				
Nonferrous Other	Scale 0-10	ASTM D7684*				
Carbonaceous Material	Scale 0-10	ASTM D7684*				
Lubricant Degradation	Scale 0-10	ASTM D7684*				
Sand/Dirt	Scale 0-10	ASTM D7684*		<b>1</b>	1	1
Fibres	Scale 0-10	ASTM D7684*				
Spheres	Scale 0-10	ASTM D7684*				
Other	Scale 0-10	ASTM D7684*		<b>1</b>	1	1

## WEAR

All component wear rates are normal. The direct-reading & analytical ferrographic results are normal indicating no abnormal wear in the system.

## DR Ferrography

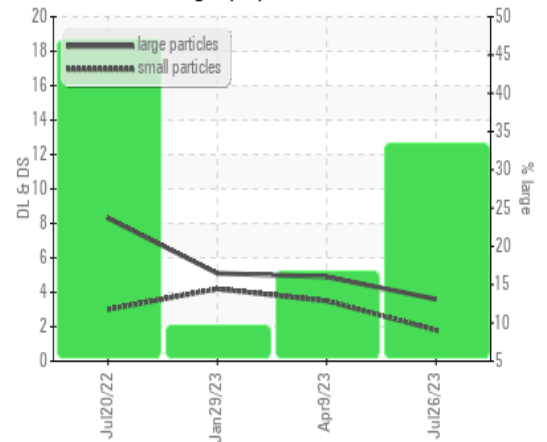

*This page left intentionally blank*