


# PROBLEM SUMMARY

Sample Rating Trend





**WATER**



Area  
**Stackpole International - S02200**  
 Machine Id  
**MI3308**  
 Component  
**Hydraulic System**  
 Fluid  
**NOT GIVEN (--- GAL)**

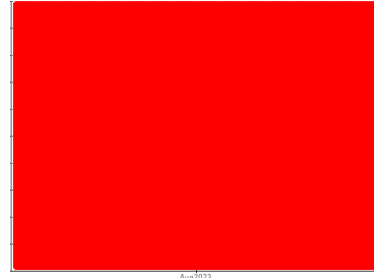

## COMPONENT CONDITION SUMMARY

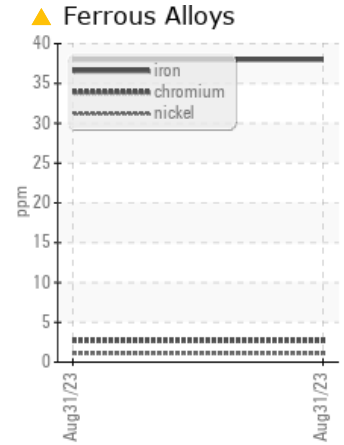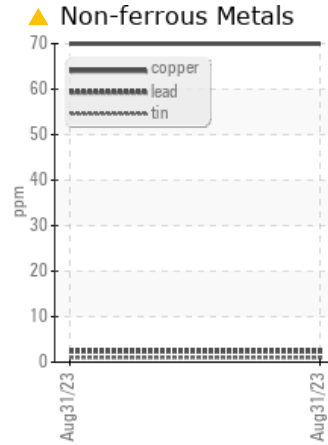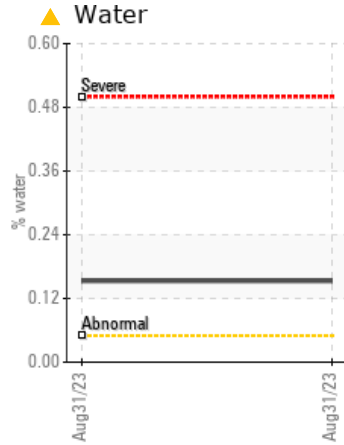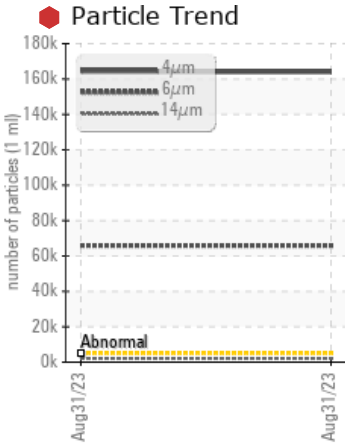

## RECOMMENDATION

This is a baseline read-out on the submitted sample.

## PROBLEMATIC TEST RESULTS

Sample Status				SEVERE	---	---
Iron	ppm	ASTM D5185(m)	>20	▲ 38	---	---
Copper	ppm	ASTM D5185(m)	>20	▲ 70	---	---
Water	%	ASTM D6304*	>0.05	▲ 0.153	---	---
ppm Water	ppm	ASTM D6304*	>500	▲ 1530.8	---	---
Particles >4µm		ASTM D7647	>5000	● 164034	---	---
Particles >6µm		ASTM D7647	>1300	● 65867	---	---
Particles >14µm		ASTM D7647	>160	● 2084	---	---
Particles >21µm		ASTM D7647	>40	● 376	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	● 25/23/18	---	---
Free Water	scalar	Visual*		● 1%	---	---

Customer Id: CHECOB  
 Sample No.: E30000230  
 Lab Number: 02580696  
 Test Package: IND 2



To manage this report scan the QR code

To discuss the diagnosis or test data:  
 Tatiana Sorkina +1 (800)263-3939  
[tsorkina@e360s.ca](mailto:tsorkina@e360s.ca)

To change component or sample information:  
 Gloria Gonzalez +1 (289)291-4643 x4643  
[gloria.gonzalez@wearcheck.com](mailto:gloria.gonzalez@wearcheck.com)

RECOMMENDED ACTIONS


*There are no recommended actions for this sample.*

HISTORICAL DIAGNOSIS

# OIL ANALYSIS REPORT

Sample Rating Trend

**WATER**

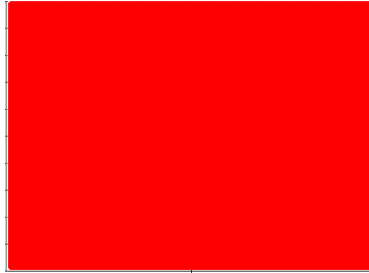

Area  
**Stackpole International - S02200**  
 Machine Id  
**MI3308**  
 Component  
**Hydraulic System**  
 Fluid  
**NOT GIVEN (--- GAL)**

## DIAGNOSIS

### Recommendation

This is a baseline read-out on the submitted sample.

### Wear

Copper and iron ppm levels are noted.

### Contamination

Particles >14µm are severely high. Particles >21µm are severely high. Particles >6µm are severely high. Particles >4µm are severely high. Oil Cleanliness are severely high. Water and ppm water contamination levels are abnormal.

### Fluid Condition

{not applicable}

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>E30000230</b>	---	---
Sample Date	Client Info		<b>31 Aug 2023</b>	---	---
Machine Age	hrs	Client Info	<b>0</b>	---	---
Oil Age	hrs	Client Info	<b>0</b>	---	---
Oil Changed	Client Info		<b>N/A</b>	---	---
Sample Status			<b>SEVERE</b>	---	---

## WEAR METALS

	method	limit/base	current	history1	history2
PQ	ASTM D8184*		<b>0</b>	---	---
Iron	ppm	ASTM D5185(m) >20	<b>38</b>	---	---
Chromium	ppm	ASTM D5185(m) >20	<b>3</b>	---	---
Nickel	ppm	ASTM D5185(m) >20	<b>1</b>	---	---
Titanium	ppm	ASTM D5185(m)	<b>&lt;1</b>	---	---
Silver	ppm	ASTM D5185(m)	<b>0</b>	---	---
Aluminum	ppm	ASTM D5185(m) >20	<b>6</b>	---	---
Lead	ppm	ASTM D5185(m) >20	<b>2</b>	---	---
Copper	ppm	ASTM D5185(m) >20	<b>70</b>	---	---
Tin	ppm	ASTM D5185(m) >20	<b>1</b>	---	---
Antimony	ppm	ASTM D5185(m)	<b>0</b>	---	---
Vanadium	ppm	ASTM D5185(m)	<b>0</b>	---	---
Beryllium	ppm	ASTM D5185(m)	<b>0</b>	---	---
Cadmium	ppm	ASTM D5185(m)	<b>0</b>	---	---

## ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)	<b>&lt;1</b>	---	---
Barium	ppm	ASTM D5185(m)	<b>&lt;1</b>	---	---
Molybdenum	ppm	ASTM D5185(m)	<b>0</b>	---	---
Manganese	ppm	ASTM D5185(m)	<b>9</b>	---	---
Magnesium	ppm	ASTM D5185(m)	<b>6</b>	---	---
Calcium	ppm	ASTM D5185(m)	<b>45</b>	---	---
Phosphorus	ppm	ASTM D5185(m)	<b>410</b>	---	---
Zinc	ppm	ASTM D5185(m)	<b>315</b>	---	---
Sulfur	ppm	ASTM D5185(m)	<b>1340</b>	---	---
Lithium	ppm	ASTM D5185(m)	<b>&lt;1</b>	---	---






## CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m) >15	<b>4</b>	---	---
Sodium	ppm	ASTM D5185(m)	<b>2</b>	---	---
Potassium	ppm	ASTM D5185(m) >20	<b>1</b>	---	---
Water	%	ASTM D6304* >0.05	<b>0.153</b>	---	---
ppm Water	ppm	ASTM D6304* >500	<b>1530.8</b>	---	---

## FLUID CLEANLINESS

	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>5000	<b>164034</b>	---	---
Particles >6µm	ASTM D7647	>1300	<b>65867</b>	---	---
Particles >14µm	ASTM D7647	>160	<b>2084</b>	---	---
Particles >21µm	ASTM D7647	>40	<b>376</b>	---	---
Particles >38µm	ASTM D7647	>10	<b>8</b>	---	---
Particles >71µm	ASTM D7647	>3	<b>1</b>	---	---
Oil Cleanliness	ISO 4406 (c)	>19/17/14	<b>25/23/18</b>	---	---

# OIL ANALYSIS REPORT

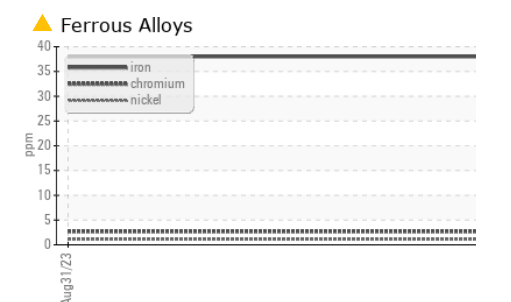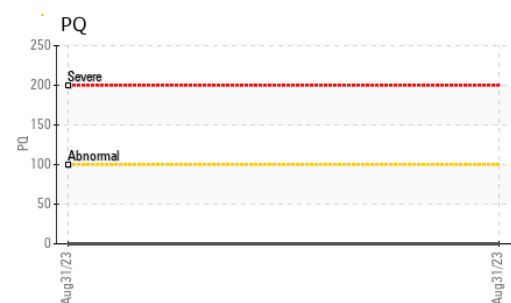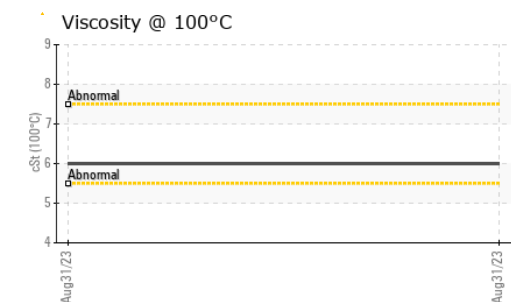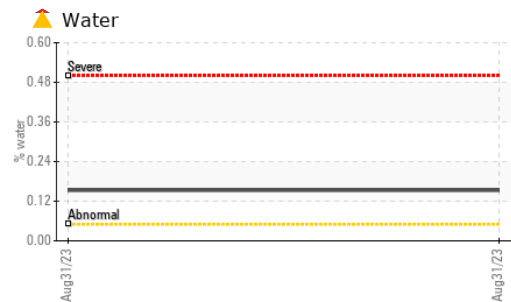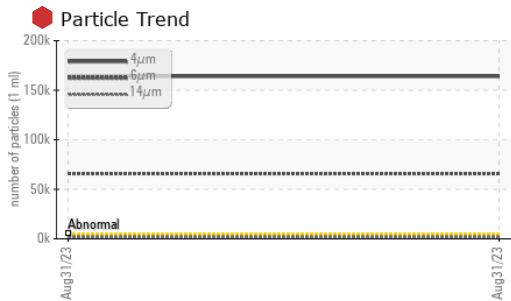





FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974*		<b>0.53</b>	---	---

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	<b>NONE</b>	---	---
Yellow Metal	scalar	Visual*	NONE	<b>NONE</b>	---	---
Precipitate	scalar	Visual*	NONE	<b>VLITE</b>	---	---
Silt	scalar	Visual*	NONE	<b>NONE</b>	---	---
Debris	scalar	Visual*	NONE	<b>NONE</b>	---	---
Sand/Dirt	scalar	Visual*	NONE	<b>NONE</b>	---	---
Appearance	scalar	Visual*	NORML	<b>WGOIL</b>	---	---
Odor	scalar	Visual*	NORML	<b>NORML</b>	---	---
Emulsified Water	scalar	Visual*	>0.05	<b>.2%</b>	---	---
Free Water	scalar	Visual*		<b>1%</b>	---	---

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)		<b>41.9</b>	---	---
Visc @ 100°C	cSt	ASTM D7279(m)		<b>6</b>	---	---
Viscosity Index (VI)	Scale	ASTM D2270*		<b>81</b>	---	---

SAMPLE IMAGES		method	limit/base	current	history1	history2
Color					no image	no image
Bottom					no image	no image

## GRAPHS

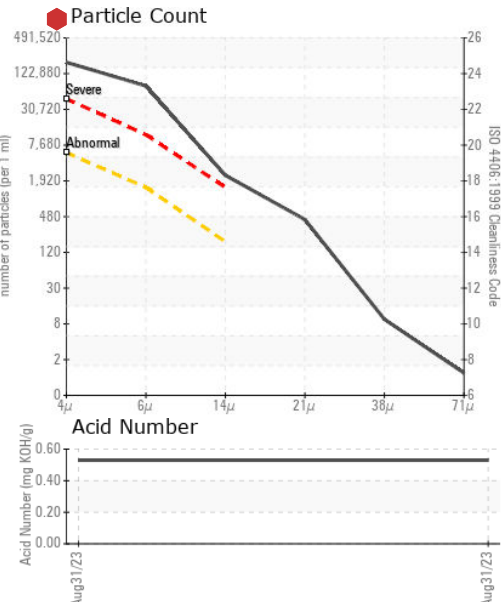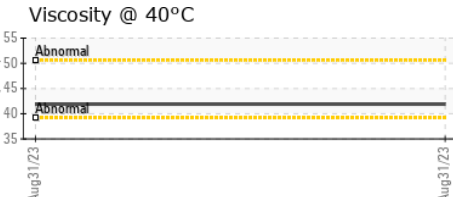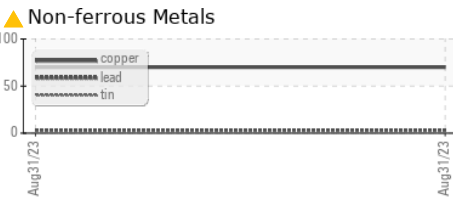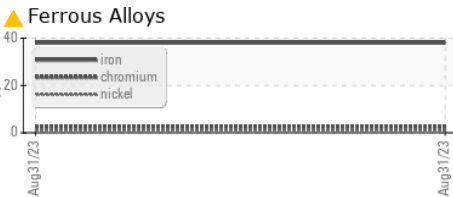

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : E3000230  
**Lab Number** : 02580696  
**Unique Number** : 5633756  
**Test Package** : IND 2 ( Additional Tests: KF, KV100, PQ, VI )

**Environmental 360 Solutions Ltd.**  
 640 Victoria Street  
 Cobourg, ON  
 CA K9A 5H5  
 Contact: Tatiana Sorkina  
 tsorkina@e360s.ca  
 T: (800)263-3939  
 F: (905)373-4950

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.