




# PROBLEM SUMMARY

Area  
**Saugen Shores SP-17701**  
 Machine Id  
**09K04**  
 Component  
**Grease**  
 Fluid  
**SKF LGWM 1 (--- LTR)**

Sample Rating Trend

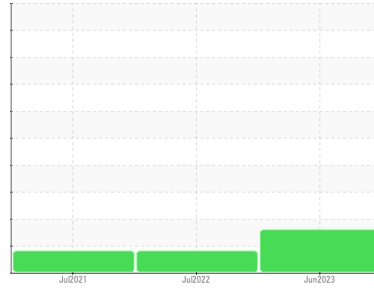

## VISCOSITY



### COMPONENT CONDITION SUMMARY

No relevant graphs to display

### RECOMMENDATION

We recommend an early resample to monitor this condition.

### PROBLEMATIC TEST RESULTS

Sample Status				SEVERE	MARGINAL	ABNORMAL
NLGI Consistency	NLGI Scale	SKF Method*	1	000	00	00
PrtFilter						

**Customer Id:** VESTAS  
**Sample No.:** PP0835246  
**Lab Number:** 02590801  
**Test Package:** GRS 1



To manage this report scan the QR code

To discuss the diagnosis or test data:  
 Bill Quesnel CLS,OMA II,MLA-III,LLA-I +1  
 (289)291-4641 x4641  
[Bill.Quesnel@wearcheck.com](mailto:Bill.Quesnel@wearcheck.com)

To change component or sample information:  
 Gloria Gonzalez +1 (289)291-4643 x4643  
[gloria.gonzalez@wearcheck.com](mailto:gloria.gonzalez@wearcheck.com)

## RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Resample	---	---	?	We recommend an early resample to monitor this condition.

## HISTORICAL DIAGNOSIS

**27 Jul 2022 Diag: Bill Quesnel**

### VISCOSITY



No corrective action is recommended at this time. Resample at the next service interval to monitor. All component wear rates are normal. There is no indication of any contamination in the grease. The NLGI grade has decreased from 1 to 00. The condition of the grease is acceptable for the time in service.

view report



**29 Jul 2021 Diag: Kevin Marson**

### VISCOSITY



We recommend an early resample to monitor this condition. All component wear rates are normal. There is no indication of any contamination in the grease. The consistency has dropped by 2 NLGI grades.


view report





# GREASE ANALYSIS

Sample Rating Trend

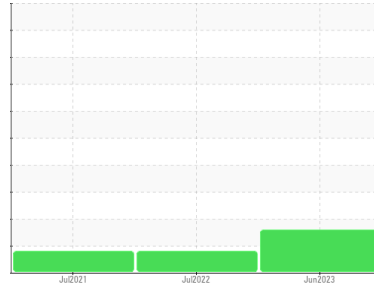

## VISCOSITY



Area  
**Saugen Shores SP-17701**  
 Machine ID  
**09K04**  
 Component  
**Grease**  
 Fluid  
**SKF LGWM 1 (--- LTR)**

### DIAGNOSIS

#### Recommendation

We recommend an early resample to monitor this condition.

#### Wear

All component wear rates are normal.

#### Grease Condition

Grease consistency has changed by 3 NLGI grades from NLGI 1 to 000.

#### Contaminants

There is no indication of any contamination in the grease.

### SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>PP0835246</b>	PP	WC0546361
Sample Date	Client Info		<b>30 Jun 2023</b>	27 Jul 2022	29 Jul 2021
Machine Age	yrs	Client Info	<b>15</b>	0	0
Grease Age	yrs	Client Info	<b>15</b>	0	0
Grease Serviced	Client Info		<b>Not Chngd</b>	N/A	N/A
Sample Status			<b>SEVERE</b>	MARGINAL	ABNORMAL

### WEAR METALS

	method	limit/base	current	history1	history2	
PQ	ASTM D8184*	>200	<b>120</b>	90	890	
Iron	ppm	ASTM D5185(m)	>250	<b>39</b>	54	173
Chromium	ppm	ASTM D5185(m)	>10	<b>&lt;1</b>	<1	1
Nickel	ppm	ASTM D5185(m)	>5	<b>&lt;1</b>	<1	<1
Cadmium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Titanium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Vanadium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Lead	ppm	ASTM D5185(m)	>25	<b>&lt;1</b>	0	0
Copper	ppm	ASTM D5185(m)	>75	<b>2</b>	0	<1
Tin	ppm	ASTM D5185(m)	>5	<b>0</b>	0	0
Silver	ppm	ASTM D5185(m)	>5	<b>&lt;1</b>	0	0

### ADDITIVES

	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185(m)	0	<b>&lt;1</b>	<1	1
Magnesium	ppm	ASTM D5185(m)	0	<b>&lt;1</b>	0	0
Manganese	ppm	ASTM D5185(m)	0	<b>0</b>	<1	<1
Molybdenum	ppm	ASTM D5185(m)	0	<b>0</b>	0	<1
Phosphorus	ppm	ASTM D5185(m)	5	<b>2</b>	7	5
Zinc	ppm	ASTM D5185(m)	20	<b>6</b>	14	16
Antimony	ppm	ASTM D5185(m)	0	<b>0</b>	0	0

### THICKENER/SOAP

	method	limit/base	current	history1	history2	
Aluminum	ppm	ASTM D5185(m)	0	<b>0</b>	<1	<1
Barium	ppm	ASTM D5185(m)	0	<b>&lt;1</b>	0	0
Calcium	ppm	ASTM D5185(m)	40	<b>15</b>	34	24
Sodium	ppm	ASTM D5185(m)	2	<b>4</b>	1	2
Lithium	ppm	ASTM D5185(m)	120	<b>80</b>	113	100
Sulfur	ppm	ASTM D5185(m)	650	<b>535</b>	677	624


### CONTAMINANTS

	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185(m)	>150	<b>&lt;1</b>	<1	<1
Potassium	ppm	ASTM D5185(m)		<b>20</b>	0	<1

### GREASE CONDITION





	method	limit/base	current	history1	history2	
Grease Color	Visual*	Brown	<b>Brown</b>	Brown	Tan	
Texture	In-house*		<b>Buttery</b>	Short fiber	Short fiber	
NLGI Consistency	NLGI Scale	SKF Method*	1	<b>000</b>	00	00

# GREASE ANALYSIS

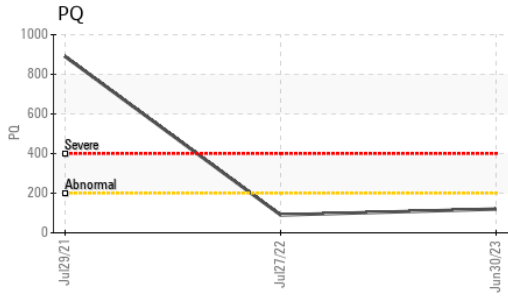

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color					
Bottom					
PrtFilter					

## GRAPHS

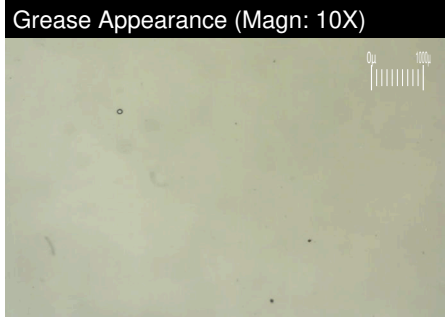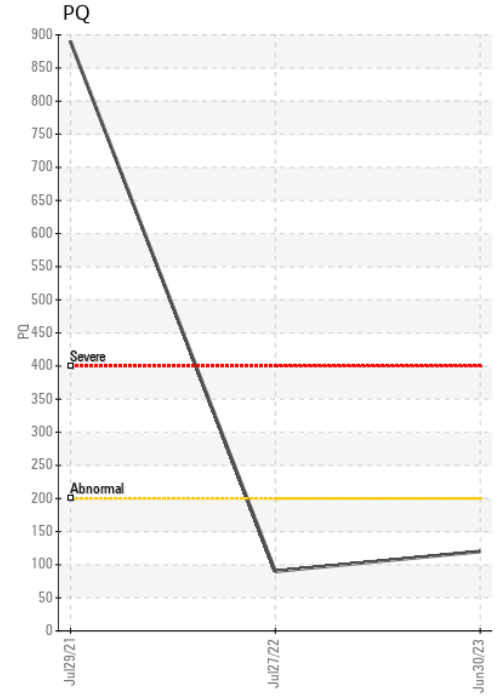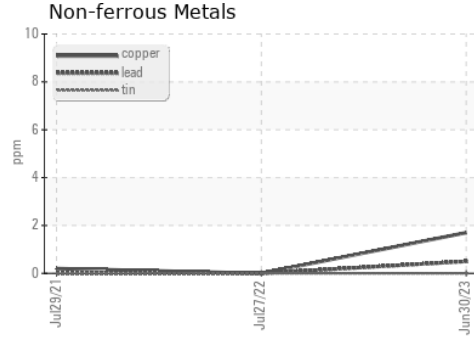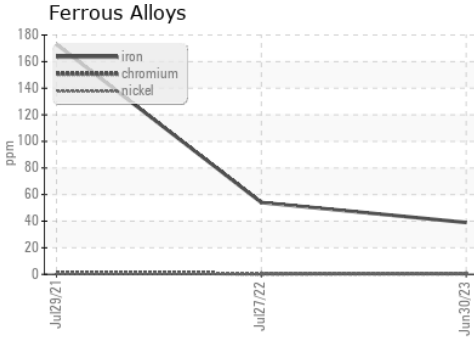

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 Vestas American Wind Technology Inc.  
**Sample No.** : PP0835246 **Received** : 20 Oct 2023  
**Lab Number** : 02590801 **Diagnosed** : 23 Oct 2023  
**Unique Number** : 5659867 **Diagnostician** : Bill Quesnel  
**Test Package** : GRS 1 ( Additional Tests: BottomAnalysis )  
 To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.

1417 NW Everett Street  
 Portland, OR  
 US 97209  
 Contact: Nicole Philippi  
 NiPhi@vestas.com  
 T: (503)327-7683  
 F: (503)327-0247