




OIL ANALYSIS REPORT

Sample Rating Trend

WEAR

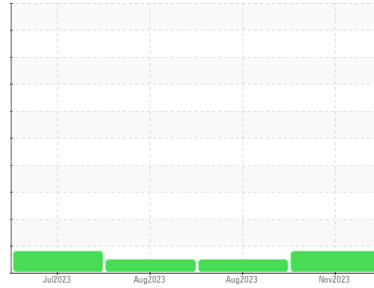

Machine Id
413135
 Component
Diesel Engine
 Fluid
DIESEL ENGINE OIL SAE 15W40 (--- GAL)

DIAGNOSIS

Recommendation

The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

Copper ppm levels are abnormal. An increase in the lead level is noted. Bearing wear is indicated.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The oil is no longer serviceable as a result of the abnormal and/or severe wear.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		WC0875101	GFL0091069	GFL0091062
Sample Date	Client Info		27 Nov 2023	23 Aug 2023	18 Aug 2023
Machine Age	hrs	Client Info	1243	21854	564
Oil Age	hrs	Client Info	543	0	0
Oil Changed	Client Info		Changed	Not Changd	Changed
Sample Status			ABNORMAL	NORMAL	NORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>3.0	<1.0	<1.0	<1.0
Water	WC Method	>0.2	NEG	NEG	NEG
Glycol	WC Method		NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185(m)	>120	16	3	9
Chromium	ppm	ASTM D5185(m)	>20	<1	0	0
Nickel	ppm	ASTM D5185(m)	>5	1	0	<1
Titanium	ppm	ASTM D5185(m)	>2	0	0	0
Silver	ppm	ASTM D5185(m)	>2	<1	<1	1
Aluminum	ppm	ASTM D5185(m)	>20	3	<1	2
Lead	ppm	ASTM D5185(m)	>40	8	<1	2
Copper	ppm	ASTM D5185(m)	>330	▲ 293	10	76
Tin	ppm	ASTM D5185(m)	>15	<1	0	<1
Antimony	ppm	ASTM D5185(m)		0	<1	0
Vanadium	ppm	ASTM D5185(m)		0	0	0
Beryllium	ppm	ASTM D5185(m)		0	0	0
Cadmium	ppm	ASTM D5185(m)		0	0	0

ADDITIVES

	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185(m)	250	5	7	28
Barium	ppm	ASTM D5185(m)	10	<1	0	0
Molybdenum	ppm	ASTM D5185(m)	100	59	58	66
Manganese	ppm	ASTM D5185(m)		<1	<1	<1
Magnesium	ppm	ASTM D5185(m)	450	942	956	931
Calcium	ppm	ASTM D5185(m)	3000	1053	1052	1102
Phosphorus	ppm	ASTM D5185(m)	1150	978	1063	1022
Zinc	ppm	ASTM D5185(m)	1350	1195	1168	1121
Sulfur	ppm	ASTM D5185(m)	4250	2442	2657	2571
Lithium	ppm	ASTM D5185(m)		<1	<1	<1

CONTAMINANTS


	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185(m)	>25	5	4	13
Sodium	ppm	ASTM D5185(m)	>158	1	1	1
Potassium	ppm	ASTM D5185(m)	>20	8	<1	5

INFRA-RED


	method	limit/base	current	history1	history2	
Soot %	%	ASTM D7844*	>4	0.2	0	0
Nitration	Abs/cm	ASTM D7624*	>20	9.2	4.6	6.4
Sulfation	Abs./1mm	ASTM D7415*	>30	20.1	18.8	20.2











OIL ANALYSIS REPORT

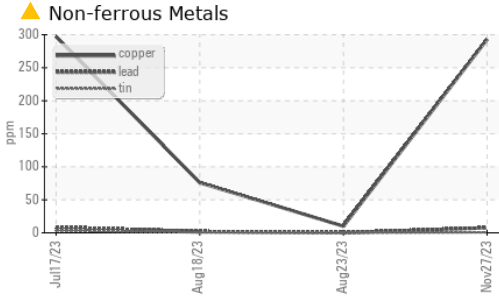

FLUID DEGRADATION		method	limit/base	current	history1	history2
Oxidation	Abs./1mm	ASTM D7414*	>25	16.3	12.8	14.4
VISUAL		method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG	NEG
FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D7279(m)	14.4	13.6	14.4	13.4

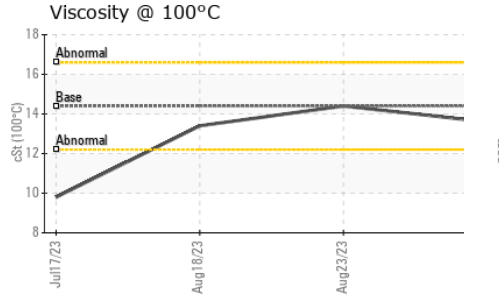

GRAPHS

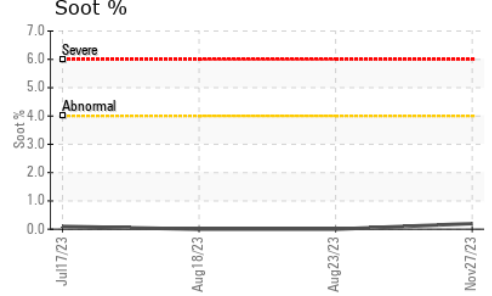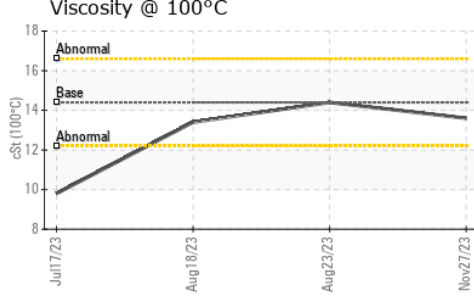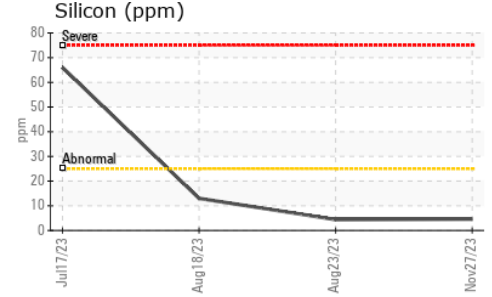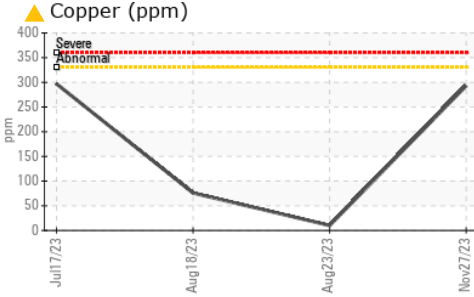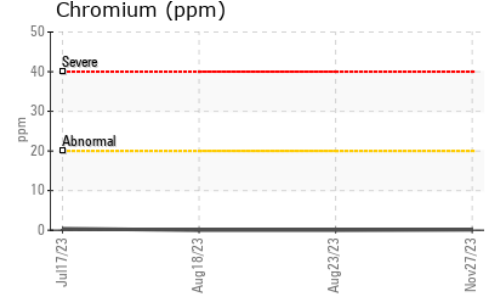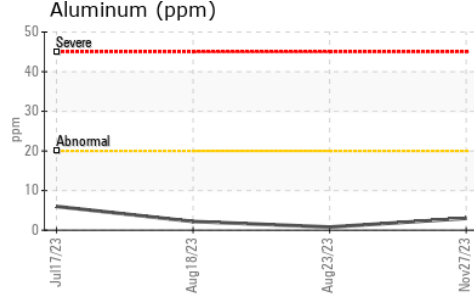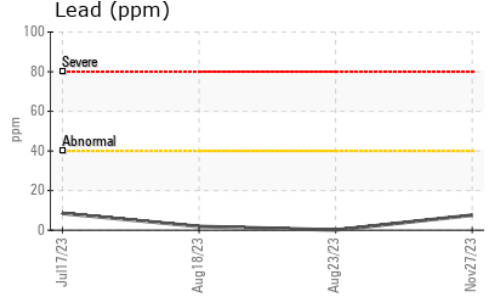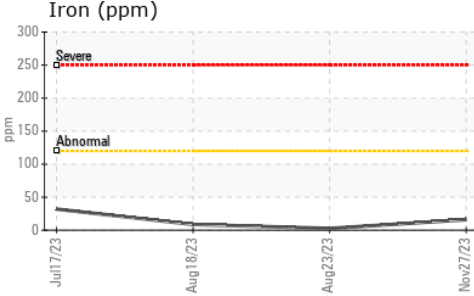

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0875101
Lab Number : 02600925
Unique Number : 5694010
Test Package : MOB 1

GFL Environmental - 217 - Aurora
 14131 BAYVIEW AVE, AURORA YARD
 AURORA, ON
 CA L4G 0K6
 Contact: Mike Havens
 MHavens@gflenv.com
 T:
 F: (905)713-2445

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.