




OIL ANALYSIS REPORT

Sample Rating Trend

WEAR PARTICLES

Area
(C-GCFF)
 Machine Id
BEECHCRAFT PWV-79161
 Component
Left Jet Turbine
 Fluid
EASTMAN TURBO OIL 2380 (10 LTR)

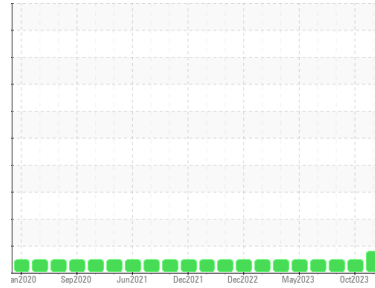

DIAGNOSIS

Recommendation

The filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition. No other corrective action is recommended at this time.

Wear

Wear particle analysis indicates that the ferrous rubbing particles are marginal. All other component wear rates are normal.

Contaminants

The water content is negligible. There is no indication of any contamination in the oil.

Oil Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

method	limit/base	current	history1	history2	
Sample Number	Client Info	WC0875118	WC0854721	WC0835988	
Sample Date	Client Info	19 Dec 2023	18 Oct 2023	24 Aug 2023	
TSN	hrs	Client Info	18129	17951	17742
TSO	hrs	Client Info	1679	1500	1292
Oil Age	hrs	Client Info	1679	1500	1292
Oil Changed	Client Info	Not Chngd	Not Chngd	Not Chngd	
Sample Status		MARGINAL	NORMAL	NORMAL	

WEAR METALS

method	limit/base	current	history1	history2		
Iron	ppm	ASTM D5185(m)	>8	0	0	0
Chromium	ppm	ASTM D5185(m)	>2	0	0	0
Nickel	ppm	ASTM D5185(m)	>2	0	0	0
Titanium	ppm	ASTM D5185(m)	>2	0	0	0
Silver	ppm	ASTM D5185(m)	>2	0	<1	0
Aluminum	ppm	ASTM D5185(m)	>2	<1	0	<1
Lead	ppm	ASTM D5185(m)	>3	0	0	0
Copper	ppm	ASTM D5185(m)	>3	0	<1	0
Tin	ppm	ASTM D5185(m)	>2	0	0	0
Antimony	ppm	ASTM D5185(m)		0	0	0
Vanadium	ppm	ASTM D5185(m)		0	0	0
Beryllium	ppm	ASTM D5185(m)		0	0	0
Cadmium	ppm	ASTM D5185(m)		0	0	0

ADDITIVES

method	limit/base	current	history1	history2		
Boron	ppm	ASTM D5185(m)	0	0	<1	<1
Barium	ppm	ASTM D5185(m)	0	0	<1	0
Molybdenum	ppm	ASTM D5185(m)	0	0	0	0
Manganese	ppm	ASTM D5185(m)		0	0	0
Magnesium	ppm	ASTM D5185(m)	0	0	0	<1
Calcium	ppm	ASTM D5185(m)	0	0	0	<1
Phosphorus	ppm	ASTM D5185(m)	2500	2761	2696	2739
Zinc	ppm	ASTM D5185(m)	0	<1	<1	2
Sulfur	ppm	ASTM D5185(m)	0	0	6	5
Lithium	ppm	ASTM D5185(m)		<1	<1	<1

CONTAMINANTS





method	limit/base	current	history1	history2		
Silicon	ppm	ASTM D5185(m)	>8	3	2	3
Sodium	ppm	ASTM D5185(m)		0	<1	<1
Potassium	ppm	ASTM D5185(m)	>20	<1	<1	<1
Water	%	ASTM D6304*	>0.1	0.025	0.065	0.075
ppm Water	ppm	ASTM D6304*	>1000	258	656.2	750.2

FLUID DEGRADATION

method	limit/base	current	history1	history2		
Acid Number (AN)	mg KOH/g	ASTM D974*	0.43	0.37	0.31	0.25




OIL ANALYSIS REPORT

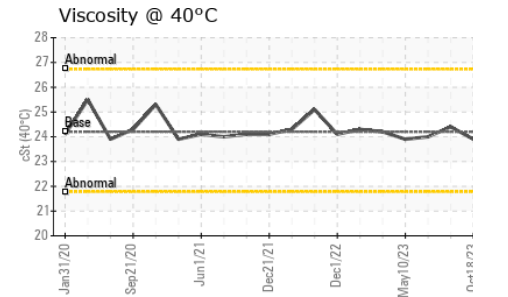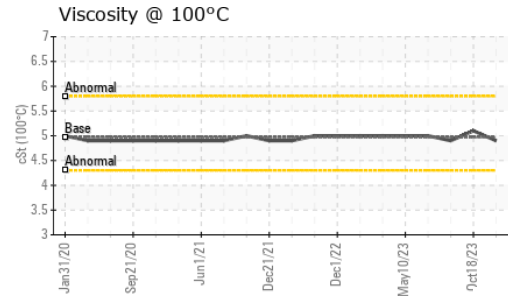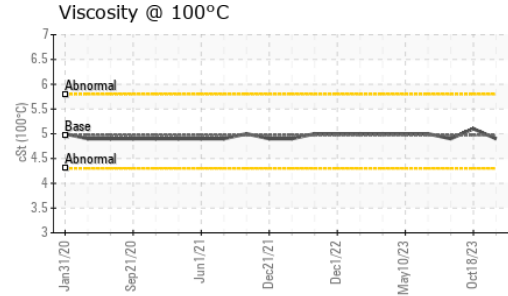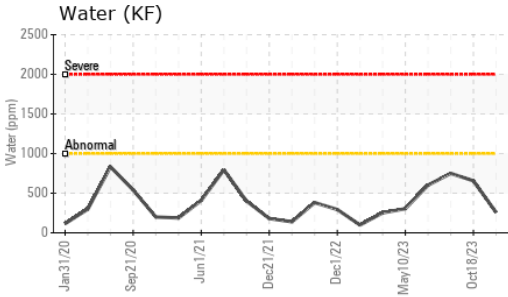





VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE
Precipitate	scalar	Visual*	NONE	NONE	NONE
Silt	scalar	Visual*	NONE	NONE	NONE
Debris	scalar	Visual*	NONE	NONE	NONE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.1	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 40°C	cSt	ASTM D7279(m)	24.2	24.6	23.9	24.4
Visc @ 100°C	cSt	ASTM D7279(m)	4.97	4.9	5.1	4.9
Viscosity Index (VI)	Scale	ASTM D2270*	134	124	148	126

SAMPLE IMAGES

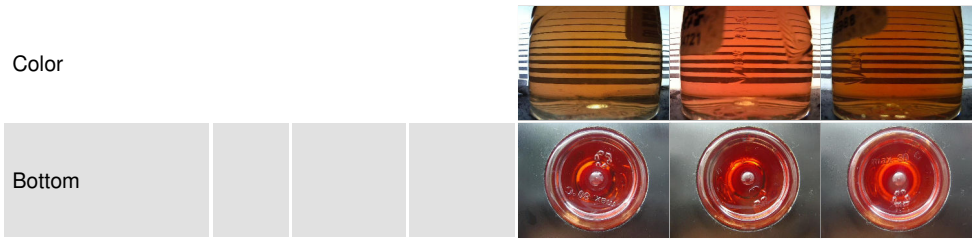

GRAPHS

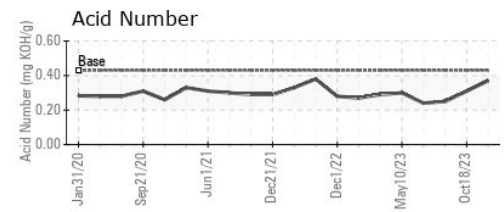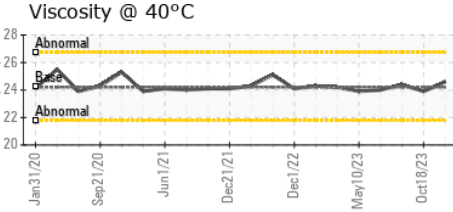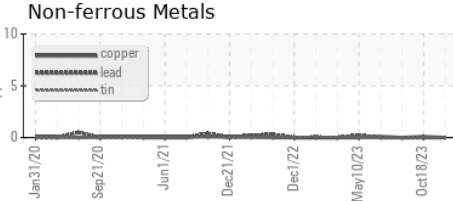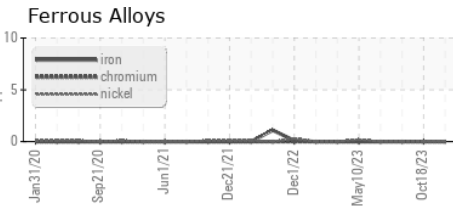

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0875118 **Received** : 22 Dec 2023
Lab Number : 02604946 **Diagnosed** : 04 Jan 2024
Unique Number : 5698031 **Diagnostician** : Kevin Marson
Test Package : AVI 3


Skynorth Air
 175 West Hangar Road
 Winnipeg, MB
 CA R3J 3Z1
 Contact: Rowena Roopchand
 parts@skynorthair.com
 T: (204)338-8039
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.

FERROGRAPHY REPORT

Area
(C-GCFF)
 Machine Id
BEECHCRAFT PWV-79161
 Component
Left Jet Turbine
 Fluid
EASTMAN TURBO OIL 2380 (10 LTR)


Magn: 200x Illum: BC

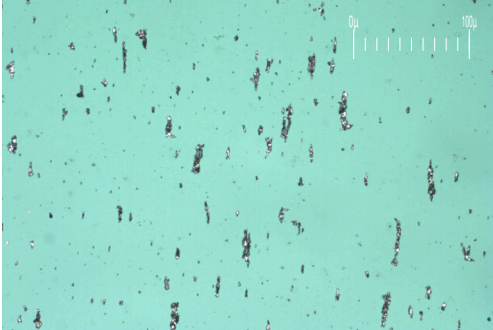

Magn: 50x Illum: RW



Magn: 100x Illum: RW

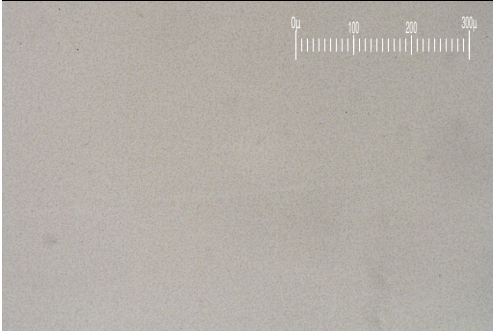


DR-FERROGRAPHY		method	limit/base	current	history1	history2
Large Particles		DR-Ferr*		1.4	4.4	0.9
Small Particles		DR-Ferr*		0.9	0.8	0.8
Total Particles		DR-Ferr*	>---	2.3	5.2	1.7
Large Particles Percentage	%	DR-Ferr*		21.7	69.2	5.9
Severity Index		DR-Ferr*		1	16	0

FERROGRAPHY		method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*		▲ 3	■ 1	■ 1
Ferrous Sliding	Scale 0-10	ASTM D7684*				
Ferrous Cutting	Scale 0-10	ASTM D7684*				
Ferrous Rolling	Scale 0-10	ASTM D7684*		■ 1		
Ferrous Break-in	Scale 0-10	ASTM D7684*				
Ferrous Spheres	Scale 0-10	ASTM D7684*				
Ferrous Black Oxides	Scale 0-10	ASTM D7684*				
Ferrous Red Oxides	Scale 0-10	ASTM D7684*				
Ferrous Corrosive	Scale 0-10	ASTM D7684*				
Ferrous Other	Scale 0-10	ASTM D7684*				
Nonferrous Rubbing	Scale 0-10	ASTM D7684*				
Nonferrous Sliding	Scale 0-10	ASTM D7684*				
Nonferrous Cutting	Scale 0-10	ASTM D7684*				
Nonferrous Rolling	Scale 0-10	ASTM D7684*				
Nonferrous Other	Scale 0-10	ASTM D7684*				
Carbonaceous Material	Scale 0-10	ASTM D7684*				
Lubricant Degradation	Scale 0-10	ASTM D7684*				
Sand/Dirt	Scale 0-10	ASTM D7684*		■ 1		
Fibres	Scale 0-10	ASTM D7684*				
Spheres	Scale 0-10	ASTM D7684*				
Other	Scale 0-10	ASTM D7684*		■ 1	■ 1	■ 1

WEAR

Wear particle analysis indicates that the ferrous rubbing particles are marginal. All other component wear rates are normal.

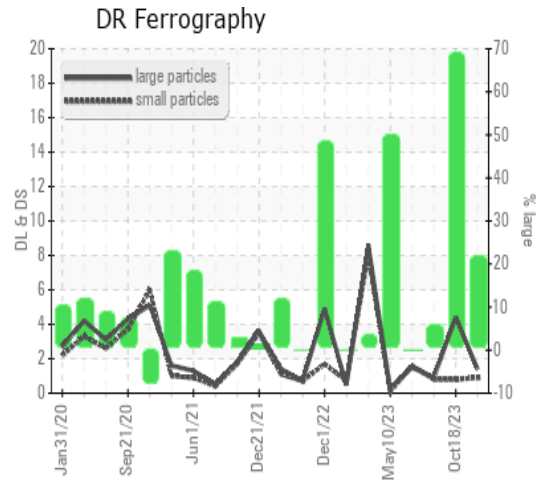

This page left intentionally blank