




# OIL ANALYSIS REPORT

Sample Rating Trend

WEAR PARTICLES

Area  
**(C-FVFN)**  
 Machine Id  
**[C-FVFN] BEEHCRAFT KING AIR B200 PCE-93437**  
 Component  
**Right Jet Turbine**  
 Fluid  
**EASTMAN TURBO OIL 2380 (12 QTS)**

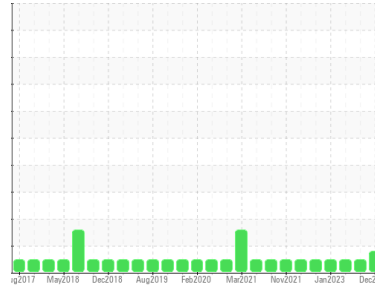

## DIAGNOSIS

### Recommendation

We recommend an early resample to monitor this condition.

### Wear

Wear particle analysis indicates that the ferrous rubbing particles are marginal. All other component wear rates are normal.

### Contaminants

The water content is negligible. There is no indication of any contamination in the oil.

### Oil Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>WC0887236</b>	WC0866221	WC0827493
Sample Date	Client Info		<b>28 Dec 2023</b>	23 Oct 2023	10 Aug 2023
TSN	hrs	Client Info	<b>14130</b>	13944	13540
TSO	hrs	Client Info	<b>5682</b>	5496	5269
Oil Age	hrs	Client Info	<b>404</b>	219	1816
Oil Changed		Client Info	<b>Not Chngd</b>	N/A	Not Chngd
Sample Status			<b>MARGINAL</b>	NORMAL	NORMAL

## WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m) >8	<b>0</b>	0	0
Chromium	ppm	ASTM D5185(m) >2	<b>0</b>	0	0
Nickel	ppm	ASTM D5185(m) >2	<b>&lt;1</b>	0	0
Titanium	ppm	ASTM D5185(m) >2	<b>0</b>	0	0
Silver	ppm	ASTM D5185(m) >2	<b>0</b>	<1	0
Aluminum	ppm	ASTM D5185(m) >2	<b>&lt;1</b>	0	0
Lead	ppm	ASTM D5185(m) >3	<b>&lt;1</b>	0	<1
Copper	ppm	ASTM D5185(m) >3	<b>0</b>	<1	0
Tin	ppm	ASTM D5185(m) >2	<b>0</b>	0	0
Antimony	ppm	ASTM D5185(m)	<b>0</b>	0	0
Vanadium	ppm	ASTM D5185(m)	<b>0</b>	0	0
Beryllium	ppm	ASTM D5185(m)	<b>0</b>	0	0
Cadmium	ppm	ASTM D5185(m)	<b>0</b>	0	0

## ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m) 0	<b>0</b>	<1	<1
Barium	ppm	ASTM D5185(m) 0	<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185(m) 0	<b>0</b>	0	0
Manganese	ppm	ASTM D5185(m)	<b>0</b>	0	0
Magnesium	ppm	ASTM D5185(m) 0	<b>0</b>	0	<1
Calcium	ppm	ASTM D5185(m) 0	<b>0</b>	0	<1
Phosphorus	ppm	ASTM D5185(m) 2500	<b>2609</b>	2729	2870
Zinc	ppm	ASTM D5185(m) 0	<b>&lt;1</b>	<1	2
Sulfur	ppm	ASTM D5185(m) 0	<b>0</b>	48	2
Lithium	ppm	ASTM D5185(m)	<b>&lt;1</b>	<1	<1

## CONTAMINANTS





	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m) >8	<b>2</b>	2	3
Sodium	ppm	ASTM D5185(m)	<b>0</b>	<1	0
Potassium	ppm	ASTM D5185(m) >20	<b>0</b>	0	0
Water	%	ASTM D6304* >0.1	<b>0.018</b>	0.045	0.070
ppm Water	ppm	ASTM D6304* >1000	<b>188</b>	450.9	706.1

## FLUID DEGRADATION

	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974* 0.43	<b>0.31</b>	0.29	0.35




# OIL ANALYSIS REPORT

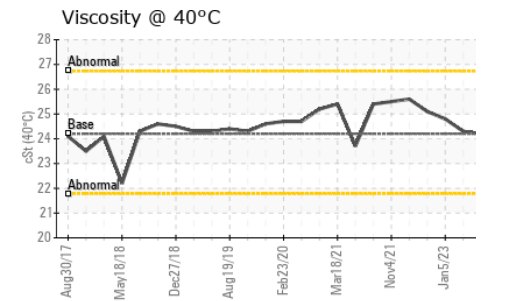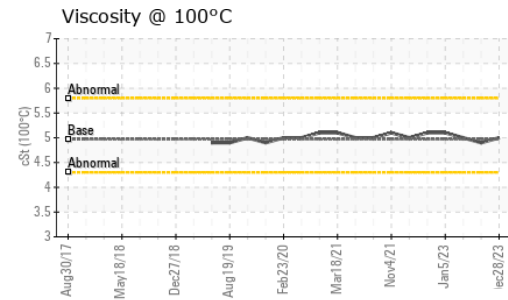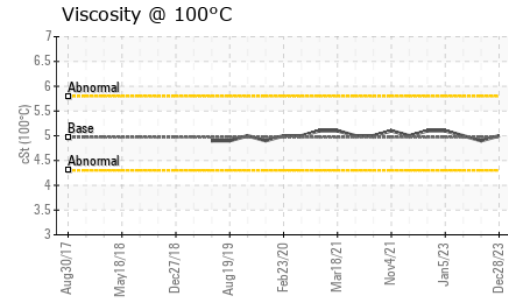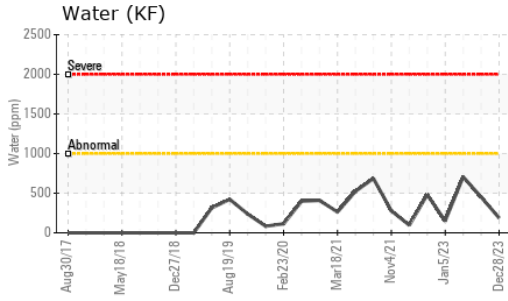





VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE
Precipitate	scalar	Visual*	NONE	NONE	NONE
Silt	scalar	Visual*	NONE	NONE	NONE
Debris	scalar	Visual*	NONE	NONE	NONE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.1	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 40°C	cSt	ASTM D7279(m)	24.2	<b>24.4</b>	24.2	24.3
Visc @ 100°C	cSt	ASTM D7279(m)	4.97	<b>5</b>	4.9	5
Viscosity Index (VI)	Scale	ASTM D2270*	134	<b>134</b>	128	135

## SAMPLE IMAGES

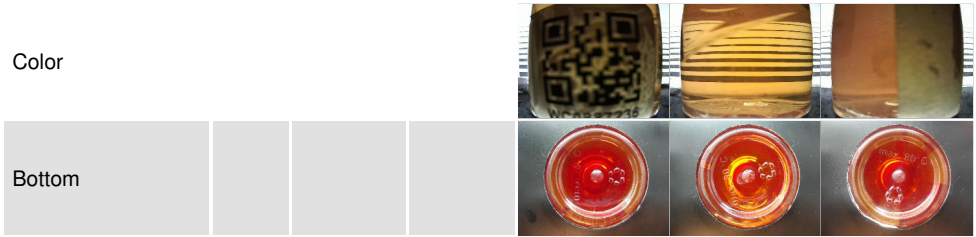

## GRAPHS

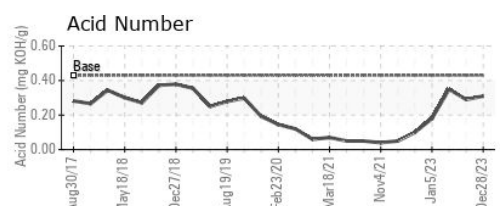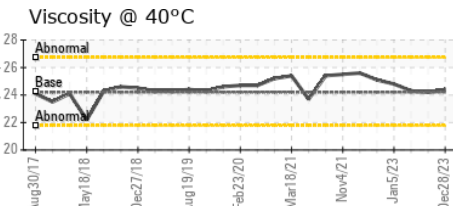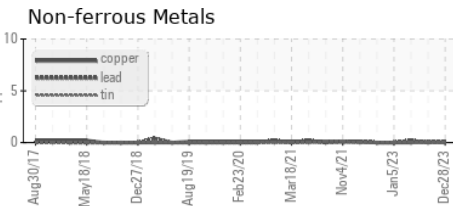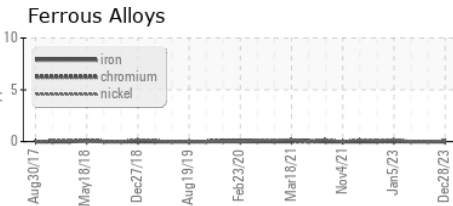

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
 Sample No. : WC0887236  
 Lab Number : **02606545**  
 Unique Number : 5707631  
 Test Package : AVI 3


**FAST AIR LTD**  
 80 HANGAR LINE ROAD  
 WINNIPEG, MB  
 CA R3J 3Y7  
 Contact: Denis Bourgouin  
 denis.bourgouin@flyfastair.com  
 T: (204)772-7622  
 F: (204)783-2483

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.

# FERROGRAPHY REPORT

Area  
**(C-FVFN)**  
 Machine Id  
**[C-FVFN] BEECHCRAFT KING AIR B200 PCE-93437**  
 Component  
**Right Jet Turbine**  
 Fluid  
**EASTMAN TURBO OIL 2380 (12 QTS)**


Magn: 200x Illum: BC

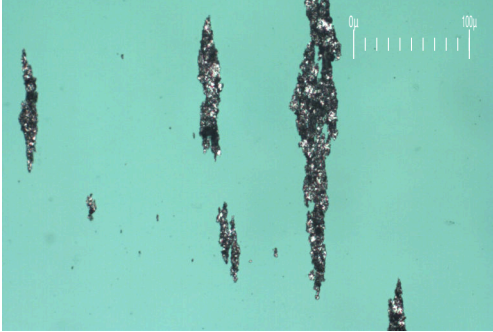

Magn: 50x Illum: RW



Magn: 100x Illum: RW

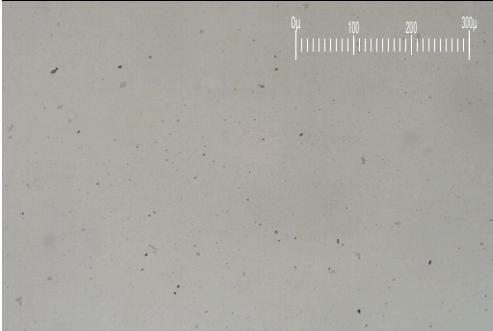


DR-FERROGRAPHY		method	limit/base	current	history1	history2
Large Particles		DR-Ferr*		<b>11.5</b>	1.7	3.4
Small Particles		DR-Ferr*		<b>2.5</b>	0.6	3.4
Total Particles		DR-Ferr*	>---	<b>14</b>	2.3	6.8
Large Particles Percentage	%	DR-Ferr*		<b>64.3</b>	47.8	0
Severity Index		DR-Ferr*		<b>104</b>	2	0

FERROGRAPHY		method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*		▲ <b>3</b>	1	1
Ferrous Sliding	Scale 0-10	ASTM D7684*				
Ferrous Cutting	Scale 0-10	ASTM D7684*				
Ferrous Rolling	Scale 0-10	ASTM D7684*		■ <b>1</b>		
Ferrous Break-in	Scale 0-10	ASTM D7684*				
Ferrous Spheres	Scale 0-10	ASTM D7684*				
Ferrous Black Oxides	Scale 0-10	ASTM D7684*				
Ferrous Red Oxides	Scale 0-10	ASTM D7684*				
Ferrous Corrosive	Scale 0-10	ASTM D7684*				
Ferrous Other	Scale 0-10	ASTM D7684*				
Nonferrous Rubbing	Scale 0-10	ASTM D7684*				
Nonferrous Sliding	Scale 0-10	ASTM D7684*				
Nonferrous Cutting	Scale 0-10	ASTM D7684*				
Nonferrous Rolling	Scale 0-10	ASTM D7684*				
Nonferrous Other	Scale 0-10	ASTM D7684*				
Carbonaceous Material	Scale 0-10	ASTM D7684*				
Lubricant Degradation	Scale 0-10	ASTM D7684*				
Sand/Dirt	Scale 0-10	ASTM D7684*		■ <b>1</b>	1	
Fibres	Scale 0-10	ASTM D7684*				
Spheres	Scale 0-10	ASTM D7684*				
Other	Scale 0-10	ASTM D7684*		■ <b>1</b>	1	1

### WEAR

Wear particle analysis indicates that the ferrous rubbing particles are marginal. All other component wear rates are normal.

DR Ferrography

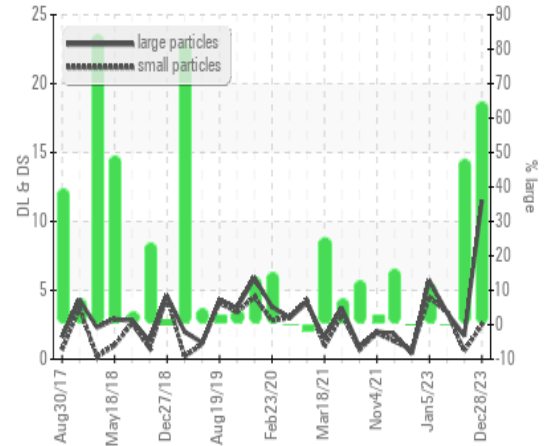

*This page left intentionally blank*