




OIL ANALYSIS REPORT

Sample Rating Trend

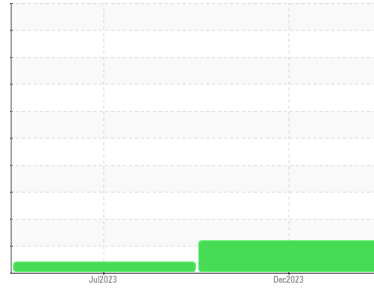

ISO



Area
RONI
 Machine Id
174

Component
Hydraulic System
 Fluid

PETRO CANADA HYDREX AW 46 (--- GAL)

DIAGNOSIS

▲ Recommendation

The filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

▲ Contamination

There is a moderate amount of silt (particulates < 14 microns in size) present in the oil.

Fluid Condition

The AN level is acceptable for this fluid. The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	WC0872988	LH0270774	---
Sample Date	Client Info	06 Dec 2023	14 Jul 2023	---
Machine Age	hrs	Client Info	0	5594
Oil Age	hrs	Client Info	0	0
Oil Changed	Client Info	Changed	Changed	---
Sample Status		ABNORMAL	ABNORMAL	---

CONTAMINATION

method	limit/base	current	history1	history2
Water	WC Method	>0.1	NEG	NEG

WEAR METALS

method	limit/base	current	history1	history2		
Iron	ppm	ASTM D5185(m)	>20	10	9	---
Chromium	ppm	ASTM D5185(m)	>10	<1	<1	---
Nickel	ppm	ASTM D5185(m)	>10	0	0	---
Titanium	ppm	ASTM D5185(m)		0	0	---
Silver	ppm	ASTM D5185(m)		0	0	---
Aluminum	ppm	ASTM D5185(m)	>10	2	1	---
Lead	ppm	ASTM D5185(m)	>10	<1	0	---
Copper	ppm	ASTM D5185(m)	>75	4	4	---
Tin	ppm	ASTM D5185(m)	>10	0	0	---
Antimony	ppm	ASTM D5185(m)		0	0	---
Vanadium	ppm	ASTM D5185(m)		0	0	---
Beryllium	ppm	ASTM D5185(m)		0	0	---
Cadmium	ppm	ASTM D5185(m)		0	<1	---

ADDITIVES

method	limit/base	current	history1	history2		
Boron	ppm	ASTM D5185(m)	0	1	2	---
Barium	ppm	ASTM D5185(m)	0	0	0	---
Molybdenum	ppm	ASTM D5185(m)	0	0	0	---
Manganese	ppm	ASTM D5185(m)	0	0	0	---
Magnesium	ppm	ASTM D5185(m)	0	1	2	---
Calcium	ppm	ASTM D5185(m)	50	128	123	---
Phosphorus	ppm	ASTM D5185(m)	330	456	494	---
Zinc	ppm	ASTM D5185(m)	430	568	570	---
Sulfur	ppm	ASTM D5185(m)	760	1388	1339	---
Lithium	ppm	ASTM D5185(m)		<1	<1	---

CONTAMINANTS

method	limit/base	current	history1	history2		
Silicon	ppm	ASTM D5185(m)	>20	4	4	---
Sodium	ppm	ASTM D5185(m)		3	3	---
Potassium	ppm	ASTM D5185(m)	>20	<1	1	---


FLUID CLEANLINESS

method	limit/base	current	history1	history2	
Particles >4µm	ASTM D7647	>5000	▲ 27051	2128	---
Particles >6µm	ASTM D7647	>1300	▲ 2903	459	---
Particles >14µm	ASTM D7647	>160	22	42	---
Particles >21µm	ASTM D7647	>40	3	8	---
Particles >38µm	ASTM D7647	>10	0	0	---
Particles >71µm	ASTM D7647	>3	0	0	---
Oil Cleanliness	ISO 4406 (c)	>19/17/14	▲ 22/19/12	18/16/13	---




OIL ANALYSIS REPORT


Particle Trend

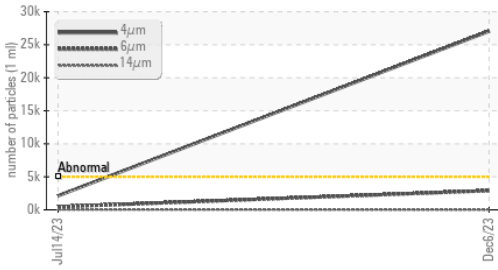


Particle Trend

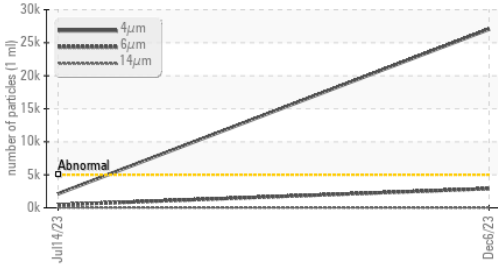

Acid Number

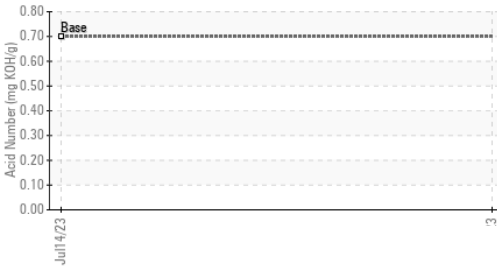

Viscosity @ 40°C

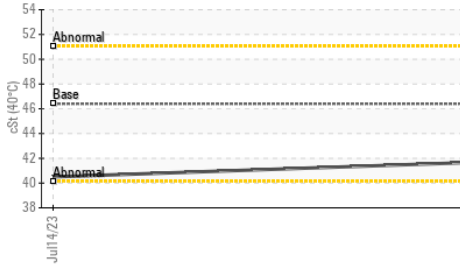



FLUID DEGRADATION

method	limit/base	current	history1	history2		
Acid Number (AN) mg KOH/g	ASTM D974*	0.70	0.49	---	---	
VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	NONE	---
Yellow Metal	scalar	Visual*	NONE	NONE	NONE	---
Precipitate	scalar	Visual*	NONE	NONE	NONE	---
Silt	scalar	Visual*	NONE	NONE	NONE	---
Debris	scalar	Visual*	NONE	NONE	VLITE	---
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE	---
Appearance	scalar	Visual*	NORML	NORML	NORML	---
Odor	scalar	Visual*	NORML	NORML	NORML	---
Emulsified Water	scalar	Visual*	>0.1	NEG	NEG	---
Free Water	scalar	Visual*		NEG	NEG	---

FLUID PROPERTIES


method	limit/base	current	history1	history2	
Visc @ 40°C cSt	ASTM D7279(m)	46.4	41.7	▲ 40.5	---

SAMPLE IMAGES

method	limit/base	current	history1	history2	
Color					 no image
Bottom					 no image

GRAPHS


Ferrous Alloys

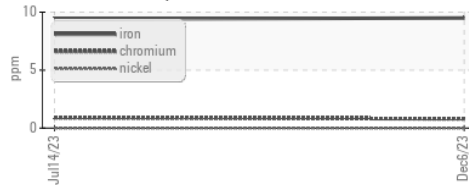


Non-ferrous Metals



Viscosity @ 40°C

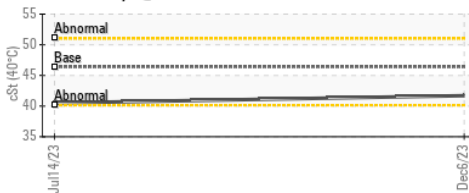

Particle Count

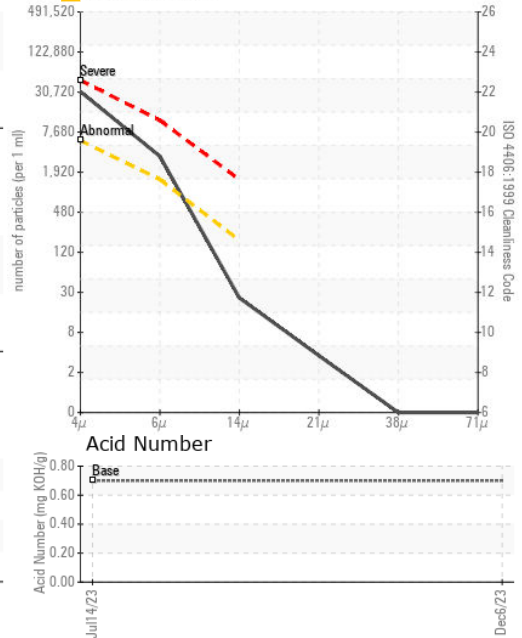

ISO 17025:2017
Accredited
Laboratory

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 **RONI/IRON SHORE EXCAVATING LTD.**
Sample No. : WC0872988 **Received** : 08 Jan 2024
Lab Number : 02607161 **Diagnosed** : 11 Jan 2024
Unique Number : 5708247 **Diagnostician** : Wes Davis
Test Package : MOBCE

To discuss this sample report, contact Customer Service at 1-800-268-2131.

Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.

Validity of results and interpretation are based on the sample and information as supplied.

100 MACINTOSH BLVD
VAUGHAN, ON
CA L4K 4P3
Contact: Service Team
service.team@roni.ca

T:
F: