




# OIL ANALYSIS REPORT

Sample Rating Trend

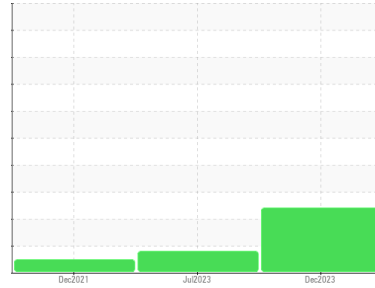

**WEAR PARTICLES**



Machine Id  
**IMM A1 SCREW DRIVE**

Component  
**Gearbox**

Fluid  
**CHEVRON CLARITY HYDRAULIC AW 46 (--- GAL)**

**DIAGNOSIS**

**Recommendation**

The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.

**Wear**

Wear particle analysis indicates that the ferrous rolling and ferrous rubbing particles are abnormal.

**Contaminants**

There is no indication of any contamination in the oil.

**Oil Condition**

The AN level is acceptable for this fluid. The oil is no longer serviceable as a result of the abnormal and/or severe wear.

**SAMPLE INFORMATION**

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>CB0031711</b>	CB0031433	CB0030602
Sample Date	Client Info		<b>27 Dec 2023</b>	20 Jul 2023	28 Dec 2021
Machine Age	hrs	Client Info	<b>0</b>	0	0
Oil Age	hrs	Client Info	<b>0</b>	0	0
Oil Changed	Client Info		<b>Changed</b>	Changed	Changed
Sample Status			<b>ABNORMAL</b>	ABNORMAL	NORMAL

**CONTAMINATION**

	method	limit/base	current	history1	history2
Water	WC Method	>0.2	<b>NEG</b>	NEG	NEG

**WEAR METALS**

	method	limit/base	current	history1	history2
PQ	ASTM D8184*		<b>18</b>	14	0
Iron	ppm	ASTM D5185(m) >200	<b>80</b>	98	24
Chromium	ppm	ASTM D5185(m) >15	<b>&lt;1</b>	<1	<1
Nickel	ppm	ASTM D5185(m) >15	<b>0</b>	0	<1
Titanium	ppm	ASTM D5185(m)	<b>0</b>	0	0
Silver	ppm	ASTM D5185(m)	<b>0</b>	0	0
Aluminum	ppm	ASTM D5185(m) >25	<b>&lt;1</b>	<1	0
Lead	ppm	ASTM D5185(m) >100	<b>&lt;1</b>	0	0
Copper	ppm	ASTM D5185(m) >200	<b>&lt;1</b>	1	1
Tin	ppm	ASTM D5185(m) >25	<b>0</b>	0	0
Antimony	ppm	ASTM D5185(m) >5	<b>0</b>	0	0
Vanadium	ppm	ASTM D5185(m)	<b>0</b>	0	0
Beryllium	ppm	ASTM D5185(m)	<b>0</b>	0	0
Cadmium	ppm	ASTM D5185(m)	<b>0</b>	0	0

**ADDITIVES**

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)	<b>&lt;1</b>	<1	<1
Barium	ppm	ASTM D5185(m)	<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185(m)	<b>0</b>	0	0
Manganese	ppm	ASTM D5185(m)	<b>0</b>	<1	<1
Magnesium	ppm	ASTM D5185(m)	<b>&lt;1</b>	<1	<1
Calcium	ppm	ASTM D5185(m)	<b>4</b>	12	2
Phosphorus	ppm	ASTM D5185(m)	<b>313</b>	274	287
Zinc	ppm	ASTM D5185(m)	<b>8</b>	6	5
Sulfur	ppm	ASTM D5185(m)	<b>441</b>	396	245
Lithium	ppm	ASTM D5185(m)	<b>&lt;1</b>	<1	<1




**CONTAMINANTS**

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m) >50	<b>8</b>	8	8
Sodium	ppm	ASTM D5185(m)	<b>0</b>	<1	0
Potassium	ppm	ASTM D5185(m) >20	<b>&lt;1</b>	<1	<1

**FLUID DEGRADATION**

	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974*	<b>0.21</b>	0.24	0.27


# OIL ANALYSIS REPORT

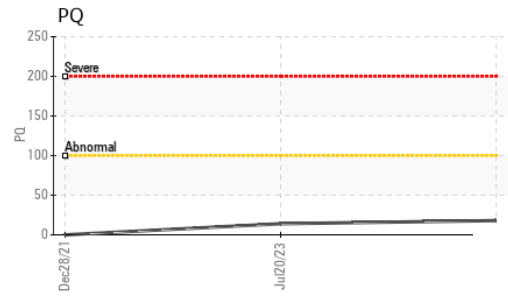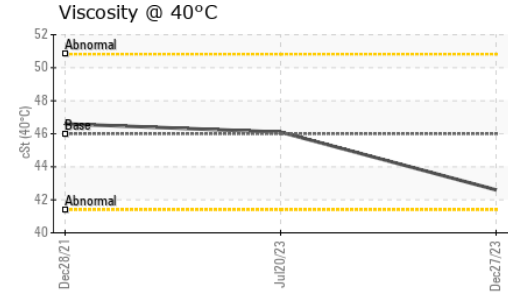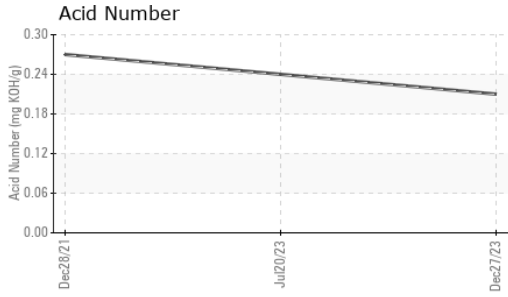






VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	VLITE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE
Precipitate	scalar	Visual*	NONE	NONE	NONE
Silt	scalar	Visual*	NONE	NONE	NONE
Debris	scalar	Visual*	NONE	NONE	NONE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	46.0	42.6	46.1

SAMPLE IMAGES	method	limit/base	current	history1	history2
---------------	--------	------------	---------	----------	----------

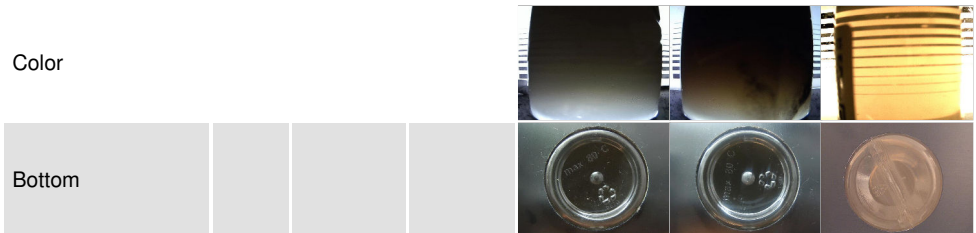

## GRAPHS

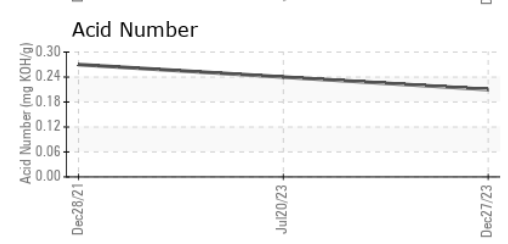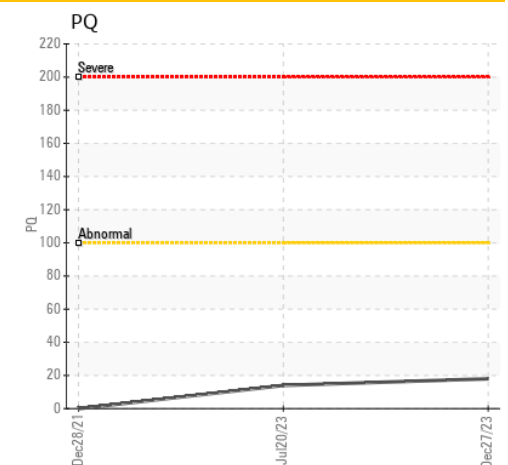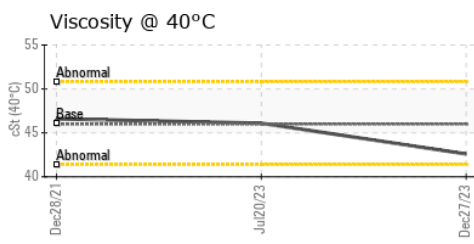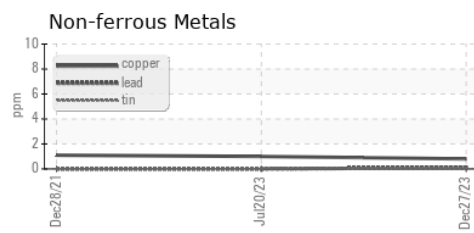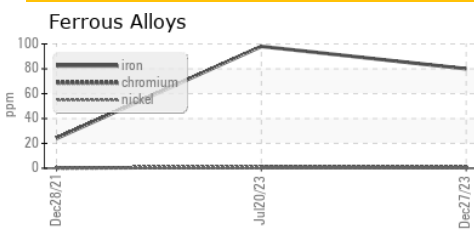




**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : CB0031711 **Received** : 10 Jan 2024  
**Lab Number** : 02607992 **Diagnosed** : 17 Jan 2024  
**Unique Number** : 5709078 **Diagnostician** : Kevin Marson  
**Test Package** : IND 3

**TOYOTA MOTOR MANUFACT.**  
 1055 FOUNTAIN STREET N.  
 CAMBRIDGE, ON  
 CA N3H 5K2  
 Contact: mike clappison  
 mike.clappison@toyota.com  
 T: (519)212-5023  
 F: (519)653-9638

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.

# FERROGRAPHY REPORT

Machine Id  
**IMM A1 SCREW DRIVE**  
Component  
**Gearbox**  
Fluid  
**CHEVRON CLARITY HYDRAULIC AW 46 (--- GAL)**

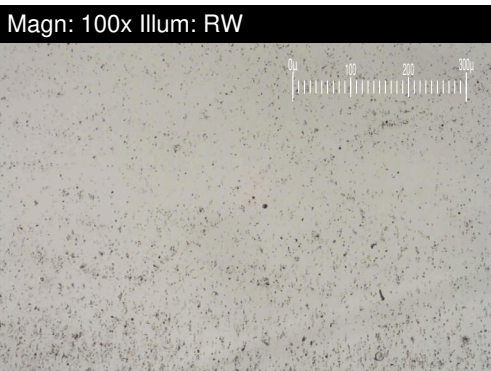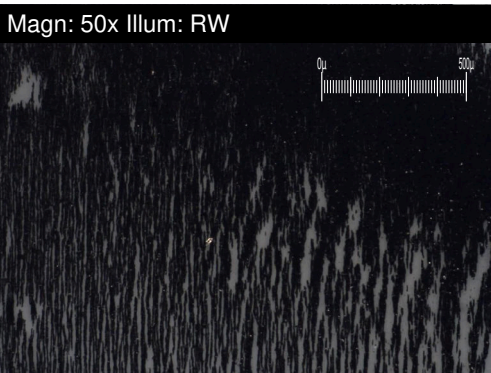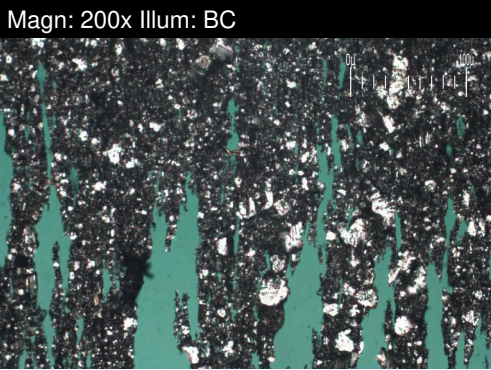


DR-FERROGRAPHY		method	limit/base	current	history1	history2
Large Particles		DR-Ferr*		<b>153.7</b>	61.0	95.0
Small Particles		DR-Ferr*		<b>131.5</b>	24.4	49.2
Total Particles		DR-Ferr*	>---	<b>285.2</b>	85.4	144.2
Large Particles Percentage	%	DR-Ferr*		<b>7.8</b>	42.9	31.8
Severity Index		DR-Ferr*		<b>3412</b>	2233	4351

FERROGRAPHY		method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*		▲ <b>8</b>	▲ 8	■ 4
Ferrous Sliding	Scale 0-10	ASTM D7684*				
Ferrous Cutting	Scale 0-10	ASTM D7684*				
Ferrous Rolling	Scale 0-10	ASTM D7684*		▲ <b>5</b>	■ 4	■ 2
Ferrous Break-in	Scale 0-10	ASTM D7684*				
Ferrous Spheres	Scale 0-10	ASTM D7684*				
Ferrous Black Oxides	Scale 0-10	ASTM D7684*				
Ferrous Red Oxides	Scale 0-10	ASTM D7684*				
Ferrous Corrosive	Scale 0-10	ASTM D7684*		■ <b>1</b>	■ 2	■ 2
Ferrous Other	Scale 0-10	ASTM D7684*				
Nonferrous Rubbing	Scale 0-10	ASTM D7684*				
Nonferrous Sliding	Scale 0-10	ASTM D7684*				
Nonferrous Cutting	Scale 0-10	ASTM D7684*				
Nonferrous Rolling	Scale 0-10	ASTM D7684*				
Nonferrous Other	Scale 0-10	ASTM D7684*				
Carbonaceous Material	Scale 0-10	ASTM D7684*				
Lubricant Degradation	Scale 0-10	ASTM D7684*			■ 1	
Sand/Dirt	Scale 0-10	ASTM D7684*		■ <b>1</b>	■ 1	■ 1
Fibres	Scale 0-10	ASTM D7684*				
Spheres	Scale 0-10	ASTM D7684*				
Other	Scale 0-10	ASTM D7684*		■ <b>1</b>	■ 2	■ 2

## WEAR

Wear particle analysis indicates that the ferrous rolling and ferrous rubbing particles are abnormal.

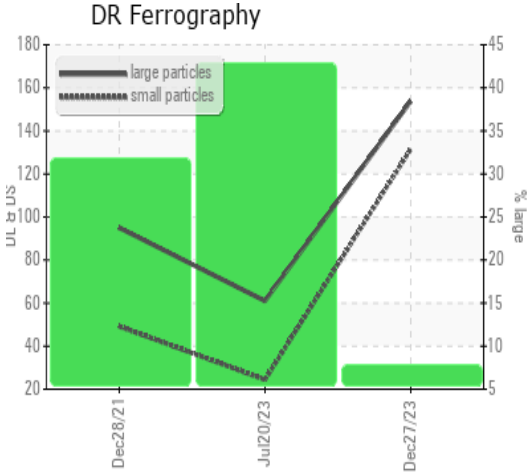

*This page left intentionally blank*