


# **PROBLEM SUMMARY**


## Area BRUCE B/8/43230 Machine Id 8-43230-P4-P IB Brg Drn Component

Inboard Bearing Fluid ESSO NUTO H ISO 46 (--- GAL)

# COMPONENT CONDITION SUMMARY

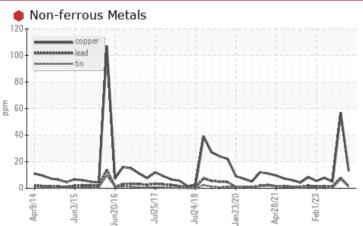



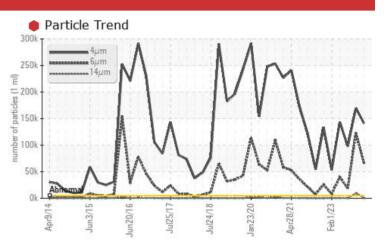

# RECOMMENDATION

Check seals and/or filters for points of contaminant entry. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. We recommend you service the filters on this component. Resample in 30-45 days to monitor this situation. No other corrective action is recommended at this time. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.

PROBLEMATIC TEST RESULTS									
Sample Status				SEVERE	SEVERE	SEVERE			
Copper	ppm	ASTM D5185(m)	>5	🛑 13	<b>6</b> 57	5			
Ferrous Cutting	Scale 0-10	ASTM D7684*		<b></b>	<b></b> 1	<b>1</b>			
Particles >4µm		ASTM D7647	>5000	<b>e</b> 141054	169532	97733			
Particles >6µm		ASTM D7647	>1300	66351	123574	18240			
Particles >14µm		ASTM D7647	>320	<u> </u>	9288	279			
Oil Cleanliness		ISO 4406 (c)	>19/17/15	<b>e</b> 24/23/17	• 25/24/20	• 24/21/15			
PrtFilter					no image	no image			

Customer Id: BRUTIV Sample No.: WC0845406 Lab Number: 02609392 Test Package: IND 2



To manage this report scan the QR code

*To discuss the diagnosis or test data:* Kevin Marson +1 (289)291-4644 x4644 Kevin.Marson@wearcheck.com

To change component or sample information: Gloria Gonzalez +1 (289)291-4643 x4643 gloria.gonzalez@wearcheck.com

## **RECOMMENDED ACTIONS**

Action	Status	Date	Done By	Description
Change Filter			?	We recommend you service the filters on this component.
Resample			?	Resample in 30-45 days to monitor this situation.
Information Required			?	NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.
Check Breathers			?	The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather.
Check Seals			?	Check seals and/or filters for points of contaminant entry.

#### HISTORICAL DIAGNOSIS

#### 06 Dec 2023 Diag: Kevin Marson



We advise that you check all areas where contaminants can enter the system. We advise that you perform a compression test. We recommend either performing an oil change or oil filtration. We cannot recommend specific action as we have limited information with regards to reservoir capacity and/or lubricant type. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. Resample in 30-45 days to monitor this situation. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.Copper pm levels are severe. Lead, tin and chromium ppm levels are abnormal. Wear particle analysis indicates that the ferrous cutting and ferrous sliding particles are marginal. Bearing wear is indicated. Cutting wear particles are caused by either hard protuberances (mis-aligned components, etc.), or abrasives entering the system and embedding themselves in softer materials (sand, etc.), and gouging out mating surfaces. Sliding wear particles are caused from metal on metal contact, and may be the result of high loads, speeds, or temperature, insufficient lubrication, or lack of anti-wear or extreme pressure additives. There is a high amount of particulates (2 to 100 microns in size) present in the oil. Elemental level of silicon (Si) above normal indicating ingress of seal material. The water content is negligible. The system cleanliness code is much higher than the acceptable limit for the target ISO 4406 cleanliness code. The AN level is acceptable for this fluid. The oil is no longer serviceable as a result of the abnormal and/or severe wear.




view report

**₩₩** 

#### 20 Jul 2023 Diag: Kevin Marson



Check seals and/or filters for points of contaminant entry. We advise that you check all areas where dirt can enter the system. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. We advise that you perform a filter service, and use off-line filtration to improve the cleanliness of the system fluid. Resample in 30-45 days to monitor this situation. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample. Wear particle analysis indicates that the ferrous cutting particles are marginal. All other component wear rates are normal. Cutting wear particles are caused by either hard protuberances (mis-aligned components, etc.), or abrasives entering the system and embedding themselves in softer materials (sand, etc.), and gouging out mating surfaces. There is a high amount of silt (particulates < 14 microns in size) present in the oil. Elemental level of silicon (Si) above normal indicating ingress of seal material. The water content is negligible. The system cleanliness code is much higher than the acceptable limit for the target ISO 4406 cleanliness code. The AN level is acceptable for this fluid. The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.





Check seals and/or filters for points of contaminant entry. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. We recommend you service the filters on this component. Resample in 30-45 days to monitor this situation. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample. Copper ppm levels are abnormal. Wear particle analysis indicates that the ferrous cutting particles are marginal. All other component wear rates are normal. Cutting wear particles are caused by either hard protuberances (mis-aligned components, etc.), or abrasives entering the system and embeding themselves in softer materials (sand, etc.), and gouging out mating surfaces. Particles >6µm are severely high. Oil Cleanliness are severely high. Particles <4µm are severely high. Silicon ppm levels are abnormally high. Particles >14µm are notably high. Elemental level of silicon (Si) above normal indicating ingress of seal material. The system cleanliness code is much higher than the acceptable limit for the target ISO 4406 cleanliness code. The AN level is acceptable for this fluid. The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.





# **OIL ANALYSIS REPORT**

#### Area BRUCE B/8/43230 Machine Id 8-43230-P4-P IB Brg Drn Component

Inboard Bearing Fluid ESSO NUTO H ISO 46 (--- GAL)

# DIAGNOSIS

# Recommendation

Check seals and/or filters for points of contaminant entry. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. We recommend you service the filters on this component. Resample in 30-45 days to monitor this situation. No other corrective action is recommended at this time. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.

### 🏓 Wear

Copper ppm levels are severe. Wear particle analysis indicates that the ferrous cutting particles are marginal. Bearing wear is indicated. Cutting wear particles are caused by either hard protuberances (mis-aligned components, etc.), or abrasives entering the system and embedding themselves in softer materials (sand, etc.), and gouging out mating surfaces.

# Contaminants

There is a high amount of silt (particulates < 14 microns in size) present in the oil. The water content is negligible. The system cleanliness code is much higher than the acceptable limit for the target ISO 4406 cleanliness code.

# **Oil Condition**

The AN level is acceptable for this fluid. The oil is no longer serviceable as a result of the abnormal and/or severe wear.



Particle Filter (Magn: 200 x)



Report Id: BRUTIV [WCAMIS] 02609392 (Generated: 01/23/2024 11:57:08) Rev: 1



SAMPLE INFOR	MATION	method	limit/base	current	history1	history2
Sample Number		Client Info		WC0845406	WC0744593	WC0744561
Sample Date		Client Info		08 Jan 2024	06 Dec 2023	20 Jul 2023
Machine Age	kms	Client Info		0	0	0
Oil Age	kms	Client Info		0	0	0
Oil Changed		Client Info		N/A	N/A	N/A
Sample Status				SEVERE	SEVERE	SEVERE
WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>10	<1	2	0
Chromium	ppm	ASTM D5185(m)	>5	<1	<u> </u>	0
Nickel	ppm	ASTM D5185(m)	>5	0	<1	0
Titanium	ppm	ASTM D5185(m)	>5	0	0	0
Silver	ppm	ASTM D5185(m)		0	<1	0
Aluminum	ppm	ASTM D5185(m)	>5	<1	<1	<1
Lead	ppm	ASTM D5185(m)	>5	1	▲ 8	1
Copper	ppm	ASTM D5185(m)	>5	🛑 13	57	5
Tin	ppm	ASTM D5185(m)	>5	1	<b></b> 7	<1
Antimony	ppm	ASTM D5185(m)		0	0	0
Vanadium	ppm	ASTM D5185(m)		0	0	0
Beryllium	ppm	ASTM D5185(m)		0	0	0
Cadmium	ppm	ASTM D5185(m)		0	0	0
ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)	0	0	<1	0
Barium	ppm	ASTM D5185(m)	0	0	<1	0
Molybdenum	ppm	ASTM D5185(m)	0	0	0	0
Manganese	ppm	ASTM D5185(m)		0	0	0
Magnesium	ppm	ASTM D5185(m)	5	<1	0	<1
Calcium	ppm	ASTM D5185(m)	50	53	53	54
Phosphorus	ppm	ASTM D5185(m)	330	377	348	383
Zinc	ppm	ASTM D5185(m)	410	429	444	455
Sulfur	ppm	ASTM D5185(m)	2700	6108	5776	5634
Lithium	ppm	ASTM D5185(m)		<1	<1	<1
CONTAMINANTS	S	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	>5	<1	<b>1</b> 7	<b></b> 7
Sodium	ppm	ASTM D5185(m)	>5	0	<1	0
Potassium	ppm	ASTM D5185(m)	>20	0	0	<1
Water	%	ASTM D6304*	>0.005	0.002	0.002	0.00
ppm Water	ppm	ASTM D6304*	>50	19	18	0.00
FLUID CLEANLI	NESS	method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>5000	🛑 141054	169532	97733
Particles >6µm		ASTM D7647	>1300	66351	123574	18240
Particles >14µm		ASTM D7647	>320	<u> </u>	9288	279
Particles >21µm		ASTM D7647	>80	52	<b>4</b> 13	33
Particles >38µm		ASTM D7647	>20	1	3	3
Particles >71µm		ASTM D7647	>4	0	0	2
Oil Cleanliness		ISO 4406 (c)	>19/17/15	<b>2</b> 4/23/17	• 25/24/20	• 24/21/15

Sample Rating Trend

Contact/Location: Pierre Adouki - BRUTIV Page 3 of 6



Acid Number

Severe Abnormal

8

1.40

# **OIL ANALYSIS REPORT**


Particle Count	FLU
122,880 Severe -24	Acid N
30,720 -22 (\$0 +00: 1999)   7,680 Abnormal   1,920 -18 (\$90 Geam]   16 120 (\$0 + 10)   12 -14 (\$0 + 10)   120 -14 (\$0 + 10)   120 -14 (\$0 + 10)   120 -14 (\$0 + 10)   10 -10 (\$0 + 10)	VIC
1,920 1,920 1,820 1,820 1,820 1,820 1,820 1,820 1,820 1,820 1,820 1,820 1,820 1,6 1,6 1,6 1,12	VIS
16 Q	White
114 min	Yellov
-12 25 C	Precip
	Silt
$0 + \frac{1}{4\mu} + \frac{1}{6\mu} + \frac{1}{14\mu} + \frac{1}{24\mu} + \frac{1}{38\mu} + \frac{1}{74\mu} + \frac{1}{6\mu} + \frac$	Debris
	Sand/
Particle Trend	Appea
= 250k - 4µm	Odor
ε 200k	Emuls
	Free \
E 250k B 200k 1 500k 1 50k 1 4μm 1 4μm 1 4μm	FLU
OK ATTACK	Visc @
Apr9/14 Jun3/15 Jun20/16 - Jul25/17 Jan23/20 Apr28/21 Feb1/23	SAN
0.0 00 <b>0.0</b> 0.0 00.00 0.000	
Non-ferrous Metals 120 T	Color
100 copper	
non tip	
80	
<u>ة</u> ۵۰	Bottor
40 N	
Apr9/14 Jun3/15 Jun20/16 Jul25/17 Jul24/18 Jan23/20 Apr28/21 Feb1/23	PrtFilt

FLUID DEGRADA	TION	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974*	0.45	0.43	0.44	0.37
VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	NONE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE	NONE
Precipitate	scalar	Visual*	NONE	NONE	NONE	NONE
Silt	scalar	Visual*	NONE	NONE	NONE	NONE
Debris	scalar	Visual*	NONE	NONE	NONE	VLITE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.005	NEG	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG	NEG
FLUID PROPERT	IES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	46	43.5	43.0	44.4
SAMPLE IMAGES		method	limit/base	current	history1	history2

# m



PrtFilter

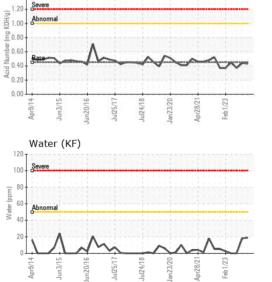


7							
EI: MARKES	🔿 CALA	Laboratory	: WearCheck - Ca	8-1175 Appleby Lin	e, Burlington, ON L7L 5	iH9 Bruc	e Power - Bruce A PdM
	Acreditation No. 1005019	Sample No.	: WC0845406	Recieved	: 17 Jan 2024	P.O.Box 1540, 177 Tie	e Road,, RM-222 U2 Column 2N11 615`
	ISO 17025:2017	Lab Number	: 02609392	Diagnosed	: 23 Jan 2024		Tiverton, ON
	Accredited	Unique Number	: 5710478	Diagnostician	: Kevin Marson		CA N0G 2T0
	Laboratory	Test Package	: IND 2 ( Additional T	Tests: A-FERR, Bottom	Analysis, DR-FERR, FILTE	RPATCH, PrtFilter)	Contact: Pierre Adouki
	To discuss this	s sample report, c	contact Customer S	Service at 1-800-26	8-2131.	pierre.a	douki@brucepower.com
「「見を思えな」	Test denoted (	*) outside scope	of accreditation, (n	n) method modified,	(e) tested at external l	ab.	T: (519)361-2673
	Validity of resu	ilts and interpreta	tion are based on	the sample and info	ormation as supplied.		F:



# FERROGRAPHY REPORT


## Area BRUCE B/8/43230 Machine Id 8-43230-P4-P IB Brg Drn Component

Inboard Bearing Fluid ESSO NUTO H ISO 46 (--- GAL)






Magn: 100x Illum: RW

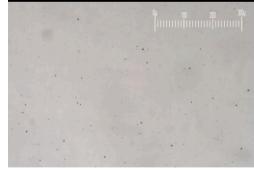

DR-FERROGRAP	ΡΗΥ	method	limit/base	current	history1	history2
Large Particles		DR-Ferr*		9.6	25.0	2.5
Small Particles		DR-Ferr*		2.8	10.3	1.4
Total Particles		DR-Ferr*	>	12.4	35.3	3.9
Large Particles Percentage	%	DR-Ferr*		54.8	41.6	28.2
Severity Index	,0	DR-Ferr*		65	368	3
,						
FERROGRAPHY		method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*		3	4	2
Ferrous Sliding	Scale 0-10	ASTM D7684*			1	
Ferrous Cutting	Scale 0-10	ASTM D7684*		<b>_</b> 1	<b>A</b> 1	<b>A</b> 1
Ferrous Rolling	Scale 0-10	ASTM D7684*		1	1	1
Ferrous Break-in	Scale 0-10	ASTM D7684*				
Ferrous Spheres	Scale 0-10	ASTM D7684*				
Ferrous Black Oxides	Scale 0-10	ASTM D7684*		1		
Ferrous Red Oxides	Scale 0-10	ASTM D7684*				
Ferrous Corrosive	Scale 0-10	ASTM D7684*			1	
Ferrous Other	Scale 0-10	ASTM D7684*				
Nonferrous Rubbing	Scale 0-10	ASTM D7684*				
Nonferrous Sliding	Scale 0-10	ASTM D7684*				
Nonferrous Cutting	Scale 0-10	ASTM D7684*				
Nonferrous Rolling	Scale 0-10	ASTM D7684*				
Nonferrous Other	Scale 0-10	ASTM D7684*				
Carbonaceous Material	Scale 0-10	ASTM D7684*				
Lubricant Degradation	Scale 0-10	ASTM D7684*				
Sand/Dirt	Scale 0-10	ASTM D7684*		1	1	1
Fibres	Scale 0-10	ASTM D7684*				
Spheres	Scale 0-10	ASTM D7684*				
Other	Scale 0-10	ASTM D7684*		1	2	1

# WEAR

Copper ppm levels are severe. Wear particle analysis indicates that the ferrous cutting particles are marginal. Bearing wear is indicated. Cutting wear particles are caused by either hard protuberances (mis-aligned components, etc.), or abrasives entering the system and embedding themselves in softer materials (sand, etc.), and gouging out mating surfaces.

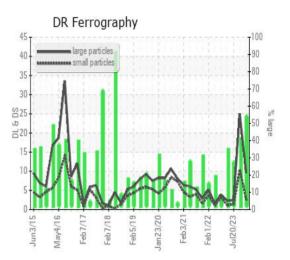

This page left intentionally blank