




# OIL ANALYSIS REPORT

Sample Rating Trend

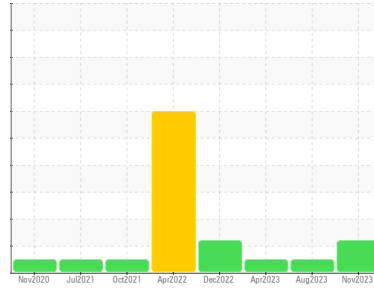

FUEL



Machine Id

**7377**

Component

**Diesel Engine**

Fluid

**DIESEL ENGINE OIL SAE 15W40 (--- GAL)**

## DIAGNOSIS

### Recommendation

No corrective action is recommended at this time. Resample at the next service interval to monitor.

### Wear

All component wear rates are normal.

### Contamination

Light fuel dilution occurring. No other contaminants were detected in the oil.

### Fluid Condition

The condition of the oil is acceptable for the time in service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>WC0853097</b>	WC0796666	WC0796357
Sample Date	Client Info		<b>01 Nov 2023</b>	02 Aug 2023	15 Apr 2023
Machine Age	kms	Client Info	<b>182223</b>	171723	155957
Oil Age	kms	Client Info	<b>0</b>	0	0
Oil Changed	Client Info		<b>Not Changed</b>	Changed	Changed
Sample Status			<b>ABNORMAL</b>	NORMAL	NORMAL

## CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.2	<b>NEG</b>	NEG	NEG
Glycol	WC Method		<b>NEG</b>	NEG	NEG

## WEAR METALS

	method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185(m)	>90	<b>11</b>	15	19
Chromium	ppm	ASTM D5185(m)	>20	<b>&lt;1</b>	<1	<1
Nickel	ppm	ASTM D5185(m)	>2	<b>&lt;1</b>	<1	<1
Titanium	ppm	ASTM D5185(m)	>2	<b>0</b>	0	<1
Silver	ppm	ASTM D5185(m)	>2	<b>&lt;1</b>	<1	0
Aluminum	ppm	ASTM D5185(m)	>20	<b>4</b>	7	15
Lead	ppm	ASTM D5185(m)	>40	<b>0</b>	0	0
Copper	ppm	ASTM D5185(m)	>330	<b>2</b>	2	2
Tin	ppm	ASTM D5185(m)	>15	<b>0</b>	0	<1
Antimony	ppm	ASTM D5185(m)		<b>0</b>	0	0
Vanadium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Beryllium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Cadmium	ppm	ASTM D5185(m)		<b>0</b>	0	0

## ADDITIVES

	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185(m)	250	<b>53</b>	49	49
Barium	ppm	ASTM D5185(m)	10	<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185(m)	100	<b>&lt;1</b>	1	2
Manganese	ppm	ASTM D5185(m)		<b>0</b>	<1	<1
Magnesium	ppm	ASTM D5185(m)	450	<b>710</b>	709	693
Calcium	ppm	ASTM D5185(m)	3000	<b>1308</b>	1306	1330
Phosphorus	ppm	ASTM D5185(m)	1150	<b>691</b>	694	695
Zinc	ppm	ASTM D5185(m)	1350	<b>756</b>	751	734
Sulfur	ppm	ASTM D5185(m)	4250	<b>2629</b>	2490	2515
Lithium	ppm	ASTM D5185(m)		<b>&lt;1</b>	<1	<1

## CONTAMINANTS

	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185(m)	>25	<b>5</b>	6	6
Sodium	ppm	ASTM D5185(m)	>158	<b>2</b>	3	3
Potassium	ppm	ASTM D5185(m)	>20	<b>4</b>	12	25
Fuel	%	ASTM D7593*	>3.0	<b>▲ 2</b>	<1.0	<1.0


## INFRA-RED

	method	limit/base	current	history1	history2	
Soot %	%	ASTM D7844*	>6	<b>0.3</b>	0.4	0.4
Nitration	Abs/cm	ASTM D7624*	>20	<b>9.5</b>	10.1	10.5
Sulfation	Abs/.1mm	ASTM D7415*	>30	<b>20.0</b>	21.5	20.8




# OIL ANALYSIS REPORT

▲ Viscosity @ 100°C

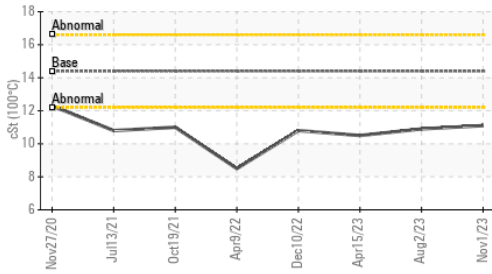

▲ Fuel Dilution

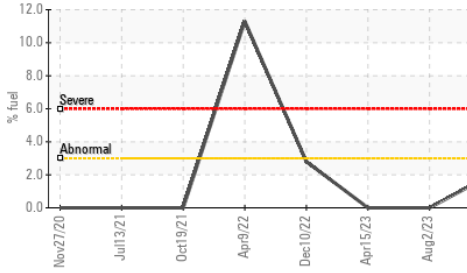


FLUID DEGRADATION	method	limit/base	current	history1	history2	
Oxidation	Abs./1mm	ASTM D7414*	>25	<b>15.4</b>	17.3	16.9

VISUAL	method	limit/base	current	history1	history2	
Emulsified Water	scalar	Visual*	>0.2	<b>NEG</b>	NEG	NEG
Free Water	scalar	Visual*		<b>NEG</b>	NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D7279(m)	14.4	<b>▲ 11.1</b>	10.9	10.5

## GRAPHS


Iron (ppm)

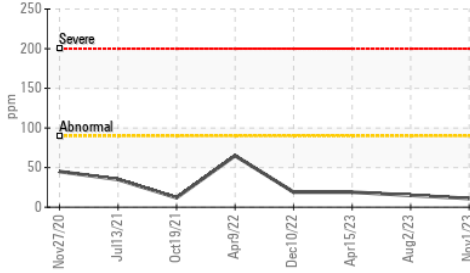


Lead (ppm)

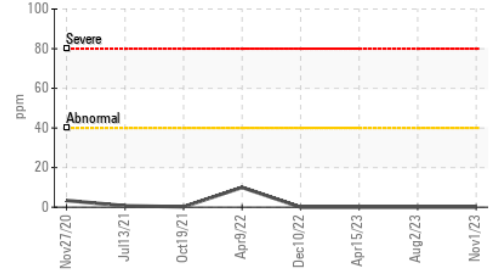


Aluminum (ppm)

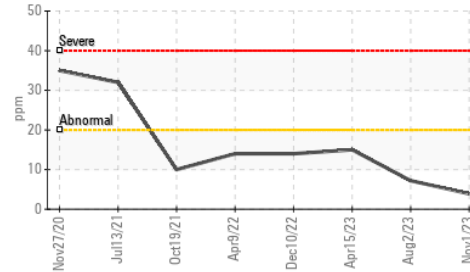


Chromium (ppm)

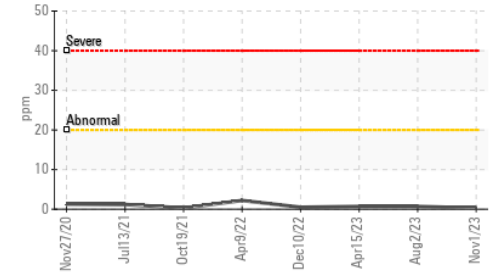


Copper (ppm)

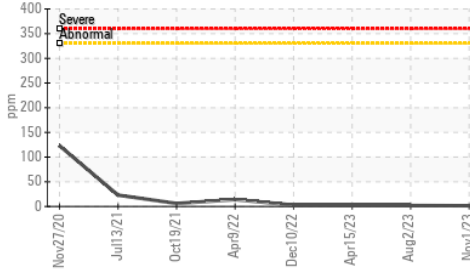


Silicon (ppm)

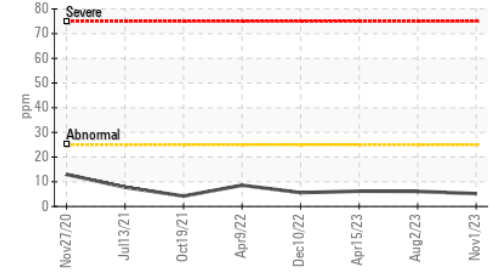

▲ Viscosity @ 100°C

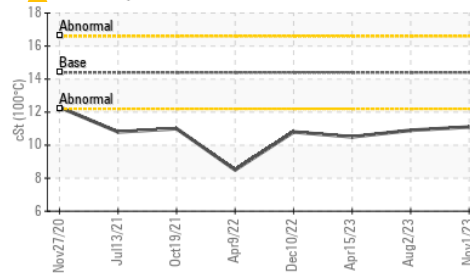

▲ Fuel Dilution

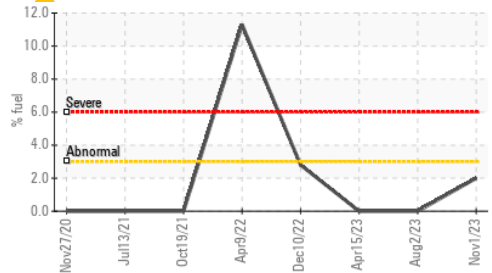

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : WC0853097 **Received** : 19 Jan 2024  
**Lab Number** : **02609908** **Diagnosed** : 22 Jan 2024  
**Unique Number** : 5710994 **Diagnostician** : Wes Davis  
**Test Package** : MOB 1 ( Additional Tests: FUELDILUTION, PercentFuel )

**Rush Truck Centres**  
 7450 Torbram Rd.  
 Mississauga, ON  
 CA L4T 1G9  
 Contact: Serdar Okur  
 sokur@rushtruckcentres.ca  
 T: (905)671-7600  
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.