


# PROBLEM SUMMARY

Sample Rating Trend

**DEGRADATION**




Machine Id  
**G2 L3**  
Component  
**Hydraulic System**  
Fluid  
**{not provided} (--- GAL)**

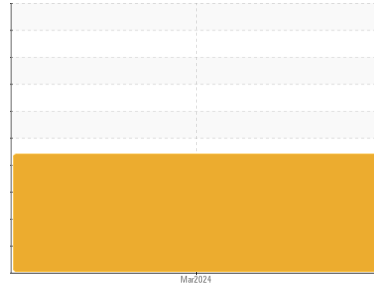

## COMPONENT CONDITION SUMMARY

### ▲ Acid Number

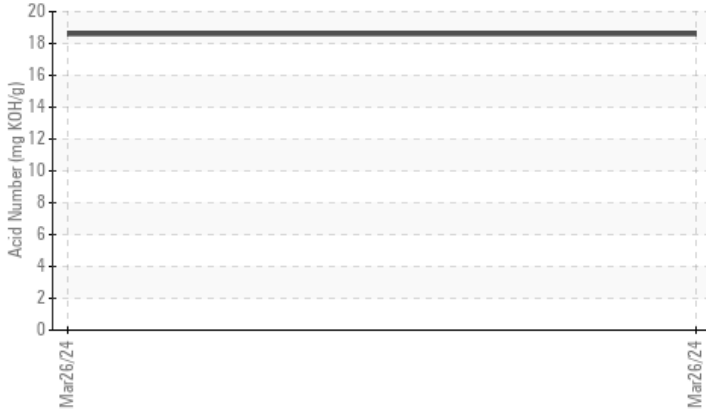

### ▲ Particle Trend



## RECOMMENDATION

Little or no information is provided as to the component and lubricant being tested. Recommendations are therefore generic in nature and may not apply to the current application. Please forward information as to equipment type, reservoir capacity, lubricant type and any pertinent information to allow for a more accurate assessment. We recommend that you drain the oil from the component if this has not already been done. We recommend you service the filters on this component. We recommend an early resample to monitor this condition. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample. Please specify the brand, type, and viscosity of the oil on your next sample.

## PROBLEMATIC TEST RESULTS

Sample Status	SEVERE	---	---
Particles >4µm	ASTM D7647 >5000 ▲ <b>10839</b>	---	---
Oil Cleanliness	ISO 4406 (c) >19/17/14 ▲ <b>21/18/13</b>	---	---
Acid Number (AN)	mg KOH/g ASTM D974* ▲ <b>18.6</b>	---	---

Customer Id: DIO5800TT  
Sample No.: ST45544  
Lab Number: 02624949  
Test Package: IND 2



To manage this report scan the QR code

To discuss the diagnosis or test data:  
Kevin Marson +1 (289)291-4644 x4644  
[Kevin.Marson@wearcheck.com](mailto:Kevin.Marson@wearcheck.com)

To change component or sample information:  
Gloria Gonzalez +1 (289)291-4643 x4643  
[gloria.gonzalez@wearcheck.com](mailto:gloria.gonzalez@wearcheck.com)


## RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Fluid	---	---	?	We recommend that you drain the oil from the component if this has not already been done.
Change Filter	---	---	?	We recommend you service the filters on this component.
Resample	---	---	?	We recommend an early resample to monitor this condition.
Alert	---	---	?	Little or no information is provided as to the component and lubricant being tested. Recommendations are therefore generic in nature and may not apply to the current application. Please forward information as to equipment type, reservoir capacity, lubricant type and any pertinent information to allow for a more accurate assessment.
Information Required	---	---	?	Please specify the brand, type, and viscosity of the oil on your next sample. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample.

## HISTORICAL DIAGNOSIS



Machine Id  
**G2 L3**  
 Component  
**Hydraulic System**  
 Fluid  
**{not provided} (--- GAL)**

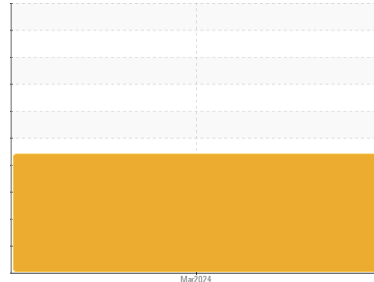

**DIAGNOSIS**

**▲ Recommendation**  
 Little or no information is provided as to the component and lubricant being tested. Recommendations are therefore generic in nature and may not apply to the current application. Please forward information as to equipment type, reservoir capacity, lubricant type and any pertinent information to allow for a more accurate assessment. We recommend that you drain the oil from the component if this has not already been done. We recommend you service the filters on this component. We recommend an early resample to monitor this condition. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample. Please specify the brand, type, and viscosity of the oil on your next sample.

**Wear**  
 All component wear rates are normal.

**▲ Contamination**  
 There is a moderate amount of silt (particulates < 14 microns in size) present in the oil. The water content is negligible.

**▲ Fluid Condition**  
 The high AN level of the oil indicates the presence of oxi-polymerized products. The AN level is much higher than the recommended limit. The oil is no longer serviceable.

**SAMPLE INFORMATION**

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>ST45544</b>	---	---
Sample Date	Client Info		<b>26 Mar 2024</b>	---	---
Machine Age	hrs	Client Info	<b>0</b>	---	---
Oil Age	hrs	Client Info	<b>0</b>	---	---
Oil Changed	Client Info		<b>N/A</b>	---	---
Sample Status			<b>SEVERE</b>	---	---

**WEAR METALS**

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>20	<b>11</b>	---
Chromium	ppm	ASTM D5185(m)	>20	<b>0</b>	---
Nickel	ppm	ASTM D5185(m)	>20	<b>0</b>	---
Titanium	ppm	ASTM D5185(m)		<b>0</b>	---
Silver	ppm	ASTM D5185(m)		<b>0</b>	---
Aluminum	ppm	ASTM D5185(m)	>20	<b>0</b>	---
Lead	ppm	ASTM D5185(m)	>20	<b>0</b>	---
Copper	ppm	ASTM D5185(m)	>20	<b>&lt;1</b>	---
Tin	ppm	ASTM D5185(m)	>20	<b>0</b>	---
Antimony	ppm	ASTM D5185(m)		<b>0</b>	---
Vanadium	ppm	ASTM D5185(m)		<b>0</b>	---
Beryllium	ppm	ASTM D5185(m)		<b>0</b>	---
Cadmium	ppm	ASTM D5185(m)		<b>0</b>	---

**ADDITIVES**

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)		<b>&lt;1</b>	---
Barium	ppm	ASTM D5185(m)		<b>0</b>	---
Molybdenum	ppm	ASTM D5185(m)		<b>0</b>	---
Manganese	ppm	ASTM D5185(m)		<b>0</b>	---
Magnesium	ppm	ASTM D5185(m)		<b>&lt;1</b>	---
Calcium	ppm	ASTM D5185(m)		<b>2</b>	---
Phosphorus	ppm	ASTM D5185(m)		<b>253</b>	---
Zinc	ppm	ASTM D5185(m)		<b>16</b>	---
Sulfur	ppm	ASTM D5185(m)		<b>1629</b>	---
Lithium	ppm	ASTM D5185(m)		<b>&lt;1</b>	---






**CONTAMINANTS**

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	>15	<b>8</b>	---
Sodium	ppm	ASTM D5185(m)		<b>&lt;1</b>	---
Potassium	ppm	ASTM D5185(m)	>20	<b>&lt;1</b>	---
Water	%	ASTM D6304*	>0.05	<b>0.049</b>	---
ppm Water	ppm	ASTM D6304*	>500	<b>491</b>	---

**FLUID CLEANLINESS**

	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>5000	<b>▲ 10839</b>	---	---
Particles >6µm	ASTM D7647	>1300	<b>● 1371</b>	---	---
Particles >14µm	ASTM D7647	>160	<b>67</b>	---	---
Particles >21µm	ASTM D7647	>40	<b>20</b>	---	---
Particles >38µm	ASTM D7647	>10	<b>4</b>	---	---
Particles >71µm	ASTM D7647	>3	<b>1</b>	---	---
Oil Cleanliness	ISO 4406 (c)	>19/17/14	<b>▲ 21/18/13</b>	---	---

# OIL ANALYSIS REPORT

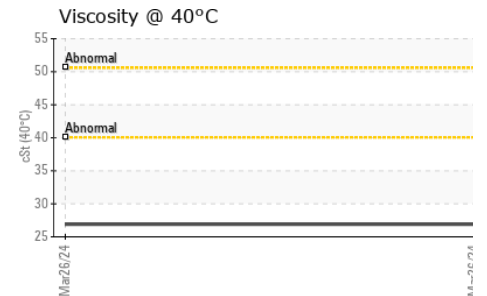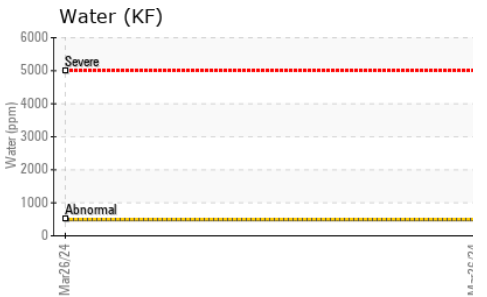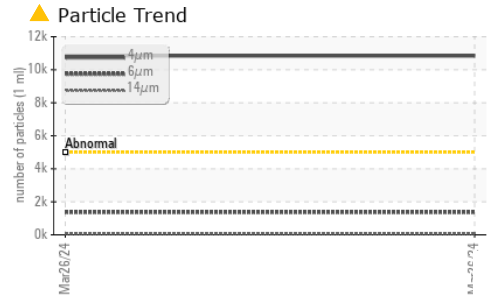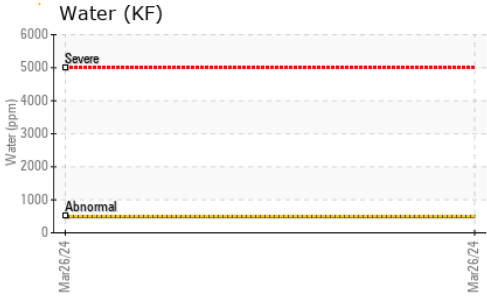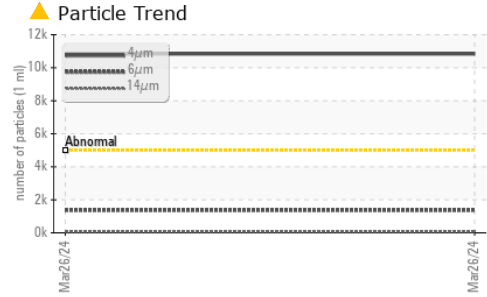






FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974*		<span style="color: red;">▲ 18.6</span>	---	---

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	<b>NONE</b>	---	---
Yellow Metal	scalar	Visual*	NONE	<b>NONE</b>	---	---
Precipitate	scalar	Visual*	NONE	<b>NONE</b>	---	---
Silt	scalar	Visual*	NONE	<b>NONE</b>	---	---
Debris	scalar	Visual*	NONE	<b>NONE</b>	---	---
Sand/Dirt	scalar	Visual*	NONE	<b>NONE</b>	---	---
Appearance	scalar	Visual*	NORML	<b>NORML</b>	---	---
Odor	scalar	Visual*	NORML	<b>NORML</b>	---	---
Emulsified Water	scalar	Visual*	>0.05	<b>NEG</b>	---	---
Free Water	scalar	Visual*		<b>NEG</b>	---	---

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)		<b>26.9</b>	---	---

SAMPLE IMAGES		method	limit/base	current	history1	history2
Color					no image	no image
Bottom					no image	no image

### GRAPHS

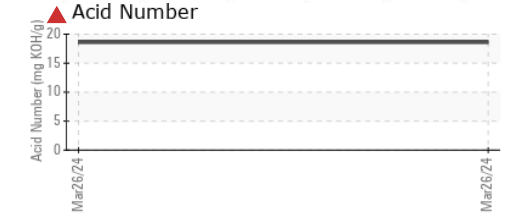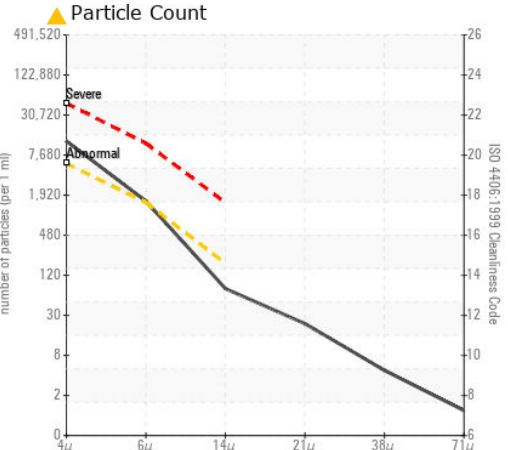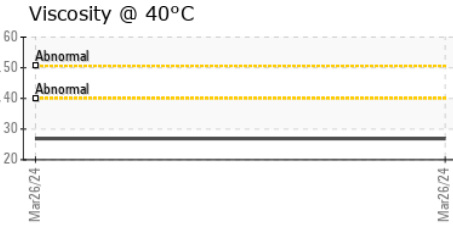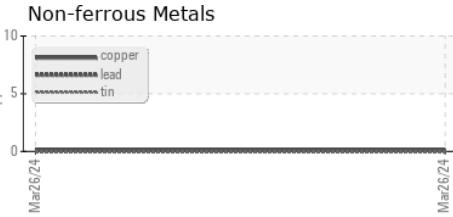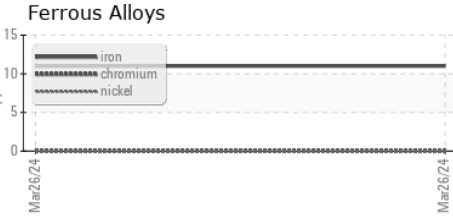

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : ST45544 **Received** : 27 Mar 2024  
**Lab Number** : 02624949 **Tested** : 28 Mar 2024  
**Unique Number** : 5750068 **Diagnosed** : 01 Apr 2024 - Kevin Marson  
**Test Package** : IND 2 ( Additional Tests: KF, TAN Man )

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.

**DIOTTES HYDRAULICS**  
 580 INDUSTRIAL AVE, #2  
 OTTAWA, ON  
 CA K1G 0Y9  
 Contact: Brodie Diotte  
 brodie@diottes.com  
 T: (613)244-4735  
 F: