



# OIL ANALYSIS REPORT

Sample Rating Trend


**NORMAL**



Area  
**3000 Series**  
Machine Id  
**Navistar 3236**

Component  
**Diesel Engine**  
Fluid

**PETRO CANADA DURON SHP 10W30 (26 LTR)**

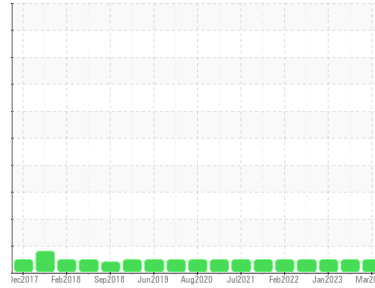

## DIAGNOSIS

### Recommendation

Confirm the source of the lubricant being utilized for top-up/fill. Resample at the next service interval to monitor.

### Wear

All component wear rates are normal.

### Contamination

Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. There is no indication of any contamination in the oil.

### Fluid Condition

Additive levels indicate the addition of a different brand, or type of oil. The condition of the oil is acceptable for the time in service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			<b>WC0915040</b>	WC0805732	WC0771251
Sample Date	Client Info			<b>27 Mar 2024</b>	29 Jul 2023	09 Jan 2023
Machine Age	mls	Client Info		<b>442795</b>	400770	358858
Oil Age	mls	Client Info		<b>21153</b>	21702	20573
Oil Changed	Client Info			<b>Changed</b>	Changed	Changed
Sample Status				<b>NORMAL</b>	NORMAL	NORMAL

CONTAMINATION		method	limit/base	current	history1	history2
Fuel	WC Method	>3.0		<b>&lt;1.0</b>	<1.0	<1.0
Water	WC Method	>0.2		<b>NEG</b>	NEG	NEG
Glycol	WC Method			<b>NEG</b>	NEG	NEG

WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>75	<b>30</b>	35	26
Chromium	ppm	ASTM D5185(m)	>5	<b>&lt;1</b>	1	<1
Nickel	ppm	ASTM D5185(m)	>4	<b>&lt;1</b>	<1	<1
Titanium	ppm	ASTM D5185(m)	>2	<b>0</b>	0	<1
Silver	ppm	ASTM D5185(m)	>2	<b>0</b>	<1	0
Aluminum	ppm	ASTM D5185(m)	>15	<b>6</b>	6	5
Lead	ppm	ASTM D5185(m)	>25	<b>0</b>	<1	<1
Copper	ppm	ASTM D5185(m)	>100	<b>1</b>	2	1
Tin	ppm	ASTM D5185(m)	>4	<b>0</b>	0	<1
Antimony	ppm	ASTM D5185(m)		<b>0</b>	0	<1
Vanadium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Beryllium	ppm	ASTM D5185(m)		<b>0</b>	0	0
Cadmium	ppm	ASTM D5185(m)		<b>0</b>	0	0



ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)	2	<b>48</b>	2	53
Barium	ppm	ASTM D5185(m)	0	<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185(m)	50	<b>8</b>	60	12
Manganese	ppm	ASTM D5185(m)	0	<b>0</b>	<1	<1
Magnesium	ppm	ASTM D5185(m)	950	<b>131</b>	969	172
Calcium	ppm	ASTM D5185(m)	1050	<b>2110</b>	1077	2146
Phosphorus	ppm	ASTM D5185(m)	995	<b>912</b>	1096	995
Zinc	ppm	ASTM D5185(m)	1180	<b>1143</b>	1233	1149
Sulfur	ppm	ASTM D5185(m)	2600	<b>2598</b>	2456	2833
Lithium	ppm	ASTM D5185(m)		<b>&lt;1</b>	<1	<1

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	>25	<b>7</b>	7	5
Sodium	ppm	ASTM D5185(m)		<b>2</b>	2	3
Potassium	ppm	ASTM D5185(m)	>20	<b>6</b>	2	6

INFRA-RED		method	limit/base	current	history1	history2
Soot %	%	ASTM D7844*	>6	<b>0.7</b>	0.6	0.5
Nitration	Abs/cm	ASTM D7624*	>20	<b>11.2</b>	11.2	11.6
Sulfation	Abs/.1mm	ASTM D7415*	>30	<b>27.2</b>	23.1	27.4



# OIL ANALYSIS REPORT







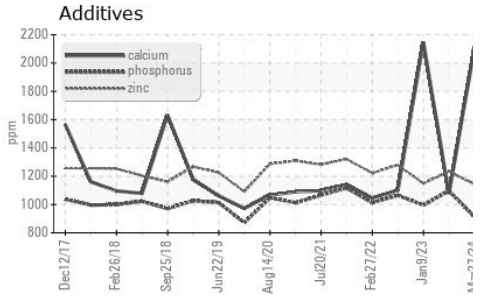
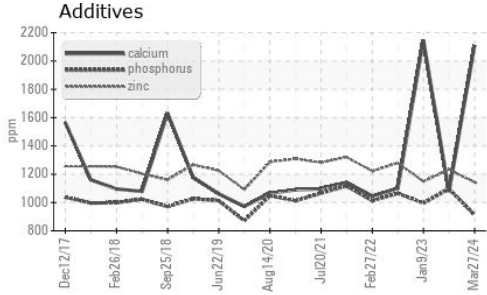


FLUID DEGRADATION		method	limit/base	current	history1	history2
Oxidation	Abs./1mm	ASTM D7414*	>25	<b>24.2</b>	20.1	23.8

VISUAL		method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.2	<b>NEG</b>	NEG	NEG
Free Water	scalar	Visual*		<b>NEG</b>	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D7279(m)	12.00	<b>11.9</b>	11.6	12.0

## GRAPHS

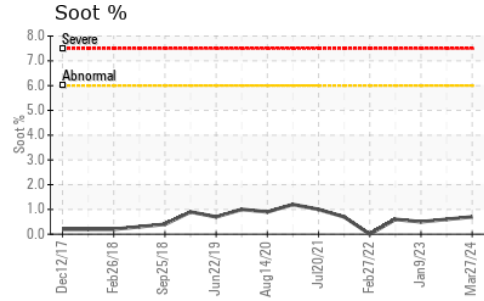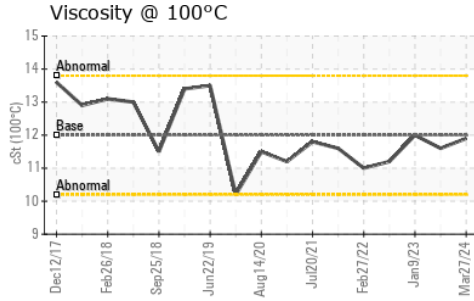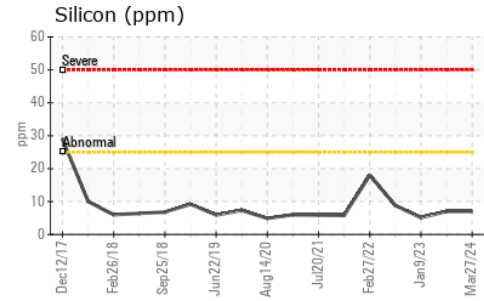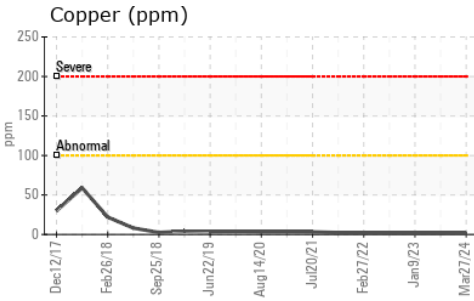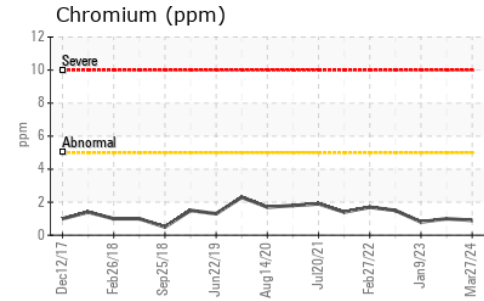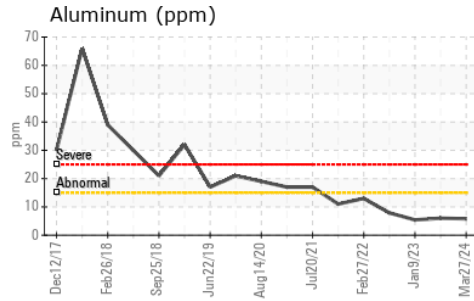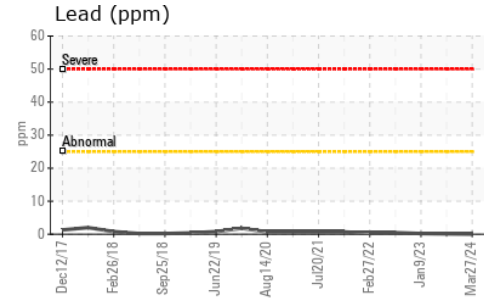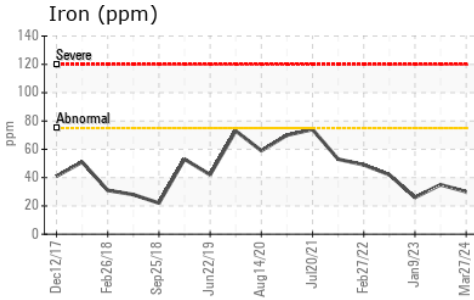

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : WC0915040  
**Lab Number** : **02626371**  
**Unique Number** : 5759503  
**Test Package** : MOB 1  
**Received** : 03 Apr 2024  
**Tested** : 03 Apr 2024  
**Diagnosed** : 03 Apr 2024 - Wes Davis

**MANITOU LIN TRANSPORT (GARAGE)**  
 1335 SHAWSON DRIVE  
 MISSISSAUGA, ON  
 CA L4W 1C4  
 Contact: Travis Spence  
 tspence@manitoulintransport.com  
 T:  
 F: (905)564-6361

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.