



COOLANT REPORT

Sample Rating Trend



WEAR



Area
UNASSIGNED [700017422]
 Machine Id
208138
 Component
Coolant
 Fluid
CATERPILLAR ELC (--- GAL)

DIAGNOSIS

▲ Recommendation

We recommend drain system, and refill with 50/50 antifreeze water mixture. We advise that you replenish the supplemental coolant additives (SCAs) and add per manufacturer's specifications. We recommend an early resample to monitor this condition.

▲ Corrosion

Copper ppm levels are abnormal. The high metal levels indicate corrosion in the system.

Contaminants

There is no indication of any contamination in the coolant.

Coolant Condition

The nitrite level is acceptable. The pH level of this fluid is within the acceptable limits. The reserve alkalinity of this fluid is acceptable.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			WC0952373	---	---
Sample Date	Client Info			07 Jun 2024	---	---
Machine Age	hrs	Client Info		0	---	---
Oil Age	hrs	Client Info		0	---	---
Oil Changed	Client Info			N/A	---	---
Sample Status				ABNORMAL	---	---

PHYSICAL TEST RESULTS		method	limit/base	current	history1	history2
Glycol Type	FT-IR			UNK	---	---
Specific Gravity	ASTM D1298*	1.070		1.077	---	---
pH	Scale 0-14	ASTM D1287*	8.3	7.78	---	---
Nitrites	ppm	Alcan Test Kit*	550	560	---	---
Reserve Alkalinity	Scale 0-20	ASTM D1121*	5.5	3.9	---	---
Percentage Glycol	%	ASTM D3321*	50	57.9	---	---
Freezing Point	°C	ASTM D3321*	-37	-47	---	---
Carboxylate				---	---	---

CORROSION INHIBITORS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	0	5	---	---
Phosphorus	ppm	ASTM D5185(m)	0	24	---	---
Boron	ppm	ASTM D5185(m)	0	79	---	---
Molybdenum	ppm	ASTM D5185(m)	950	58	---	---

CORROSION		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>15	0	---	---
Aluminum	ppm	ASTM D5185(m)	>10	0	---	---
Copper	ppm	ASTM D5185(m)	>10	▲ 17	---	---
Lead	ppm	ASTM D5185(m)	>10	0	---	---
Tin	ppm	ASTM D5185(m)	>10	0	---	---
Silver	ppm	ASTM D5185(m)	>10	<1	---	---
Zinc	ppm	ASTM D5185(m)		<1	---	---


CARRIER SALTS		method	limit/base	current	history1	history2
Sodium	ppm	ASTM D5185(m)		6157	---	---
Potassium	ppm	ASTM D5185(m)		320	---	---

SCALE POTENTIAL		method	limit/base	current	history1	history2
Calcium	ppm	ASTM D5185(m)	>100	2	---	---
Magnesium	ppm	ASTM D5185(m)	>40	1	---	---
Hardness	mg/L CaCO3	In-house*	<75	9	---	---





COOLANT REPORT

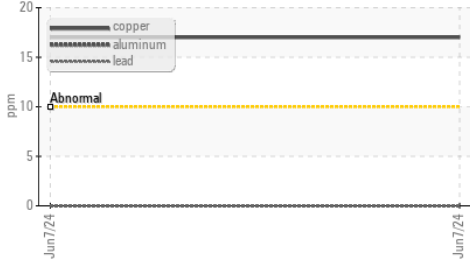▲ Copper/Aluminum/Lead



Nitrites




VISUAL	method	limit/base	current	history1	history2
Coolant Color	Visual*	Red	Orange	---	---
Coolant Appearance	Visual*	Clear	Clear	---	---
Color				no image	no image
Bottom				no image	no image

GRAPHS


Iron/Tin/Silver




Reserve Alkalinity

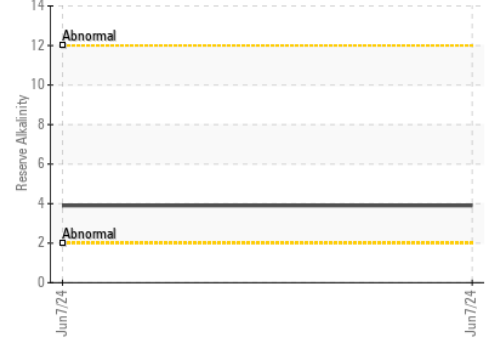


▲ Copper/Aluminum/Lead

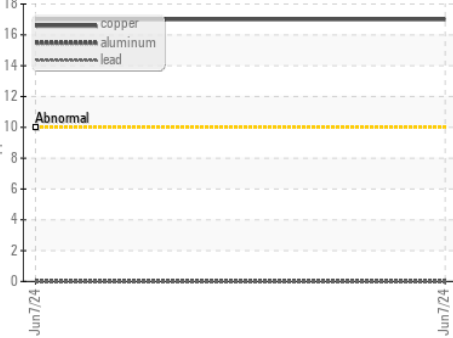


Freeze Point

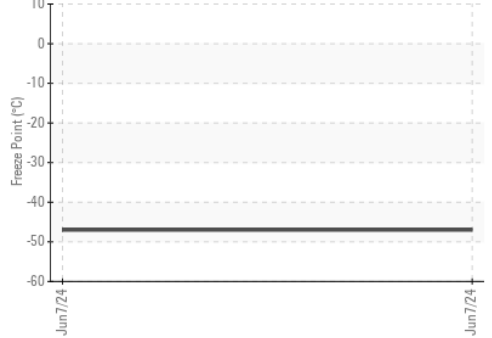

pH

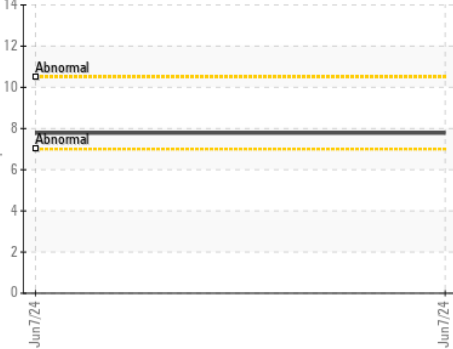

Nitrites

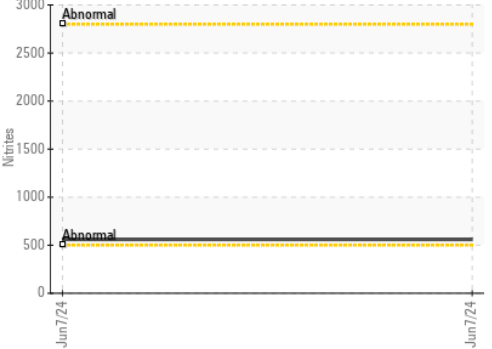

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0952373 **Received** : 10 Jun 2024
Lab Number : **02640878** **Tested** : 11 Jun 2024
Unique Number : 5798417 **Diagnosed** : 12 Jun 2024 - Kevin Marson
Test Package : COOL (Additional Tests: GlycolType)

REGION OF HALTON
 1141 LAKESHORE ROAD
 BURLINGTON, ON
 CA L7S 1A8
 Contact: RICK BULLMANN
 rick.bullmann@halton.ca
 T: (905)825-6000
 F: (905)639-5990

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.