




PROBLEM SUMMARY

Sample Rating Trend


WEAR PARTICLES



Machine Id
MASERATI ZAM57RTAOF1140963
 Component
Gasoline Engine
 Fluid
GASOLINE ENGINE OIL SAE 5W20 (--- GAL)

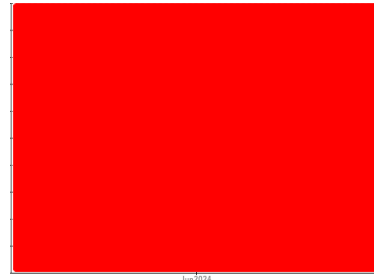

COMPONENT CONDITION SUMMARY

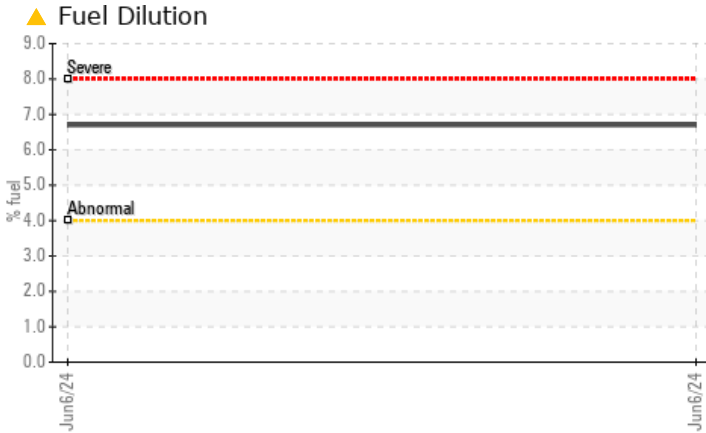

RECOMMENDATION

We understand that this sample is for warranty/insurance purposes. An inspection for the source(s) of wear may be warranted at this time. Diagnostician's Note: There was a moderate amount of gasoline present in the oil, however, this would likely not cause the failure. The wear metals indicate the crank or camshaft likely failed. There is mostly ferrous sliding wear particles (cam/crankshaft) and little aluminum (bearings). The wear particles indicate a rapid failure, and there are no signs of tempering of the wear particles so a lack of lubrication was not a contributing factor.

PROBLEMATIC TEST RESULTS

Sample Status	Scale	ASTM	SEVERE	---	---
Ferrous Rubbing	Scale 0-10	ASTM D7684*	▲ 8		
Ferrous Sliding	Scale 0-10	ASTM D7684*	▲ 8		
Ferrous Rolling	Scale 0-10	ASTM D7684*	▲ 4		
Patch Weight	mg	ASTM D7684*	▲ 2854	---	---
Fuel	%	ASTM D7593*	▲ 6.7	---	---

Customer Id: JENOSH
 Sample No.: PP0001077
 Lab Number: 02641106
 Test Package: INS



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Bill Quesnel CLS,OMA II,MLA-III,LLA-I +1
 (289)291-4641 x4641
Bill.Quesnel@wearcheck.com

To change component or sample information:
 Gloria Gonzalez +1 (289)291-4643 x4643
gloria.gonzalez@wearcheck.com

RECOMMENDED ACTIONS


Action	Status	Date	Done By	Description
Inspect Wear Source	---	---	?	An inspection for the source(s) of wear may be warranted at this time.

HISTORICAL DIAGNOSIS



OIL ANALYSIS REPORT

Sample Rating Trend

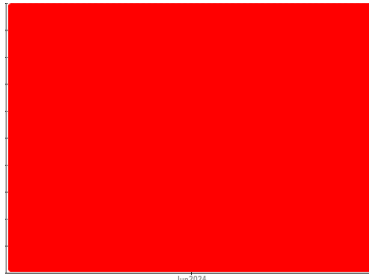

WEAR PARTICLES



Machine Id

MASERATI ZAM57RTAOF1140963

Component

Gasoline Engine

Fluid

GASOLINE ENGINE OIL SAE 5W20 (--- GAL)

DIAGNOSIS

▲ Recommendation

We understand that this sample is for warranty/insurance purposes. An inspection for the source(s) of wear may be warranted at this time. Diagnostician's Note: There was a moderate amount of gasoline present in the oil, however, this would likely not cause the failure. The wear metals indicate the crank or camshaft likely failed. There is mostly ferrous sliding wear particles (cam/crankshaft) and little aluminum (bearings). The wear particles indicate a rapid failure, and there are no signs of tempering of the wear particles so a lack of lubrication was not a contributing factor.

▲ Wear Particles

Wear particle analysis indicates that the ferrous rolling and ferrous sliding particles are severe. Wear particle analysis indicates that the patch weight and ferrous rubbing particles are abnormal.

▲ Contaminants

There is a moderate amount of fuel present in the oil. Tests confirm the presence of fuel in the oil.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		PP0001077	---	---
Sample Date	Client Info		06 Jun 2024	---	---
Machine Age	kms	Client Info	139828	---	---
Oil Age	kms	Client Info	0	---	---
Oil Changed	Client Info		N/A	---	---
Sample Status			SEVERE	---	---

CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.2	NEG	---	---
Glycol	WC Method		NEG	---	---

WEAR METALS






	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>150	103	---
Chromium	ppm	ASTM D5185(m)	>20	<1	---
Nickel	ppm	ASTM D5185(m)	>5	0	---
Titanium	ppm	ASTM D5185(m)		0	---
Silver	ppm	ASTM D5185(m)	>2	<1	---
Aluminum	ppm	ASTM D5185(m)	>40	29	---
Lead	ppm	ASTM D5185(m)	>50	0	---
Copper	ppm	ASTM D5185(m)	>155	18	---
Tin	ppm	ASTM D5185(m)	>10	0	---
Antimony	ppm	ASTM D5185(m)		0	---
Vanadium	ppm	ASTM D5185(m)		0	---
Beryllium	ppm	ASTM D5185(m)		0	---
Cadmium	ppm	ASTM D5185(m)		0	---

FERROGRAPHY

	method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*	▲ 8		
Ferrous Sliding	Scale 0-10	ASTM D7684*	▲ 8		
Ferrous Cutting	Scale 0-10	ASTM D7684*			
Ferrous Rolling	Scale 0-10	ASTM D7684*	▲ 4		
Ferrous Break-in	Scale 0-10	ASTM D7684*			
Ferrous Spheres	Scale 0-10	ASTM D7684*			
Ferrous Black Oxides	Scale 0-10	ASTM D7684*			
Ferrous Red Oxides	Scale 0-10	ASTM D7684*			
Ferrous Corrosive	Scale 0-10	ASTM D7684*			
Ferrous Other	Scale 0-10	ASTM D7684*			
Nonferrous Rubbing	Scale 0-10	ASTM D7684*	■ 3		
Nonferrous Sliding	Scale 0-10	ASTM D7684*	■ 2		
Nonferrous Cutting	Scale 0-10	ASTM D7684*			
Nonferrous Rolling	Scale 0-10	ASTM D7684*	■ 2		
Nonferrous Other	Scale 0-10	ASTM D7684*			
Sand/Dirt	Scale 0-10	ASTM D7684*	■ 2		
Fibres	Scale 0-10	ASTM D7684*	■ 1		
Spheres	Scale 0-10	ASTM D7684*			
Other	Scale 0-10	ASTM D7684*			
Patch Weight	mg	ASTM D7684*	▲ 2854	---	---



OIL ANALYSIS REPORT

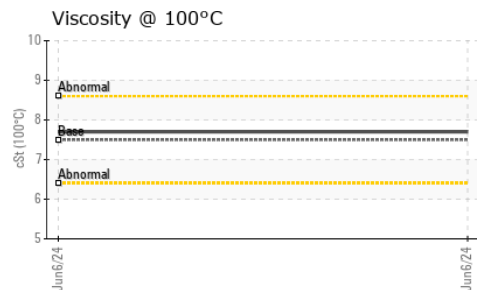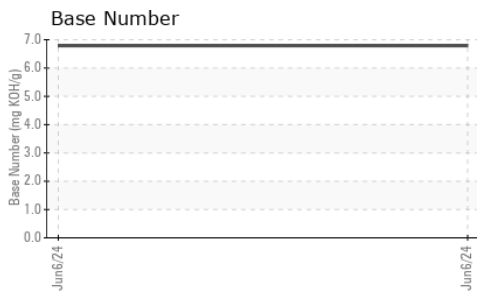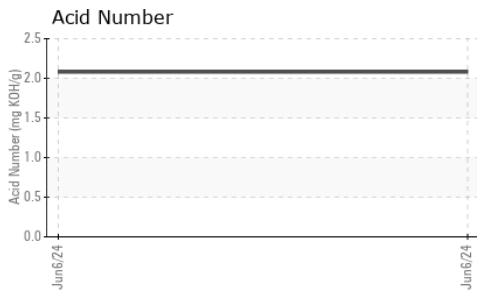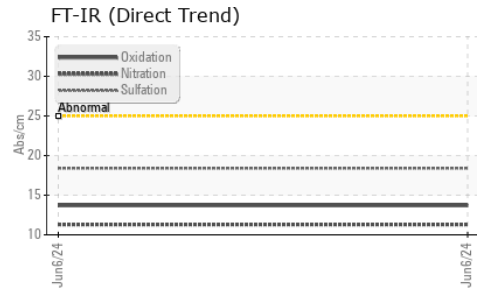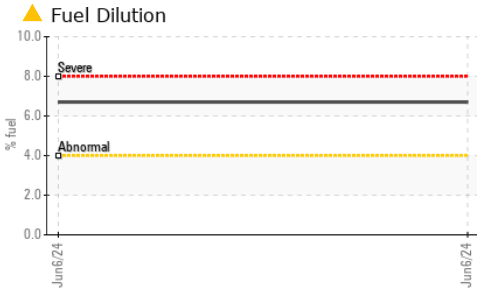

ADDITIVES	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185(m)	75	52	---	---
Barium	ppm	ASTM D5185(m)	5	0	---	---
Molybdenum	ppm	ASTM D5185(m)	100	57	---	---
Manganese	ppm	ASTM D5185(m)		4	---	---
Magnesium	ppm	ASTM D5185(m)	12	523	---	---
Calcium	ppm	ASTM D5185(m)	2100	911	---	---
Phosphorus	ppm	ASTM D5185(m)	650	504	---	---
Zinc	ppm	ASTM D5185(m)	850	590	---	---
Sulfur	ppm	ASTM D5185(m)	2500	1819	---	---
Lithium	ppm	ASTM D5185(m)		<1	---	---

CONTAMINANTS	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185(m)	>30	8	---	---
Sodium	ppm	ASTM D5185(m)	>50	2	---	---
Potassium	ppm	ASTM D5185(m)	>20	2	---	---
Fuel	%	ASTM D7593*	>4.0	6.7	---	---

INFRA-RED	method	limit/base	current	history1	history2	
Soot %	%	ASTM D7844*		0	---	---
Nitration	Abs/cm	ASTM D7624*	>20	11.3	---	---
Sulfation	Abs./1mm	ASTM D7415*	>30	18.4	---	---

FLUID DEGRADATION	method	limit/base	current	history1	history2	
Oxidation	Abs./1mm	ASTM D7414*	>25	13.7	---	---
Acid Number (AN)	mg KOH/g	ASTM D974*		2.08	---	---
Base Number (BN)	mg KOH/g	ASTM D2896*		6.79	---	---

VISUAL	method	limit/base	current	history1	history2	
White Metal	scalar	Visual*	NONE	VLITE	---	---
Yellow Metal	scalar	Visual*	NONE	NONE	---	---
Precipitate	scalar	Visual*	NONE	NONE	---	---
Silt	scalar	Visual*	NONE	NONE	---	---
Debris	scalar	Visual*	NONE	NONE	---	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---	---
Appearance	scalar	Visual*	NORML	NORML	---	---
Odor	scalar	Visual*	NORML	NORML	---	---
Emulsified Water	scalar	Visual*	>0.2	NEG	---	---
Free Water	scalar	Visual*		NEG	---	---

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 40°C	cSt	ASTM D7279(m)	44	40.2	---	---
Visc @ 100°C	cSt	ASTM D7279(m)	7.5	7.7	---	---
Viscosity Index (VI)	Scale	ASTM D2270*	136	164	---	---



Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : PP0001077
Lab Number : 02641106
Unique Number : 5798645
Test Package : INS (Additional Tests: FT-IR, FuelDilution, PercentFuel, TAN Man, VI)

JENISH ENGINEERING LIMITED
 1675 baseline Road West
 Courtice, ON
 CA L1E 2S6
 Contact: Gord Jenish
 kl@jenish.ca
 T: (905)404-9285
 F: (905)404-9843



To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.

FILTER REPORT

Machine Id
MASERATI ZAM57RTAOF1140963

Component
Gasoline Engine

Fluid
GASOLINE ENGINE OIL SAE 5W20 (--- GAL)

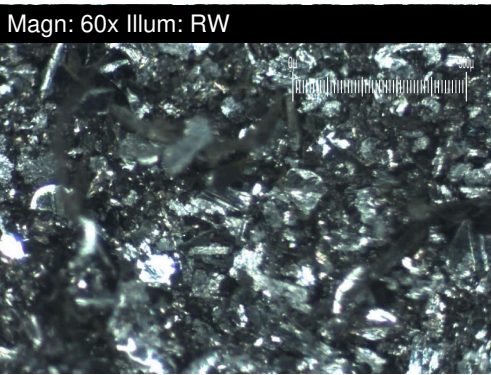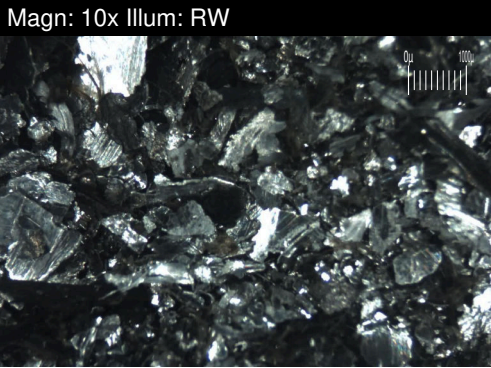

FERROGRAPHY			method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	ASTM D7684*			▲ 8		
Ferrous Sliding	Scale 0-10	ASTM D7684*			▲ 8		
Ferrous Cutting	Scale 0-10	ASTM D7684*					
Ferrous Rolling	Scale 0-10	ASTM D7684*			▲ 4		
Ferrous Break-in	Scale 0-10	ASTM D7684*					
Ferrous Spheres	Scale 0-10	ASTM D7684*					
Ferrous Black Oxides	Scale 0-10	ASTM D7684*					
Ferrous Red Oxides	Scale 0-10	ASTM D7684*					
Ferrous Corrosive	Scale 0-10	ASTM D7684*					
Ferrous Other	Scale 0-10	ASTM D7684*					
Nonferrous Rubbing	Scale 0-10	ASTM D7684*			■ 3		
Nonferrous Sliding	Scale 0-10	ASTM D7684*			■ 2		
Nonferrous Cutting	Scale 0-10	ASTM D7684*					
Nonferrous Rolling	Scale 0-10	ASTM D7684*			■ 2		
Nonferrous Other	Scale 0-10	ASTM D7684*					
Sand/Dirt	Scale 0-10	ASTM D7684*			■ 2		
Fibres	Scale 0-10	ASTM D7684*			■ 1		
Spheres	Scale 0-10	ASTM D7684*					
Other	Scale 0-10	ASTM D7684*					
Patch Weight	mg	ASTM D7684*			▲ 2854	---	---

WEAR

Wear particle analysis indicates that the ferrous rolling and ferrous sliding particles are severe. Wear particle analysis indicates that the patch weight and ferrous rubbing particles are abnormal.

This page left intentionally blank