

OIL ANALYSIS REPORT

SAMPLE INFO

Batch #

Department

Sent to WC Sample Number Sample Date Machine Age Oil Age

Oil Changed

Sample From

Production Stage

hrs

Client Info

Client Info

Core Molding - C16700 M13418

Component Hydraulic System Fluic {not provided} (--- GAL)

Recommendation

We certify that this oil is clean, that the additives are at acceptable levels, and that it is suitable for use.

Wear

Copper and iron ppm levels are noted.

			Jun ² 024		
RM	ATION	method			
		Client Info	Mobile		
		Client Info	Production		
		Client Info	Machine		
		Client Info	Final		
		Client Info	06/24/2024		
		Client Info	E30002465		
		Client Info	18 Jun 2024		
	hrs	Client Info	0		

0

N/A

Sample Status				NORMAL		
WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>20	23		
Chromium	ppm	ASTM D5185(m)	>20	<1		
Nickel	ppm	ASTM D5185(m)	>20	<1		
Titanium	ppm	ASTM D5185(m)		0		
Silver	ppm	ASTM D5185(m)		0		
Aluminum	ppm	ASTM D5185(m)	>20	3		
Lead	ppm	ASTM D5185(m)	>20	2		
Copper	ppm	ASTM D5185(m)	>20	28		
Tin	ppm	ASTM D5185(m)	>20	0		
Antimony	ppm	ASTM D5185(m)		0		
Vanadium	ppm	ASTM D5185(m)		0		
Beryllium	ppm	ASTM D5185(m)		0		
Cadmium	ppm	ASTM D5185(m)		<1		


ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)		<1		
Barium	ppm	ASTM D5185(m)		<1		
Molybdenum	ppm	ASTM D5185(m)		0		
Manganese	ppm	ASTM D5185(m)		<1		
Magnesium	ppm	ASTM D5185(m)		5		
Calcium	ppm	ASTM D5185(m)		27		
Phosphorus	ppm	ASTM D5185(m)		712		
Zinc	ppm	ASTM D5185(m)		404		
Sulfur	ppm	ASTM D5185(m)		2259		
Lithium	ppm	ASTM D5185(m)		<1		
CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	>15	7		
Sodium	ppm	ASTM D5185(m)		0		
Potassium	ppm	ASTM D5185(m)	>20	0		
Water	%	ASTM D6304*	>0.05	0.001		
ppm Water	ppm	ASTM D6304*	>500	13		


Sample Rating Trend






OIL ANALYSIS REPORT

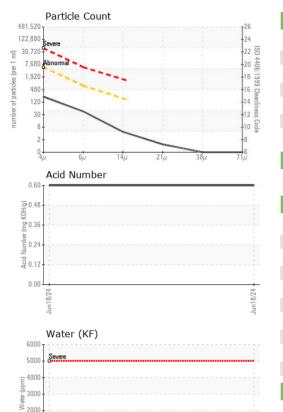

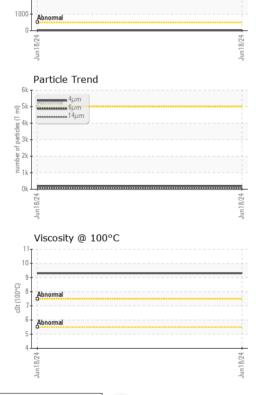

FLUID CLEANLIN	ESS	method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>5000	191		
Particles >6µm		ASTM D7647	>640	38		
Particles >14µm		ASTM D7647	>160	4		
Particles >21µm		ASTM D7647	>40	1		
Particles >38µm		ASTM D7647	>10	0		
Particles >71µm		ASTM D7647	>3	0		
Oil Cleanliness		ISO 4406 (c)	>19/16/14	15/12/9		
FLUID DEGRADA	TION	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974*		0.60		
VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE		
Yellow Metal	scalar	Visual*	NONE	NONE		
Precipitate	scalar	Visual*	NONE	NONE		
Silt	scalar	Visual*	NONE	NONE		
Debris	scalar	Visual*	NONE	NONE		
Sand/Dirt	scalar	Visual*	NONE	NONE		
Appearance	scalar	Visual*	NORML	NORML		
Odor	scalar	Visual*	NORML	NORML		
Emulsified Water	scalar	Visual*	>0.05	NEG		
Free Water	scalar	Visual*		NEG		
FLUID PROPERT	IES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)		69.5		
Visc @ 100°C	cSt	ASTM D7279(m)		9.3		
Viscosity Index (VI)	Scale	ASTM D2270*		110		
SAMPLE IMAGES	\$	method	limit/base	current	history1	history2
Color					no image	no image
Bottom					no image	no image



Report Id: CHECOB [WCAMIS] 02644162 (Generated: 06/27/2024 10:06:14) Rev: 1

Contact/Location: Tatiana Sorkina - CHECOB Page 2 of 2