OIL ANALYSIS REPORT

Sample Rating Trend

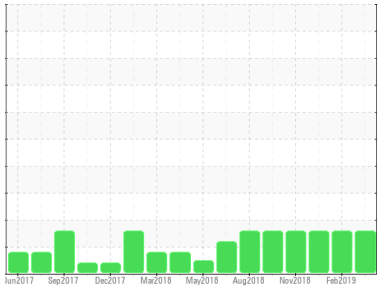

ISO

Area
RAW MATS
Machine Id
DISCHARGE HYD UNIT BALL MILL 2
Component
Hydraulic System
Fluid
MOBIL SHC 630 (25 GAL)

DIAGNOSIS

Recommendation
We recommend you service the filters on this component if applicable. Resample at the next service interval to monitor.

Wear
All component wear rates are normal.

Contamination
There is a high amount of particulates present in the oil.

Fluid Condition
The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number		Client Info		**WC0312509**	WC0312566	WCI2351112
Sample Date		Client Info		**29 Mar 2019**	18 Feb 2019	15 Jan 2019
Machine Age	days	Client Info		**0**	0	0
Oil Age	days	Client Info		**0**	0	0
Oil Changed		Client Info		**Not Changd**	Not Changd	Not Changd
Sample Status				**ABNORMAL**	ABNORMAL	ABNORMAL

WEAR METALS		method	limit/base	current	history1	history2
PQ		ASTM D8184		**14**	13	20
Iron	ppm	ASTM D5185m	>20	**<1**	<1	<1
Chromium	ppm	ASTM D5185m	>20	**0**	0	<1
Nickel	ppm	ASTM D5185m	>20	**0**	0	<1
Titanium	ppm	ASTM D5185m		**0**	0	<1
Silver	ppm	ASTM D5185m		**0**	0	0
Aluminum	ppm	ASTM D5185m	>20	**<1**	<1	<1
Lead	ppm	ASTM D5185m	>20	**<1**	<1	2
Copper	ppm	ASTM D5185m	>20	**<1**	<1	2
Tin	ppm	ASTM D5185m	>20	**0**	0	<1
Antimony	ppm	ASTM D5185m		**0**	0	0
Vanadium	ppm	ASTM D5185m		**0**	0	<1
Cadmium	ppm	ASTM D5185m		**0**	0	<1

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m		**0**	0	0
Barium	ppm	ASTM D5185m		**<1**	0	0
Molybdenum	ppm	ASTM D5185m		**<1**	<1	<1
Manganese	ppm	ASTM D5185m		**0**	<1	<1
Magnesium	ppm	ASTM D5185m		**0**	0	0
Calcium	ppm	ASTM D5185m		**0**	0	0
Phosphorus	ppm	ASTM D5185m		**461**	380	410
Zinc	ppm	ASTM D5185m		**0**	<1	0
Sulfur	ppm	ASTM D5185m		**14**	59	65

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>15	**15**	14	12
Sodium	ppm	ASTM D5185m		**0**	0	0
Potassium	ppm	ASTM D5185m	>20	**0**	<1	0
Water	%	ASTM D6304	>0.05	**0.002**	0.001	0.002
ppm Water	ppm	ASTM D6304	>500	**20**	10	20

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>640	▲ **59835**	▲ 3773	▲ 102768
Particles >6µm		ASTM D7647	>160	▲ **9245**	▲ 911	▲ 16634
Particles >14µm		ASTM D7647	>20	▲ **172**	▲ 33	▲ 516
Particles >21µm		ASTM D7647	>4	▲ **17**	▲ 8	▲ 80
Particles >38µm		ASTM D7647	>3	**0**	0	2
Particles >71µm		ASTM D7647	>3	**0**	0	0
Oil Cleanliness		ISO 4406 (c)	>16/14/11	▲ **23/20/15**	▲ 19/17/12	▲ 24/21/16

OIL ANALYSIS REPORT

Particle Trend

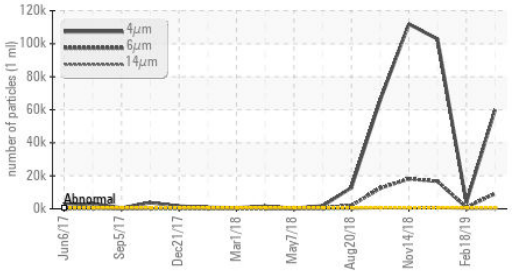

Water (KF)

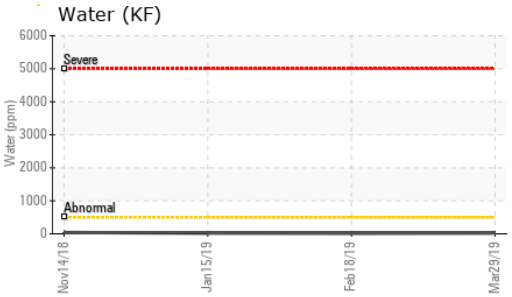

PQ

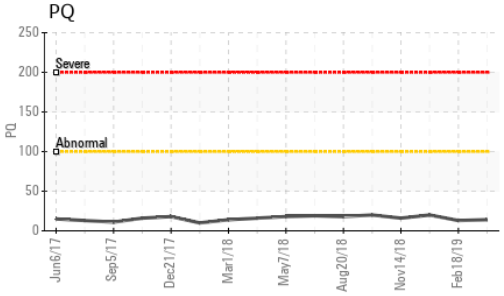

Water (KF)

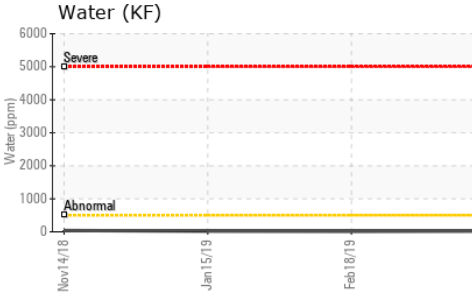

Viscosity @ 40°C

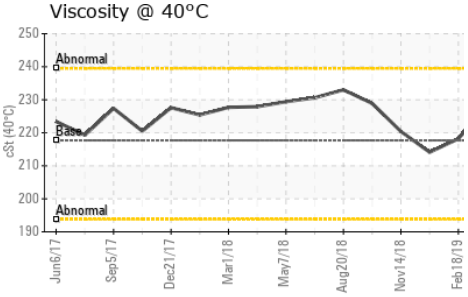

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045		**0.734**	0.434	0.366

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Precipitate	scalar	*Visual	NONE	**NONE**	NONE	NONE
Silt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Debris	scalar	*Visual	NONE	**NONE**	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Appearance	scalar	*Visual	NORML	**NORML**	NORML	NORML
Odor	scalar	*Visual	NORML	**NORML**	NORML	NORML
Emulsified Water	scalar	*Visual	>0.05	**NEG**	NEG	NEG
Free Water	scalar	*Visual		**NEG**	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	217.7	**227.9**	218.2	214.1

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color					
Bottom					

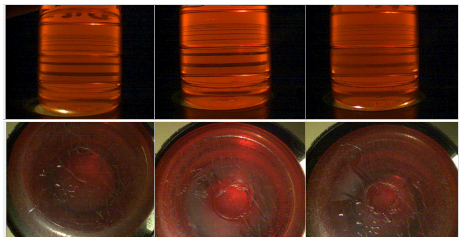

GRAPHS

Ferrous Alloys

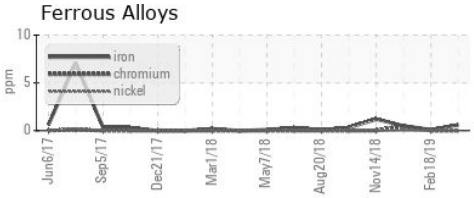

Non-ferrous Metals

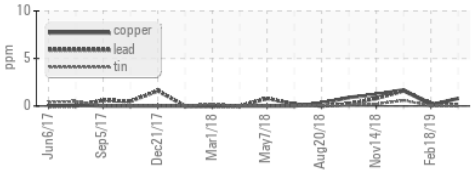

Viscosity @ 40°C

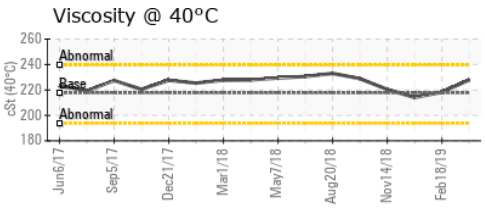

Particle Count

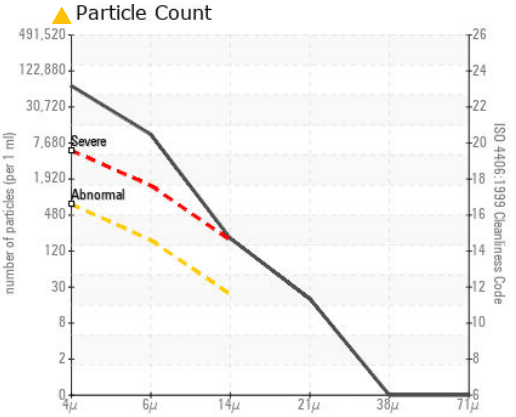

Acid Number

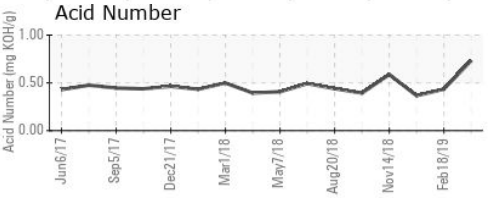

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0312509 **Recieved** : 05 Apr 2019
Lab Number : 04685670 **Diagnosed** : 08 Apr 2019
Unique Number : 8552186 **Diagnostician** : Jonathan Hester
Test Package : IND 2 (Additional Tests: KF, PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JAMES HARDIE BUILDING PRODUCTS - PULASKI
1000 JAMES HARDIE WAY
PULASKI, VA
US 24031
Contact: MICHAEL MITCHELL
mike.mitchell@jameshardie.com
T:
F: