




PROBLEM SUMMARY


Area
P2
 Machine Id
3521-A EVAPORATOR
 Component
Gearbox
 Fluid
MOBIL MOBILGEAR 600 XP ISO 150 (15 QTS)

Sample Rating Trend

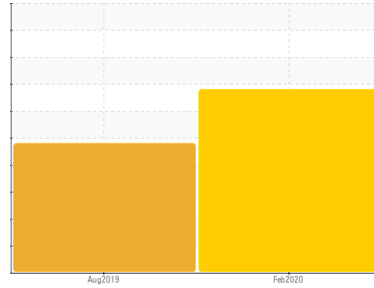


COMPONENT CONDITION SUMMARY

Ferrous Alloys

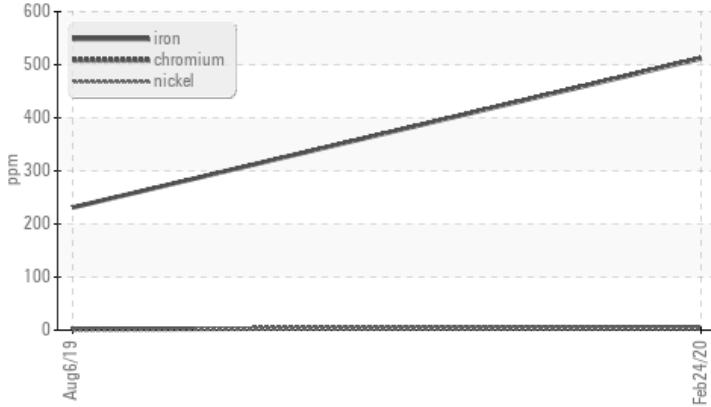

Particle Trend

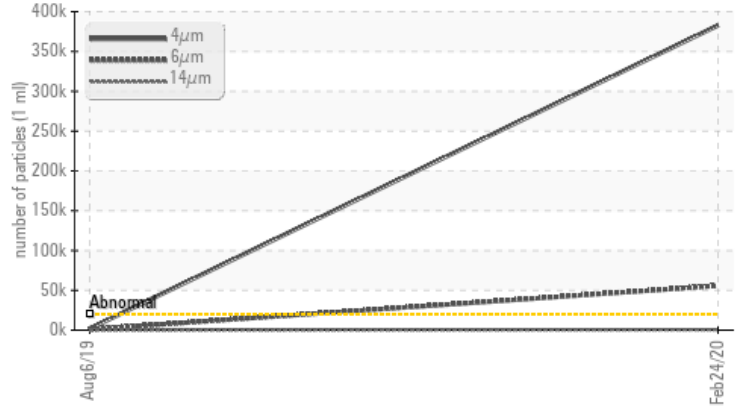

RECOMMENDATION

We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

PROBLEMATIC TEST RESULTS

Sample Status				SEVERE	ABNORMAL	---
Iron	ppm	ASTM D5185m	>200	512	231	---
Particles >4µm		ASTM D7647	>20000	382771	1820	---
Particles >6µm		ASTM D7647	>5000	55783	991	---
Oil Cleanliness		ISO 4406 (c)	>21/19/16	26/23/16	18/17/15	---

Customer Id: AJIRAL
 Sample No.: WC0425043
 Lab Number: 04920871
 Test Package: IND 2



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Doug Bogart +1 (800)237-1369 x4016
dougb@wearcheckusa.com

To change component or sample information:
 Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Inspect Wear Source	SKIPPED	Apr 17 2020	?	We advise that you inspect for the source(s) of wear.
Resample	SKIPPED	Apr 17 2020	?	We recommend an early resample to monitor this condition.

HISTORICAL DIAGNOSIS

06 Aug 2019 Diag: Jonathan Hester

WATER



We advise that you check for the source of water entry. We advise that you follow the water drain-off procedure for this component, and use off-line filtration to improve the cleanliness of the system fluid. We recommend an early resample to monitor this condition. Gear wear is indicated. Free water present. There is a moderate concentration of water present in the oil. The amount and size of particulates present in the system are acceptable. The AN level is acceptable for this fluid.


view report





OIL ANALYSIS REPORT

Sample Rating Trend

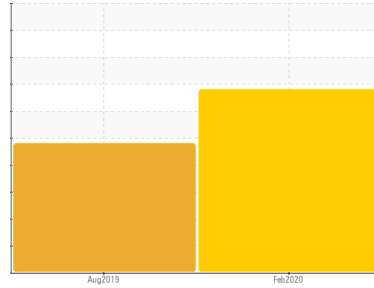

WEAR



Area
P2
 Machine Id
3521-A EVAPORATOR
 Component
Gearbox
 Fluid
MOBIL MOBILGEAR 600 XP ISO 150 (15 QTS)

DIAGNOSIS

Recommendation

We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

Wear

Gear wear is indicated.

Contamination

There is a high amount of silt (particulates < 14 microns in size) present in the oil.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		WC0425043	WC0368420	---
Sample Date	Client Info		24 Feb 2020	06 Aug 2019	---
Machine Age	hrs	Client Info	0	150	---
Oil Age	hrs	Client Info	150	150	---
Oil Changed	Client Info		Not Changd	Not Changd	---
Sample Status			SEVERE	ABNORMAL	---

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >200	512	231	---
Chromium	ppm	ASTM D5185m >15	5	2	---
Nickel	ppm	ASTM D5185m >15	3	1	---
Titanium	ppm	ASTM D5185m	1	<1	---
Silver	ppm	ASTM D5185m	0	0	---
Aluminum	ppm	ASTM D5185m >25	2	<1	---
Lead	ppm	ASTM D5185m >100	2	<1	---
Copper	ppm	ASTM D5185m >200	<1	2	---
Tin	ppm	ASTM D5185m >25	0	<1	---
Antimony	ppm	ASTM D5185m	207	108	---
Vanadium	ppm	ASTM D5185m	0	0	---
Cadmium	ppm	ASTM D5185m	0	<1	---

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	21	10	---
Barium	ppm	ASTM D5185m	0	0	---
Molybdenum	ppm	ASTM D5185m	<1	1	---
Manganese	ppm	ASTM D5185m	6	3	---
Magnesium	ppm	ASTM D5185m	1	<1	---
Calcium	ppm	ASTM D5185m	3	4	---
Phosphorus	ppm	ASTM D5185m	361	298	---
Zinc	ppm	ASTM D5185m	3	16	---
Sulfur	ppm	ASTM D5185m	14638	15686	---

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >50	4	<1	---
Sodium	ppm	ASTM D5185m	4	2	---
Potassium	ppm	ASTM D5185m >20	10	2	---
Water	%	ASTM D6304 >0.2	0.007	0.460	---
ppm Water	ppm	ASTM D6304 >2000	70.6	4600	---

FLUID CLEANLINESS






	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>20000	382771	1820	---
Particles >6µm	ASTM D7647	>5000	55783	991	---
Particles >14µm	ASTM D7647	>640	570	168	---
Particles >21µm	ASTM D7647	>160	143	57	---
Particles >38µm	ASTM D7647	>40	3	8	---
Particles >71µm	ASTM D7647	>10	0	0	---
Oil Cleanliness	ISO 4406 (c)	>21/19/16	26/23/16	18/17/15	---

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	0.669	0.659	---




OIL ANALYSIS REPORT

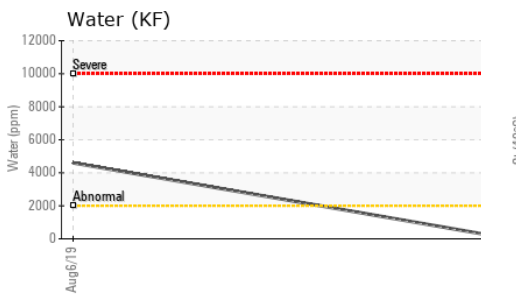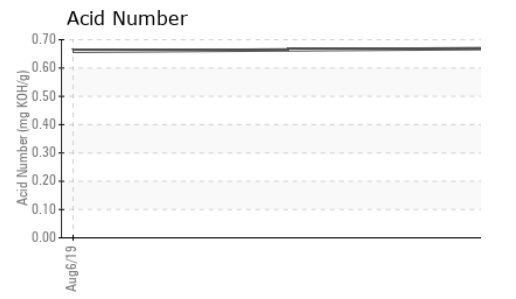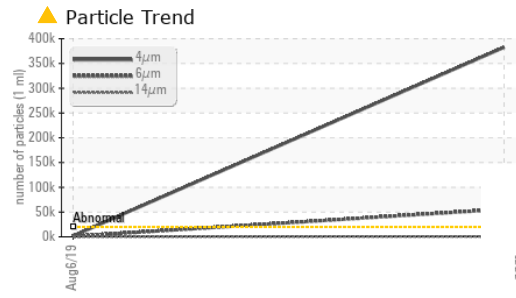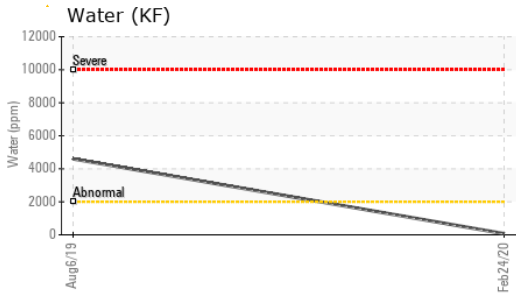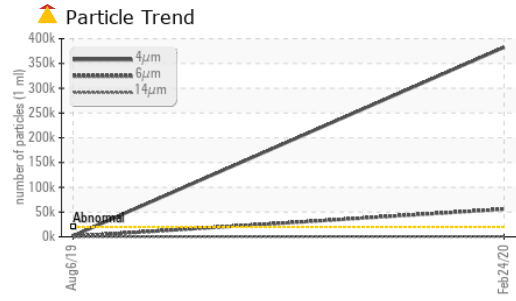





VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	---
Precipitate	scalar	*Visual	NONE	NONE	---
Silt	scalar	*Visual	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	MODER
Sand/Dirt	scalar	*Visual	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	▲ LAYRD
Odor	scalar	*Visual	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.2	NEG	0.2%
Free Water	scalar	*Visual		NEG	▲ 2.0

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	150	154	---

SAMPLE IMAGES	method	limit/base	current	history1	history2
---------------	--------	------------	---------	----------	----------

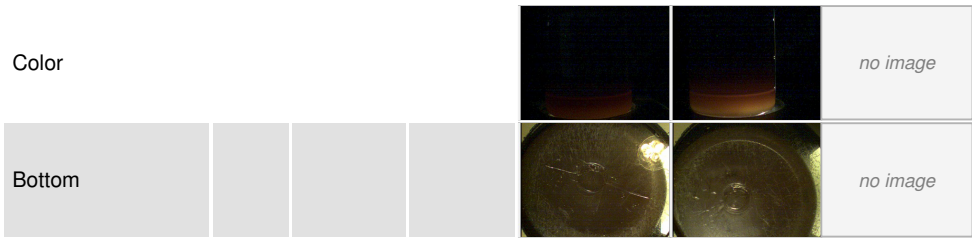

GRAPHS

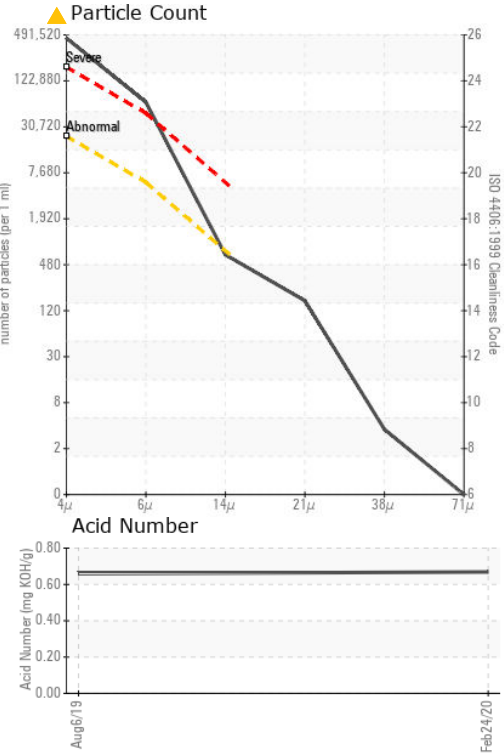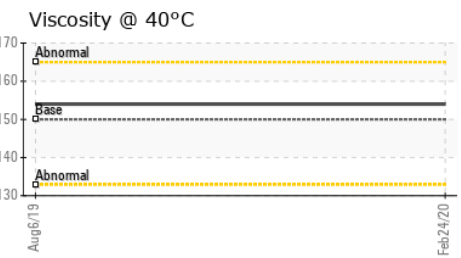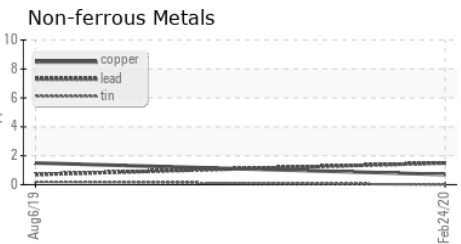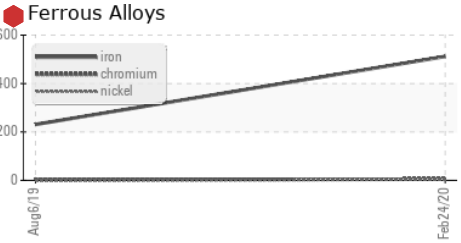

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0425043 **Received** : 26 Feb 2020
Lab Number : 04920871 **Diagnosed** : 27 Feb 2020
Unique Number : 8935950 **Diagnostician** : Doug Bogart
Test Package : IND 2 (Additional Tests: KF, PQ, PrtCount)

AJINOMOTO USA
 4020 AJINOMOTO DRIVE
 RALEIGH, NC
 US 27610
 Contact: Michael Thompson
 thompsonm@ajiusa.com
 T: (919)723-2142
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)