



OIL ANALYSIS REPORT

Sample Rating Trend



ISO



Machine Id
7288984 (S/N 1515)

Component
Compressor
Fluid
KAESER SIGMA (OEM) S-460 (--- GAL)

DIAGNOSIS

▲ Recommendation

We recommend you service the filters on this component. Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

▲ Contamination

There is a high amount of particulates present in the oil.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	KC72576	---	---
Sample Date	Client Info	05 Mar 2020	---	---
Machine Age	hrs	Client Info	526	---
Oil Age	hrs	Client Info	526	---
Oil Changed	Client Info	Not Chngd	---	---
Sample Status		ABNORMAL	---	---

WEAR METALS

method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >50	1	---
Chromium	ppm	ASTM D5185m >10	0	---
Nickel	ppm	ASTM D5185m >3	0	---
Titanium	ppm	ASTM D5185m >3	0	---
Silver	ppm	ASTM D5185m >2	0	---
Aluminum	ppm	ASTM D5185m >10	<1	---
Lead	ppm	ASTM D5185m >10	<1	---
Copper	ppm	ASTM D5185m >50	1	---
Tin	ppm	ASTM D5185m >10	0	---
Antimony	ppm	ASTM D5185m	0	---
Vanadium	ppm	ASTM D5185m	0	---
Cadmium	ppm	ASTM D5185m	0	---

ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	<1	---
Barium	ppm	ASTM D5185m 90	82	---
Molybdenum	ppm	ASTM D5185m	0	---
Manganese	ppm	ASTM D5185m	<1	---
Magnesium	ppm	ASTM D5185m 90	89	---
Calcium	ppm	ASTM D5185m 2	2	---
Phosphorus	ppm	ASTM D5185m	1	---
Zinc	ppm	ASTM D5185m	2	---

CONTAMINANTS

method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	2	---
Sodium	ppm	ASTM D5185m	8	---
Potassium	ppm	ASTM D5185m >20	8	---
Water	%	ASTM D6304 >0.05	0.005	---
ppm Water	ppm	ASTM D6304 >500	53.5	---






FLUID CLEANLINESS

method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	22238	---	---
Particles >6µm	ASTM D7647 >1300	▲ 12303	---	---
Particles >14µm	ASTM D7647 >80	▲ 2799	---	---
Particles >21µm	ASTM D7647 >20	▲ 939	---	---
Particles >38µm	ASTM D7647 >4	▲ 42	---	---
Particles >71µm	ASTM D7647 >3	1	---	---
Oil Cleanliness	ISO 4406 (c) >--/17/13	▲ 21/19	---	---

FLUID DEGRADATION

method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045 0.4	0.379	---

OIL ANALYSIS REPORT

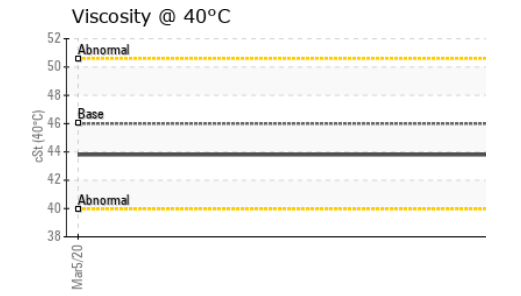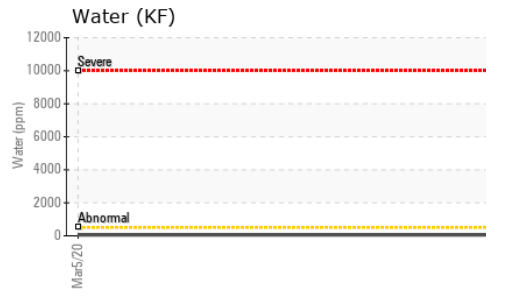
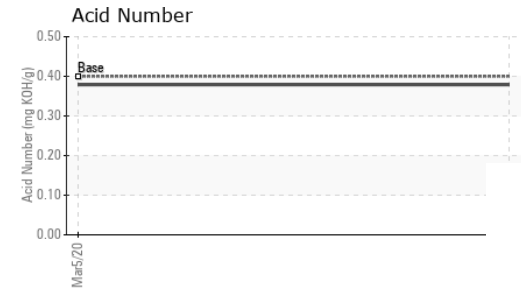
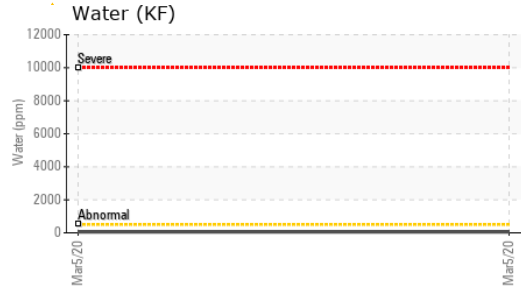
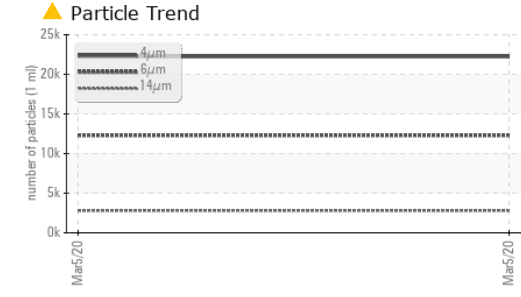


PARAMETER	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	LIGHT	---
Yellow Metal	scalar	*Visual	NONE	NONE	---
Precipitate	scalar	*Visual	NONE	NONE	---
Silt	scalar	*Visual	NONE	NONE	---
Debris	scalar	*Visual	NONE	LIGHT	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.05	NEG	---
Free Water	scalar	*Visual		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	46	43.8	---

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color				no image	no image
Bottom				no image	no image

GRAPHS

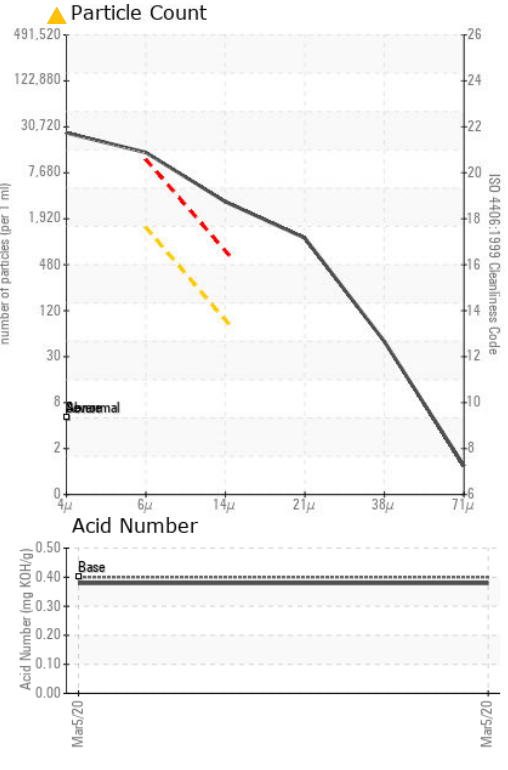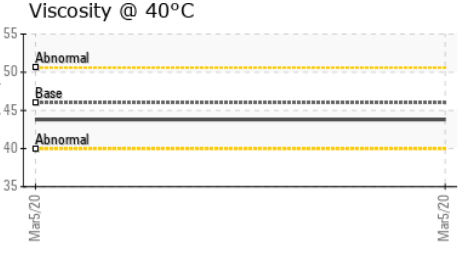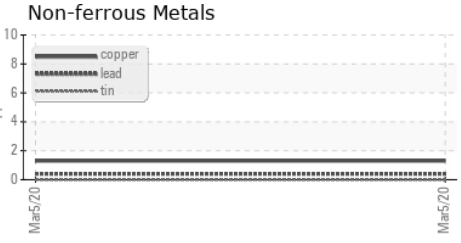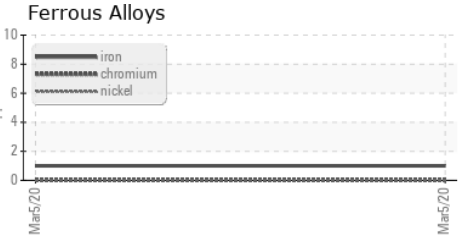

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : KC72576 **Received** : 11 Mar 2020
Lab Number : 04931319 **Diagnosed** : 13 Mar 2020
Unique Number : 8956415 **Diagnostician** : Jonathan Hester
Test Package : IND 2

ACHILLIES AEROSPACE
 2100 ENTERPRISE PKWY
 TWINSBURG, OH
 US 44087
 Contact: Service Manager

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)