OIL ANALYSIS REPORT

Sample Rating Trend

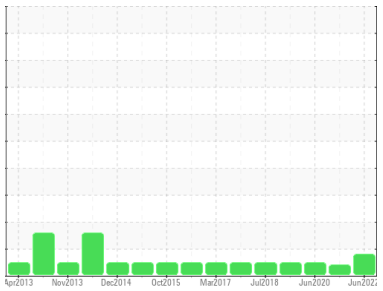

WEAR

Area
EVA CREEK
Machine Id
WEC 14 - 91977 (S/N 26113)
Component
Wind Turbine Gearbox
Fluid
CASTROL OPTIGEAR SYNTHETIC A ISO 320 (475 GAL)

DIAGNOSIS

Recommendation
No corrective action is recommended at this time. We recommend an early resample to monitor this condition.

Wear
Gear wear is indicated.

Contamination
There is no indication of any contamination in the oil. The amount and size of particulates present in the system are acceptable.

Fluid Condition
The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number		Client Info		**WC0634818**	WC0544197	WC0373049
Sample Date		Client Info		**01 Jun 2022**	29 Jul 2021	03 Jun 2020
Machine Age	hrs	Client Info		**79043**	74129	66097
Oil Age	hrs	Client Info		**0**	74129	66097
Oil Changed		Client Info		**N/A**	Not Changd	Not Changd
Sample Status				**ABNORMAL**	ATTENTION	NORMAL

WEAR METALS		method	limit/base	current	history1	history2
PQ		ASTM D8184	>80	**27**	36	29
Iron	ppm	ASTM D5185m	>90	▲ **245**	247	204
Chromium	ppm	ASTM D5185m	>4	**4**	4	3
Nickel	ppm	ASTM D5185m	>3	**0**	<1	0
Titanium	ppm	ASTM D5185m		**0**	<1	<1
Silver	ppm	ASTM D5185m		**<1**	0	0
Aluminum	ppm	ASTM D5185m	>10	**2**	2	1
Lead	ppm	ASTM D5185m	>11	**<1**	<1	<1
Copper	ppm	ASTM D5185m	>55	**6**	6	5
Tin	ppm	ASTM D5185m	>10	**0**	<1	0
Antimony	ppm	ASTM D5185m		**---**	0	0
Vanadium	ppm	ASTM D5185m		**<1**	<1	<1
Cadmium	ppm	ASTM D5185m		**0**	<1	<1

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	0	**2**	6	2
Barium	ppm	ASTM D5185m	0	**4**	0	3
Molybdenum	ppm	ASTM D5185m	1150	**1186**	1275	1155
Manganese	ppm	ASTM D5185m		**4**	3	3
Magnesium	ppm	ASTM D5185m	1800	**1820**	1931	1724
Calcium	ppm	ASTM D5185m	20	**15**	17	14
Phosphorus	ppm	ASTM D5185m	1450	**1382**	1494	1282
Zinc	ppm	ASTM D5185m	1650	**1638**	1729	1455
Sulfur	ppm	ASTM D5185m	4900	**5768**	5956	4927

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>35	**17**	16	17
Sodium	ppm	ASTM D5185m	>25	**6**	6	6
Potassium	ppm	ASTM D5185m	>20	**0**	2	2
Water	%	ASTM D6304	>.110	**0.052**	0.048	0.018
ppm Water	ppm	ASTM D6304	>1100	**524.6**	483.8	182.1

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>2500	**406**	3466	579
Particles >6µm		ASTM D7647	>640	**68**	159	101
Particles >14µm		ASTM D7647	>80	**9**	10	25
Particles >21µm		ASTM D7647	>20	**4**	5	20
Particles >38µm		ASTM D7647	>4	**1**	0	2
Particles >71µm		ASTM D7647	>3	**0**	0	0
Oil Cleanliness		ISO 4406 (c)	>18/16/13	**16/13/10**	19/14/10	16/14/12

OIL ANALYSIS REPORT

Water (KF)

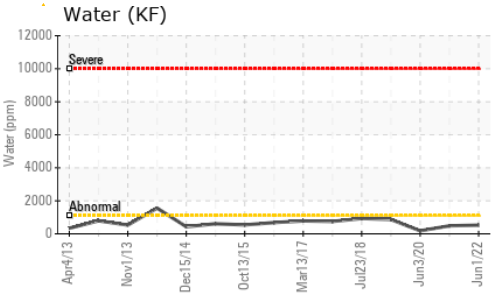

PQ

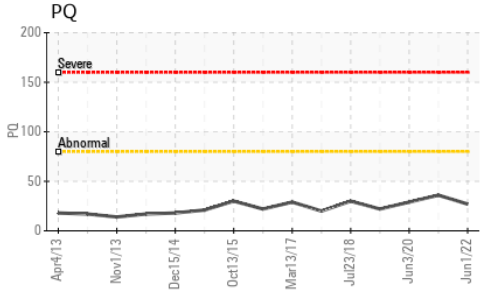

Particle Trend

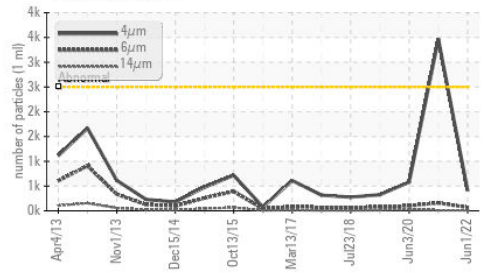

Water (KF)

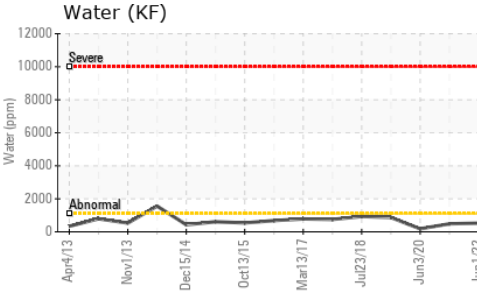

Viscosity @ 40°C

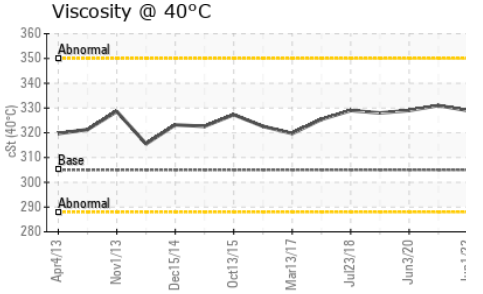

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	3.3	**2.33**	3.221	2.774

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	**NONE**	LIGHT	NONE
Yellow Metal	scalar	*Visual	NONE	**NONE**	NONE	NONE
Precipitate	scalar	*Visual	NONE	**NONE**	NONE	NONE
Silt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Debris	scalar	*Visual	NONE	**NONE**	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	**NONE**	NONE	NONE
Appearance	scalar	*Visual	NORML	**NORML**	NORML	NORML
Odor	scalar	*Visual	NORML	**NORML**	NORML	NORML
Emulsified Water	scalar	*Visual	>.110	**NEG**	NEG	NEG
Free Water	scalar	*Visual		**NEG**	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	305	**329**	331	329

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color					
Bottom					

GRAPHS

Ferrous Alloys

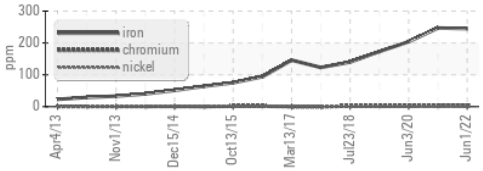

Non-ferrous Metals

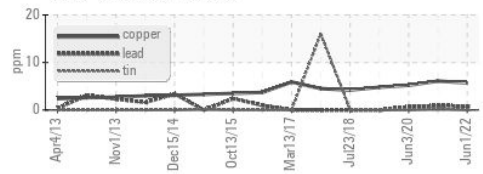

Viscosity @ 40°C

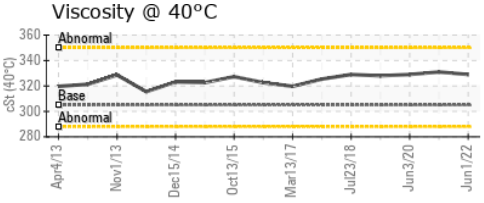

Particle Count

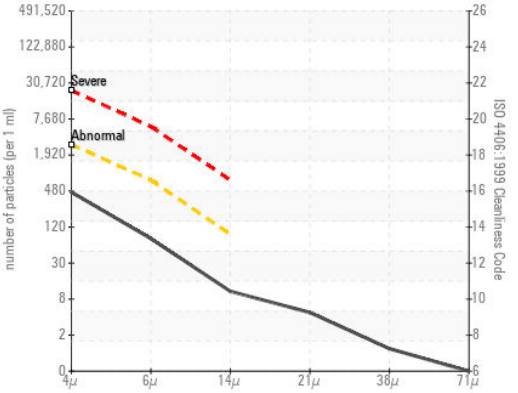

Acid Number

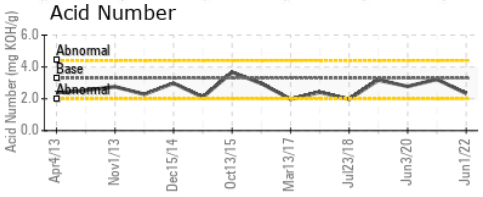

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0634818 **Received** : 16 Jun 2022
Lab Number : 05570060 **Tested** : 17 Jun 2022
Unique Number : 10019477 **Diagnosed** : 17 Jun 2022 - Jonathan Hester
Test Package : IND 2 (Additional Tests: KF, PQ, PrtCount)

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

GOLDEN VALLEY ELECTRIC
MILE 2.5 HEALY SPUR RD
HEALY, AK
US 99743
Contact: RYAN DEWITT
rjdewitt@gvea.com
T:
F: