




# OIL ANALYSIS REPORT

Sample Rating Trend

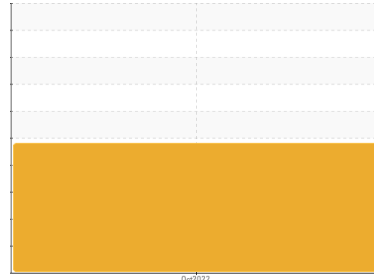

Machine Id  
**JK1539-L05**  
 Component  
**Gasoline Engine**  
 Fluid  
**PENZOIL 0W30 (--- QTS)**

## DIAGNOSIS

**Recommendation**  
 We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. The oil is near the end of its useful service life, recommend schedule an oil change. Resample at the next service interval to monitor. Please note that this is a corrected copy for laboratory data updates.

**Wear**  
 All component wear rates are normal.

**Contamination**  
 Fuel content negligible. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. The water content is negligible.

**Fluid Condition**  
 The BN level is low. The AN level is at the top-end of the recommended limit.

## SAMPLE INFORMATION

	method	limit/base	current	history 1	history 2
Sample Number	Client Info		<b>WC0751538</b>	---	---
Sample Date	Client Info		<b>18 Oct 2022</b>	---	---
Machine Age	kms	Client Info	<b>68856</b>	---	---
Oil Age	kms	Client Info	<b>41047</b>	---	---
Oil Changed	Client Info		<b>Not Chngd</b>	---	---
Sample Status			<b>ABNORMAL</b>	---	---

## CONTAMINATION

	method	limit/base	current	history 1	history 2
Glycol	WC Method		<b>NEG</b>	---	---

## WEAR METALS

	method	limit/base	current	history 1	history 2
Iron	ppm	ASTM D5185m >150	<b>25</b>	---	---
Chromium	ppm	ASTM D5185m >20	<b>&lt;1</b>	---	---
Nickel	ppm	ASTM D5185m >5	<b>&lt;1</b>	---	---
Titanium	ppm	ASTM D5185m	<b>8</b>	---	---
Silver	ppm	ASTM D5185m >2	<b>0</b>	---	---
Aluminum	ppm	ASTM D5185m >40	<b>▲ 11</b>	---	---
Lead	ppm	ASTM D5185m >50	<b>&lt;1</b>	---	---
Copper	ppm	ASTM D5185m >155	<b>9</b>	---	---
Tin	ppm	ASTM D5185m >10	<b>&lt;1</b>	---	---
Vanadium	ppm	ASTM D5185m	<b>&lt;1</b>	---	---
Cadmium	ppm	ASTM D5185m	<b>0</b>	---	---

## ADDITIVES

	method	limit/base	current	history 1	history 2
Boron	ppm	ASTM D5185m	<b>109</b>	---	---
Barium	ppm	ASTM D5185m	<b>0</b>	---	---
Molybdenum	ppm	ASTM D5185m	<b>22</b>	---	---
Manganese	ppm	ASTM D5185m	<b>2</b>	---	---
Magnesium	ppm	ASTM D5185m	<b>30</b>	---	---
Calcium	ppm	ASTM D5185m	<b>1623</b>	---	---
Phosphorus	ppm	ASTM D5185m	<b>574</b>	---	---
Zinc	ppm	ASTM D5185m	<b>850</b>	---	---
Sulfur	ppm	ASTM D5185m	<b>2012</b>	---	---

## CONTAMINANTS






	method	limit/base	current	history 1	history 2
Silicon	ppm	ASTM D5185m >30	<b>▲ 50</b>	---	---
Sodium	ppm	ASTM D5185m >400	<b>2</b>	---	---
Potassium	ppm	ASTM D5185m >20	<b>1</b>	---	---
Fuel	%	ASTM D3524 >4.0	<b>1.9</b>	---	---
Water	%	ASTM D6304 >0.2	<b>0.044</b>	---	---
ppm Water	ppm	ASTM D6304 >2000	<b>441.6</b>	---	---

## INFRA-RED

	method	limit/base	current	history 1	history 2
Soot %	%	*ASTM D7844	<b>0.1</b>	---	---
Nitration	Abs/cm	*ASTM D7624 >20	<b>16.6</b>	---	---
Sulfation	Abs/.1mm	*ASTM D7415 >30	<b>30.6</b>	---	---



# OIL ANALYSIS REPORT




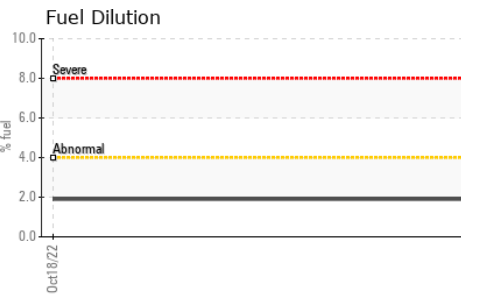
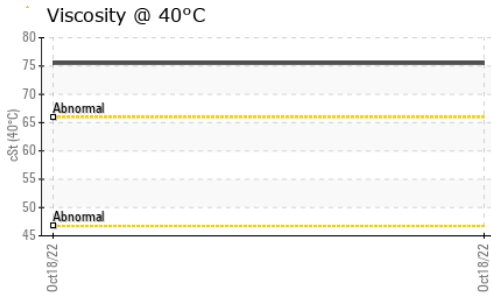
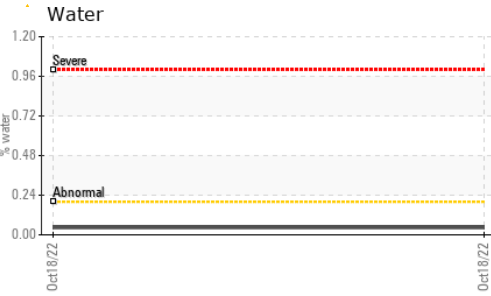
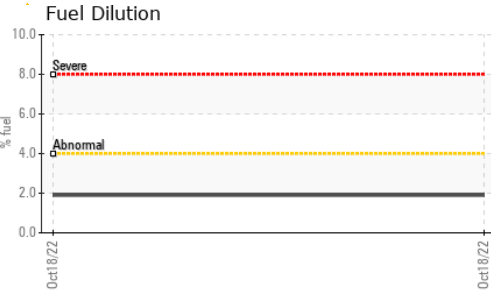
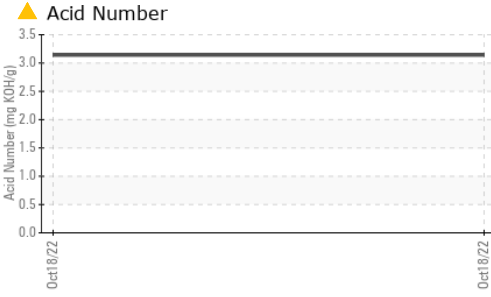


FLUID DEGRADATION		method	limit/base	current	history 1	history 2
Oxidation	Abs./1mm	*ASTM D7414	>25	<b>37.1</b>	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045		<b>▲ 3.14</b>	---	---
Base Number (BN)	mg KOH/g	ASTM D2896		<b>▲ 3.02</b>	---	---

VISUAL		method	limit/base	current	history 1	history 2
White Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---
Precipitate	scalar	*Visual	NONE	<b>NONE</b>	---	---
Silt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Debris	scalar	*Visual	NONE	<b>NONE</b>	---	---
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Appearance	scalar	*Visual	NORML	<b>NORML</b>	---	---
Odor	scalar	*Visual	NORML	<b>NORML</b>	---	---
Emulsified Water	scalar	*Visual	>0.2	<b>NEG</b>	---	---
Free Water	scalar	*Visual		<b>NEG</b>	---	---

FLUID PROPERTIES		method	limit/base	current	history 1	history 2
Visc @ 40°C	cSt	ASTM D445		<b>75.5</b>	---	---
Visc @ 100°C	cSt	ASTM D445		<b>12.7</b>	---	---
Viscosity Index (VI)	Scale	ASTM D2270		<b>168</b>	---	---

### GRAPHS

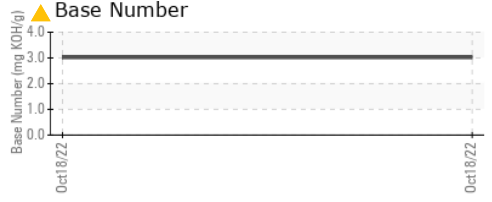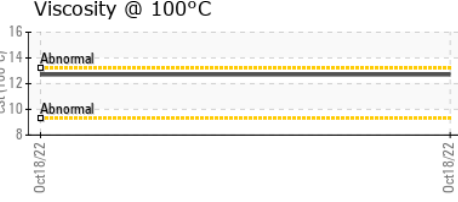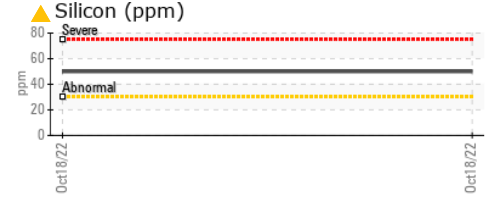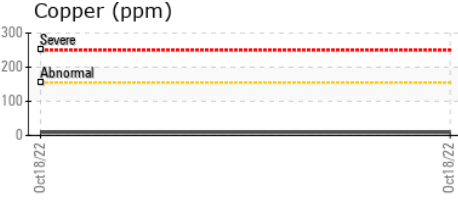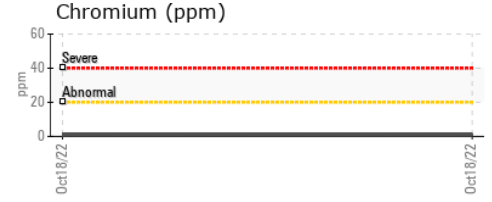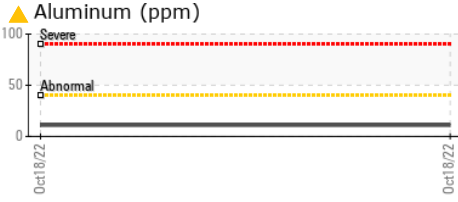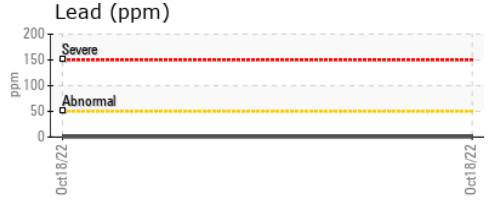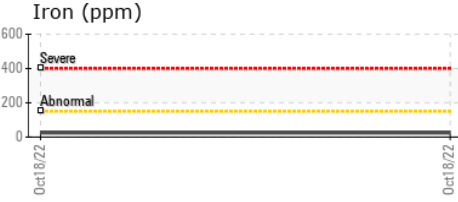

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : WC0751538 **Received** : 09 Nov 2022  
**Lab Number** : 05689750 **Diagnosed** : 15 Nov 2022  
**Unique Number** : 10214323 **Diagnostician** : Jonathan Hester  
**Test Package** : MOB 2 ( Additional Tests: fueldilution, KF, KV40, PercentFuel, TBN, VI )

**AVL POWERTRAIN ENGINEERING INC**  
 47519 HALYARD DRIVE  
 PLYMOUTH, MI  
 US 48170-2438  
 Contact: Service Manager

To discuss this sample report, contact Customer Service at 1-800-237-1369.  
 \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.  
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)