




OIL ANALYSIS REPORT

Sample Rating Trend

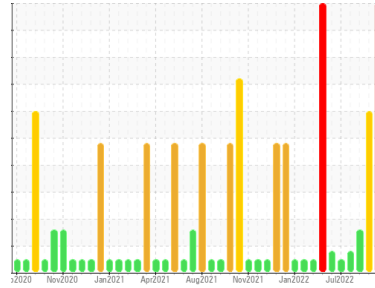

WEAR



Machine Id
COVM03BE (S/N GZJ00181)
 Component
Biogas Engine
 Fluid
CHEVRON HDAX 6500 LFG GAS ENGINE OIL (141 GAL)

DIAGNOSIS

Recommendation

We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

Wear

The iron level is severe. Cylinder, crank, or cam shaft wear is indicated. Valve wear is indicated.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The AN level is acceptable for this fluid.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		WC0722557	WC05625791	WC0722528
Sample Date	Client Info		18 Jan 2023	12 Aug 2022	05 Aug 2022
Machine Age	hrs	Client Info	124098	123481	123466
Oil Age	hrs	Client Info	873	3020	3005
Oil Changed	Client Info		Not Chngd	N/A	N/A
Sample Status			SEVERE	SEVERE	ABNORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>4.0	<1.0	<1.0	<1.0
Glycol	WC Method		NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >15	85	77	8
Chromium	ppm	ASTM D5185m >4	<1	1	<1
Nickel	ppm	ASTM D5185m >2	6	4	<1
Titanium	ppm	ASTM D5185m	0	0	0
Silver	ppm	ASTM D5185m >5	<1	1	<1
Aluminum	ppm	ASTM D5185m >6	2	4	3
Lead	ppm	ASTM D5185m >9	<1	2	2
Copper	ppm	ASTM D5185m >6	2	3	2
Tin	ppm	ASTM D5185m >4	1	2	4
Vanadium	ppm	ASTM D5185m	0	0	0
Cadmium	ppm	ASTM D5185m	0	<1	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	9	31	9
Barium	ppm	ASTM D5185m	0	<1	0
Molybdenum	ppm	ASTM D5185m	6	11	4
Manganese	ppm	ASTM D5185m	1	1	<1
Magnesium	ppm	ASTM D5185m	27	30	28
Calcium	ppm	ASTM D5185m	1539	1461	1449
Phosphorus	ppm	ASTM D5185m	313	305	307
Zinc	ppm	ASTM D5185m	369	374	370
Sulfur	ppm	ASTM D5185m	2874	2530	2841

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >181	63	72	196
Sodium	ppm	ASTM D5185m	2	8	0
Potassium	ppm	ASTM D5185m >20	2	3	0

INFRA-RED

	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844	0	0.1	0.1
Nitration	Abs/cm	*ASTM D7624 >20	3.7	4.5	4.4
Sulfation	Abs/.1mm	*ASTM D7415 >30	16.0	18.3	17.9


FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	7.8	9.3	9.1
Acid Number (AN)	mg KOH/g	ASTM D8045 1.2	0.54	1.07	0.89
Base Number (BN)	mg KOH/g	ASTM D2896 4.5	4.47	4.18	4.21




OIL ANALYSIS REPORT


Ferrous Alloys

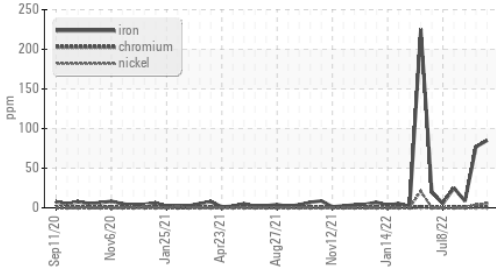


Acid Number

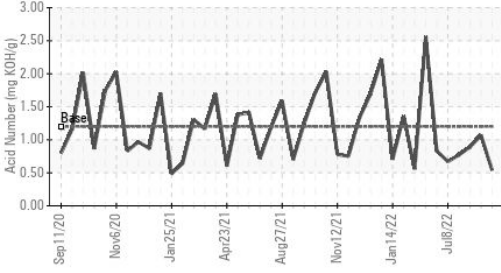

Base Number

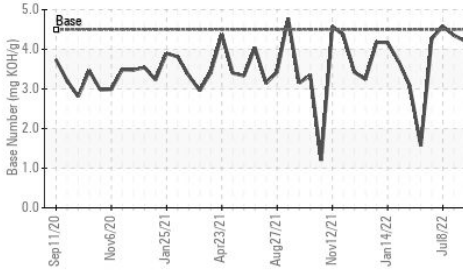

Viscosity @ 100°C

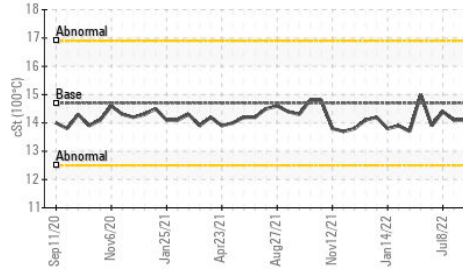


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	14.7	14.2	13.8

GRAPHS


Iron (ppm)

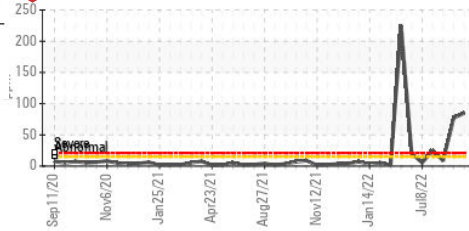


Aluminum (ppm)

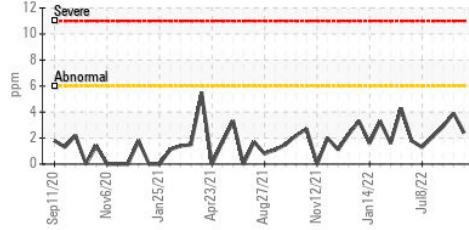


Copper (ppm)

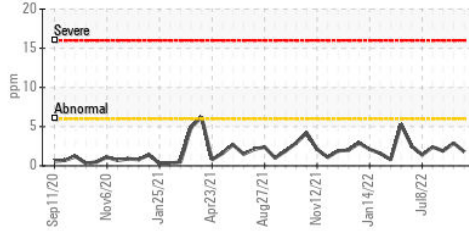


Viscosity @ 100°C

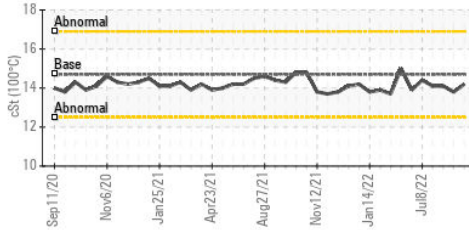


Lead (ppm)

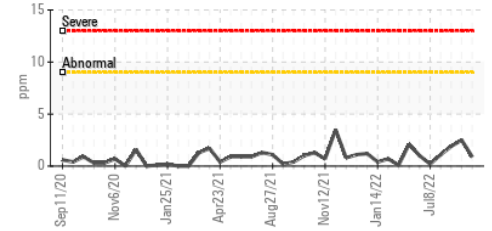


Chromium (ppm)

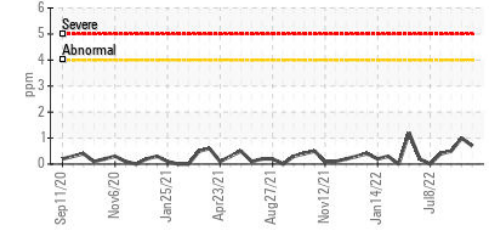

Silicon (ppm)

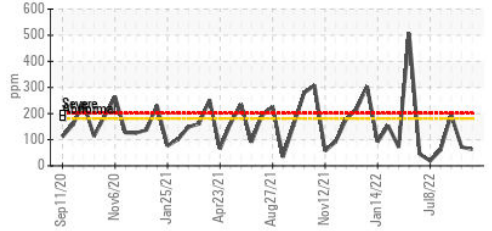

Base Number

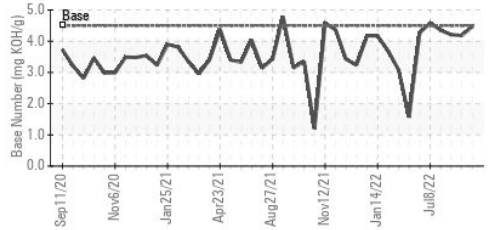

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
 Sample No. : WC0722557
 Lab Number : 05744744
 Unique Number : 10299343
 Test Package : MOB 2

Received : 20 Jan 2023
 Diagnosed : 23 Jan 2023
 Diagnostician : Don Baldrige

EDL NA Recips-Covel
 COVEL GARDENS POWER STATION, 8611 COVEL ROAD
 SAN ANTONIO, TX
 US 78252
 Contact: ARIEL CARRION
 ariel.carrion@edlenergy.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:
F: