




OIL ANALYSIS REPORT

Sample Rating Trend

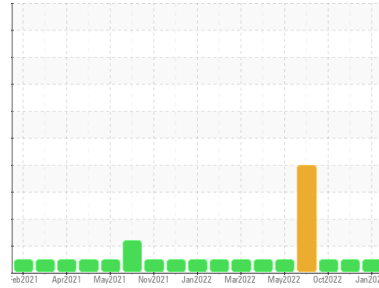

NORMAL



Area
GUAY SON/Yavaros [CONHER]
 Machine Id
Pacifico Industrial - PISA2 Aux1
 Component
Diesel Engine
 Fluid
CHEVRON DELO 400 SDE SAE 15W40 (40 LTR)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		KL0010217	KL0011316	KL0011192
Sample Date	Client Info		16 Jan 2023	15 Nov 2022	16 Oct 2022
Machine Age	hrs	Client Info	39366	38766	38266
Oil Age	hrs	Client Info	1300	700	200
Oil Changed	Client Info		Changed	Changed	Not Changed
Sample Status			NORMAL	NORMAL	NORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<1.0	<1.0	<1.0
Water	WC Method	>0.2	NEG	NEG	NEG
Glycol	WC Method		NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185m	>250	76	66	28
Chromium	ppm	ASTM D5185m	>10	1	1	2
Nickel	ppm	ASTM D5185m	>5	0	<1	<1
Titanium	ppm	ASTM D5185m		0	0	<1
Silver	ppm	ASTM D5185m	>3	0	0	4
Aluminum	ppm	ASTM D5185m	>35	2	3	2
Lead	ppm	ASTM D5185m	>100	4	4	4
Copper	ppm	ASTM D5185m	>60	10	11	14
Tin	ppm	ASTM D5185m	>5	<1	1	2
Vanadium	ppm	ASTM D5185m		0	<1	<1
Cadmium	ppm	ASTM D5185m		0	0	<1

ADDITIVES

	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185m		181	177	328
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		135	118	106
Manganese	ppm	ASTM D5185m		<1	<1	2
Magnesium	ppm	ASTM D5185m		612	614	583
Calcium	ppm	ASTM D5185m		1492	1539	1410
Phosphorus	ppm	ASTM D5185m	760	691	674	615
Zinc	ppm	ASTM D5185m	800	886	819	745
Sulfur	ppm	ASTM D5185m	3000	2556	2643	2485

CONTAMINANTS

	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185m	>35	16	19	24
Sodium	ppm	ASTM D5185m		3	<1	4
Potassium	ppm	ASTM D5185m	>20	2	<1	2

INFRA-RED



	method	limit/base	current	history1	history2	
Soot %	%	*ASTM D7844	>3	1.9	1.7	1
Nitration	Abs/cm	*ASTM D7624	>20	12.0	11.5	9.1
Sulfation	Abs/.1mm	*ASTM D7415	>30	28.1	27.3	27.1

FLUID DEGRADATION

	method	limit/base	current	history1	history2	
Oxidation	Abs/.1mm	*ASTM D7414	>25	22.8	21.6	21.3
Base Number (BN)	mg KOH/g	ASTM D2896	10	7.9	7.80	7.38







OIL ANALYSIS REPORT

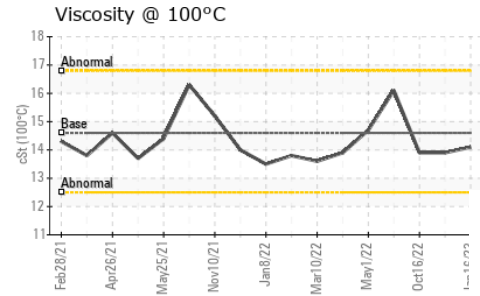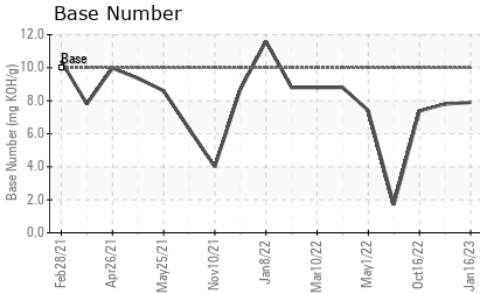

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	14.6	14.1	13.9

GRAPHS

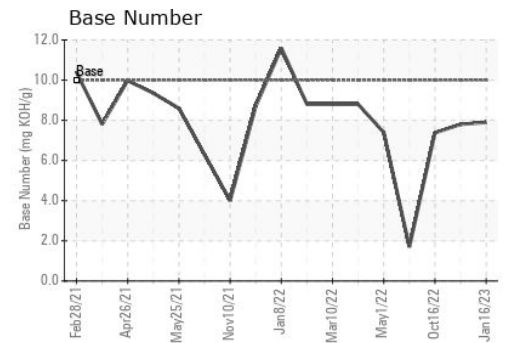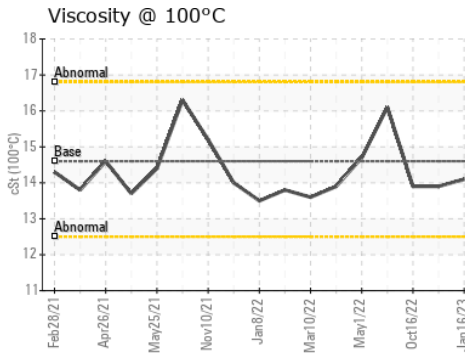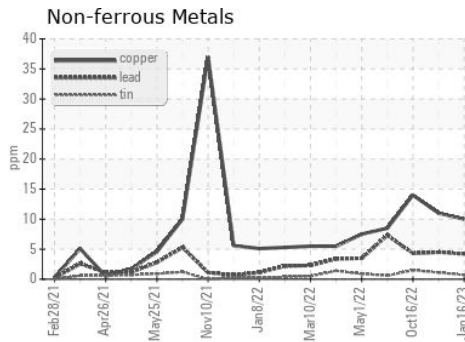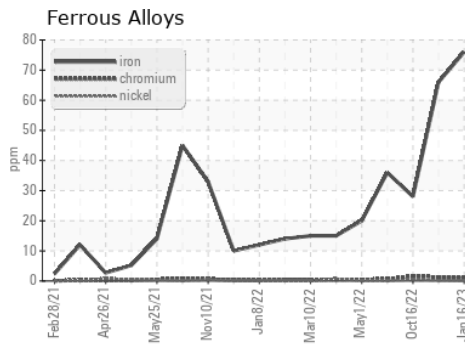

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : KL0010217
Lab Number : 05755975
Unique Number : 10320582
Test Package : FLEET
Received : 01 Feb 2023
Tested : 02 Feb 2023
Diagnosed : 02 Feb 2023 - Angela Borella

CONOR
 JUAREZ 348
 HERMOSILLO,
 MX 83140

Contact: EDUARDO GARCIA
 egarcia.comsa@gmail.com

T: (526)622-1581 x:81

F: x:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)