




# OIL ANALYSIS REPORT

Area  
**OKLAHOMA/102/EG - DOZER**  
 Machine Id  
**35.101L [OKLAHOMA^102^EG - DOZER]**  
 Component  
**Diesel Engine**  
 Fluid  
**MOBIL DELVAC 1300 SUPER15W40 (--- GAL)**

Sample Rating Trend

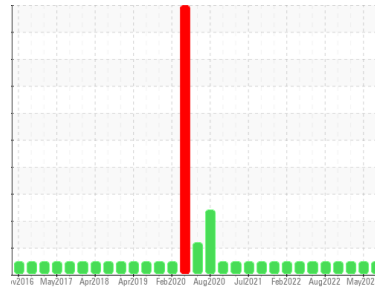

**NORMAL**



## DIAGNOSIS

### Recommendation

Resample at the next service interval to monitor. ( Customer Sample Comment: 8667 hrs )

### Wear

All component wear rates are normal.

### Contamination

There is no indication of any contamination in the oil.

### Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

## SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		<b>WC0819874</b>	WC0746722	WC0603256
Sample Date	Client Info		<b>17 Jul 2023</b>	10 May 2023	17 Feb 2023
Machine Age	hrs	Client Info	<b>8667</b>	8356	7980
Oil Age	hrs	Client Info	<b>6477</b>	6477	6477
Oil Changed	Client Info		<b>N/A</b>	N/A	N/A
Sample Status			<b>NORMAL</b>	NORMAL	NORMAL

## CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<b>&lt;1.0</b>	<1.0	<1.0
Glycol	WC Method		<b>NEG</b>	NEG	NEG

## WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >100	<b>16</b>	17	12
Chromium	ppm	ASTM D5185m >20	<b>&lt;1</b>	<1	<1
Nickel	ppm	ASTM D5185m >2	<b>0</b>	0	0
Titanium	ppm	ASTM D5185m >2	<b>0</b>	<1	0
Silver	ppm	ASTM D5185m >2	<b>0</b>	0	0
Aluminum	ppm	ASTM D5185m >25	<b>6</b>	1	4
Lead	ppm	ASTM D5185m >40	<b>0</b>	0	<1
Copper	ppm	ASTM D5185m >330	<b>&lt;1</b>	6	1
Tin	ppm	ASTM D5185m >15	<b>&lt;1</b>	<1	<1
Vanadium	ppm	ASTM D5185m	<b>0</b>	0	0
Cadmium	ppm	ASTM D5185m	<b>0</b>	0	0

## ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 0	<b>38</b>	38	49
Barium	ppm	ASTM D5185m 0	<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185m 0	<b>44</b>	40	38
Manganese	ppm	ASTM D5185m	<b>&lt;1</b>	<1	<1
Magnesium	ppm	ASTM D5185m 0	<b>566</b>	579	523
Calcium	ppm	ASTM D5185m	<b>1782</b>	1793	1633
Phosphorus	ppm	ASTM D5185m	<b>757</b>	775	713
Zinc	ppm	ASTM D5185m	<b>977</b>	978	873
Sulfur	ppm	ASTM D5185m	<b>2940</b>	2727	2815

## CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	<b>5</b>	6	4
Sodium	ppm	ASTM D5185m	<b>8</b>	6	6
Potassium	ppm	ASTM D5185m >20	<b>1</b>	1	0

## INFRA-RED



	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >3	<b>0.4</b>	0.4	0.3
Nitration	Abs/cm	*ASTM D7624 >20	<b>8.1</b>	8.3	8.7
Sulfation	Abs.1mm	*ASTM D7415 >30	<b>22.4</b>	22.7	21.8

## FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs.1mm	*ASTM D7414 >25	<b>20.3</b>	20.9	16.6
Base Number (BN)	mg KOH/g	ASTM D2896 9.4	<b>9.2</b>	9.4	8.7







# OIL ANALYSIS REPORT

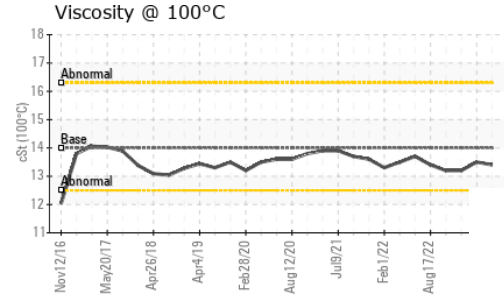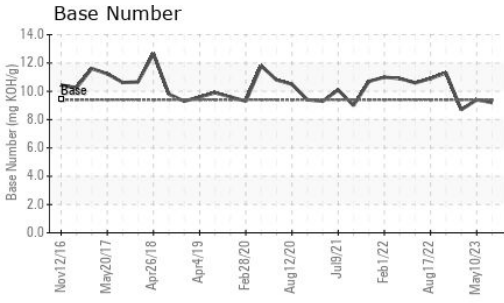

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 100°C	cSt	ASTM D445	14	<b>13.4</b>	13.5	13.2

## GRAPHS

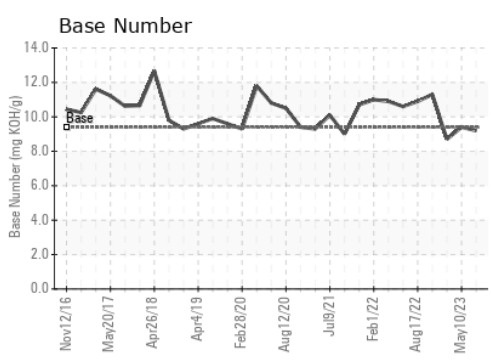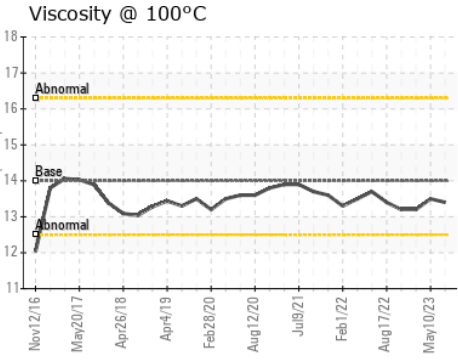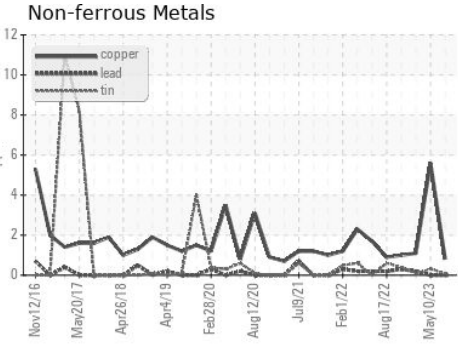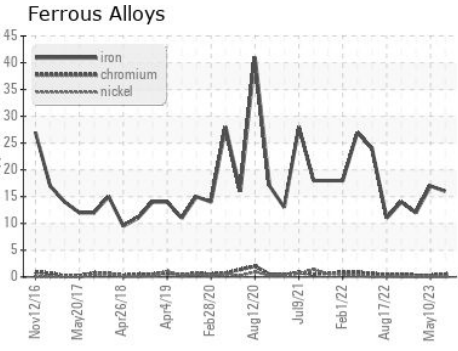

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : WC0819874 **Received** : 20 Jul 2023  
**Lab Number** : **05903661** **Diagnosed** : 24 Jul 2023  
**Unique Number** : 10565017 **Diagnostician** : Don Baldrige  
**Test Package** : CONST ( Additional Tests: TBN )

**SHERWOOD CONSTRUCTION CO INC**  
 3219 WEST MAY ST  
 WICHITA, KS  
 US 67213  
 Contact: DOUG KING  
 doug.king@sherwood.net  
 T: (316)617-3161  
 F: x:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)