

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Filter	---	---	?	We recommend you service the filters on this component.

HISTORICAL DIAGNOSIS

15 Aug 2023 Diag: Jonathan Hester

ISO



We recommend you service the filters on this component. Resample at the next service interval to monitor. All component wear rates are normal. There is a high amount of particulates present in the oil. The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

view report



14 Aug 2023 Diag: Jonathan Hester

ISO



We recommend you service the filters on this component. Resample at the next service interval to monitor. All component wear rates are normal. There is a high amount of particulates present in the oil. The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

view report



11 Aug 2023 Diag: Jonathan Hester

ISO



We recommend you service the filters on this component. Resample at the next service interval to monitor. All component wear rates are normal. There is a high amount of particulates present in the oil. The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.


view report





OIL ANALYSIS REPORT

Sample Rating Trend

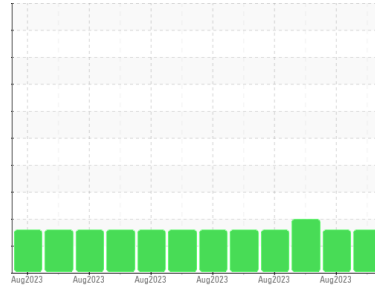

ISO



Area
WCLSNC
 Machine Id
QC230801HY

Component
Hydraulic System
 Fluid

JOHN DEERE HY-GARD HYD/TRANS (--- GAL)

DIAGNOSIS

Recommendation

We recommend you service the filters on this component. Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is a high amount of particulates present in the oil.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		WC0844493	WC0844492	WC0844491
Sample Date	Client Info		16 Aug 2023	15 Aug 2023	14 Aug 2023
Machine Age	hrs	Client Info	0	0	0
Oil Age	hrs	Client Info	0	0	0
Oil Changed	Client Info		N/A	N/A	N/A
Sample Status			ABNORMAL	ABNORMAL	ABNORMAL

WEAR METALS

	method	limit/base	current	history1	history2
PQ	ASTM D8184		26	38	37
Iron	ppm	ASTM D5185m >18	60	75	57
Chromium	ppm	ASTM D5185m >2	<1	1	<1
Nickel	ppm	ASTM D5185m >2	1	2	1
Titanium	ppm	ASTM D5185m >2	0	0	<1
Silver	ppm	ASTM D5185m >2	0	0	<1
Aluminum	ppm	ASTM D5185m >3	2	4	3
Lead	ppm	ASTM D5185m >3	9	9	10
Copper	ppm	ASTM D5185m >10	77	78	75
Tin	ppm	ASTM D5185m >2	2	2	3
Vanadium	ppm	ASTM D5185m	0	0	<1
Cadmium	ppm	ASTM D5185m	0	0	<1

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 6	102	103	106
Barium	ppm	ASTM D5185m 0	2	0	2
Molybdenum	ppm	ASTM D5185m 0	0	<1	<1
Manganese	ppm	ASTM D5185m	17	19	15
Magnesium	ppm	ASTM D5185m 145	21	21	28
Calcium	ppm	ASTM D5185m 3570	3490	3455	3237
Phosphorus	ppm	ASTM D5185m 1290	1149	1161	1050
Zinc	ppm	ASTM D5185m 1640	1384	1366	1267
Sulfur	ppm	ASTM D5185m	3474	3273	3516

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >4	9	9	8
Sodium	ppm	ASTM D5185m >2	12	15	19
Potassium	ppm	ASTM D5185m >20	2	2	<1
Water	%	ASTM D6304 >0.05	0.102	0.082	0.072
ppm Water	ppm	ASTM D6304 >500	1021.4	829.9	725.5

FLUID CLEANLINESS






	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>5000	▲ 322177	▲ 259499	▲ 278200
Particles >6µm	ASTM D7647	>1300	▲ 150619	▲ 119276	▲ 170924
Particles >14µm	ASTM D7647	>160	▲ 1016	▲ 503	▲ 3561
Particles >21µm	ASTM D7647	>40	24	15	▲ 88
Particles >38µm	ASTM D7647	>10	0	1	0
Particles >71µm	ASTM D7647	>3	0	1	0
Oil Cleanliness	ISO 4406 (c)	>19/17/14	▲ 26/24/17	▲ 25/24/16	▲ 25/25/19

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045 1.8	1.00	0.97	1.06



OIL ANALYSIS REPORT

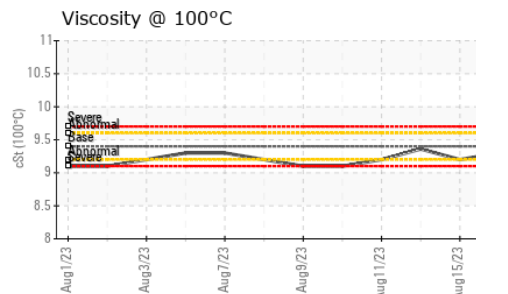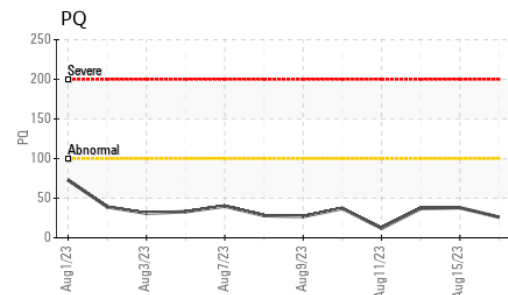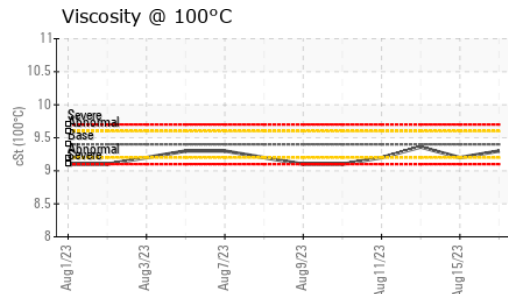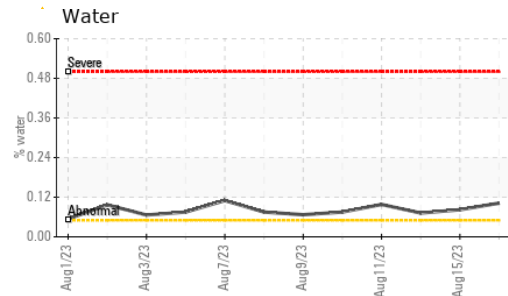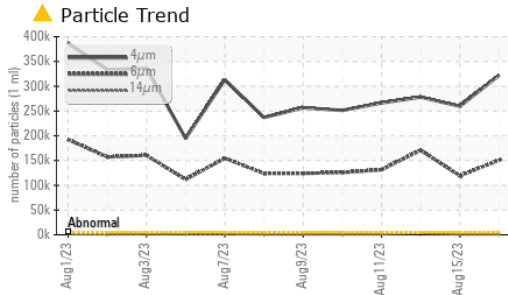


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	MODER	MODER
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	HEAVY	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.05	NEG	0.2%
Free Water	scalar	*Visual		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	57.0	61.4	62.8
Visc @ 100°C	cSt	ASTM D445	9.4	9.3	9.2
Viscosity Index (VI)	Scale	ASTM D2270	147	131	124






SAMPLE IMAGES	method	limit/base	current	history1	history2
---------------	--------	------------	---------	----------	----------

Color

Bottom

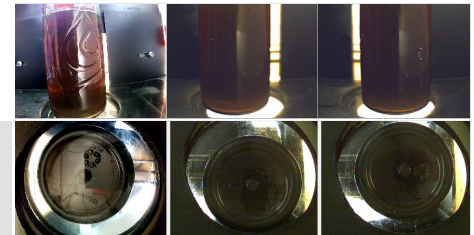

GRAPHS

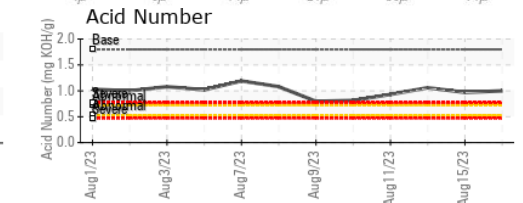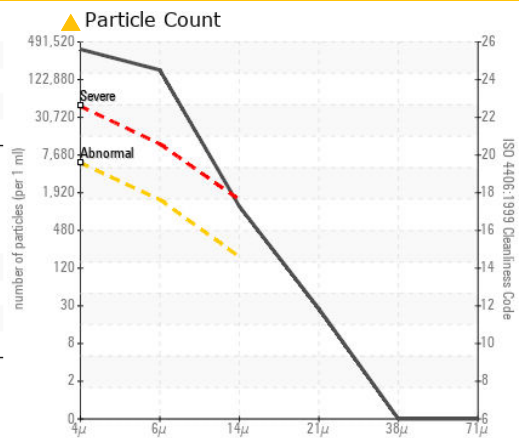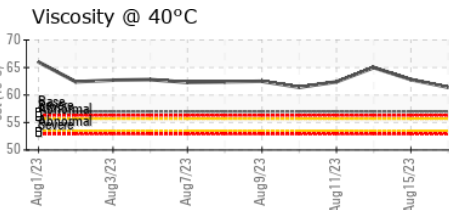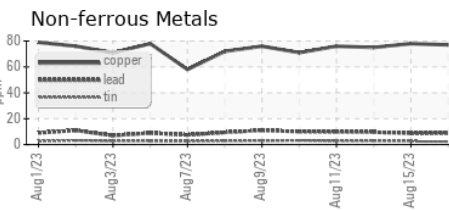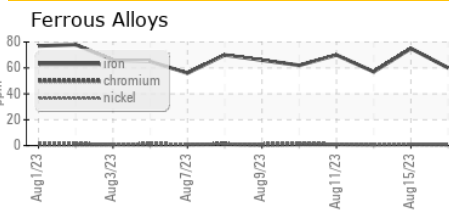

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0844493 **Received** : 16 Aug 2023
Lab Number : 05926136 **Diagnosed** : 21 Aug 2023
Unique Number : 10606083 **Diagnostician** : Jonathan Hester
Test Package : IND 2 (Additional Tests: KF, KV100, PQ, VI)

WEARCHECK LUBRICATION SERVICES QA ACCOUNT
 501 Madison Ave
 Cary, NC
 US 27513
 Contact: WCLS CARY NC

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (919)379-4102
 F: (919)379-4050