



# OIL ANALYSIS REPORT

Sample Rating Trend

**WATER**



Area  
**PLOGER**  
 Machine Id  
**6173 - PLOGER**  
 Component  
**Transmission**  
 Fluid  
**NOT GIVEN (--- GAL)**

## DIAGNOSIS

### ▲ Recommendation

We recommend that you drain the fluid from the component if this has not already been done. We recommend an early resample to monitor this condition.

### Wear

All component wear rates are normal.

### ▲ Contamination

There is a high amount of silt (particulates < 14 microns in size) present in the fluid. There is a light concentration of water present in the fluid.

### ▲ Fluid Condition

The AN level is above the recommended limit.

## SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	<b>WC0843161</b>	---	---
Sample Date	Client Info	<b>11 Jul 2023</b>	---	---
Machine Age	mls Client Info	<b>518477</b>	---	---
Oil Age	mls Client Info	<b>0</b>	---	---
Oil Changed	Client Info	<b>N/A</b>	---	---
Sample Status		<b>ABNORMAL</b>	---	---

## WEAR METALS

method	limit/base	current	history1	history2
Iron ppm	ASTM D5185m >200	<b>30</b>	---	---
Chromium ppm	ASTM D5185m >10	<b>&lt;1</b>	---	---
Nickel ppm	ASTM D5185m	<b>0</b>	---	---
Titanium ppm	ASTM D5185m	<b>&lt;1</b>	---	---
Silver ppm	ASTM D5185m	<b>0</b>	---	---
Aluminum ppm	ASTM D5185m >50	<b>4</b>	---	---
Lead ppm	ASTM D5185m >50	<b>0</b>	---	---
Copper ppm	ASTM D5185m >200	<b>12</b>	---	---
Tin ppm	ASTM D5185m >10	<b>0</b>	---	---
Vanadium ppm	ASTM D5185m	<b>0</b>	---	---
Cadmium ppm	ASTM D5185m	<b>0</b>	---	---

## ADDITIVES

method	limit/base	current	history1	history2
Boron ppm	ASTM D5185m	<b>243</b>	---	---
Barium ppm	ASTM D5185m	<b>0</b>	---	---
Molybdenum ppm	ASTM D5185m	<b>&lt;1</b>	---	---
Manganese ppm	ASTM D5185m	<b>8</b>	---	---
Magnesium ppm	ASTM D5185m	<b>0</b>	---	---
Calcium ppm	ASTM D5185m	<b>157</b>	---	---
Phosphorus ppm	ASTM D5185m	<b>1319</b>	---	---
Zinc ppm	ASTM D5185m	<b>1</b>	---	---
Sulfur ppm	ASTM D5185m	<b>1154</b>	---	---

## CONTAMINANTS

method	limit/base	current	history1	history2
Silicon ppm	ASTM D5185m >50	<b>25</b>	---	---
Sodium ppm	ASTM D5185m	<b>2</b>	---	---
Potassium ppm	ASTM D5185m >20	<b>&lt;1</b>	---	---
Water %	ASTM D6304 >0.1	<b>▲ 0.115</b>	---	---
ppm Water	ASTM D6304 >1000	<b>▲ 1151.2</b>	---	---

## FLUID CLEANLINESS






method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647 >10000	<b>▲ 62906</b>	---	---
Particles >6µm	ASTM D7647 >2500	<b>▲ 8001</b>	---	---
Particles >14µm	ASTM D7647 >320	<b>85</b>	---	---
Particles >21µm	ASTM D7647 >80	<b>21</b>	---	---
Particles >38µm	ASTM D7647 >20	<b>1</b>	---	---
Particles >71µm	ASTM D7647 >4	<b>0</b>	---	---
Oil Cleanliness	ISO 4406 (c) >20/18/15	<b>▲ 23/20/14</b>	---	---

## FLUID DEGRADATION

method	limit/base	current	history1	history2
Acid Number (AN) mg KOH/g	ASTM D8045	<b>▲ 4.72</b>	---	---



# OIL ANALYSIS REPORT

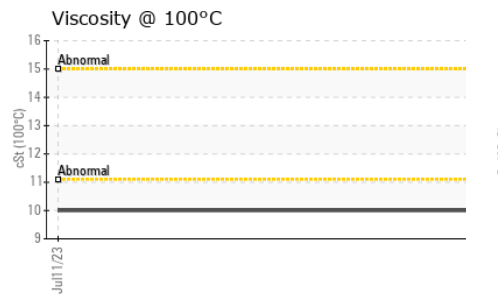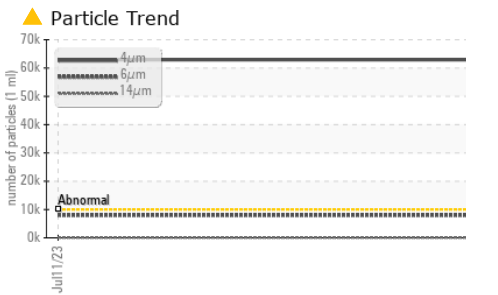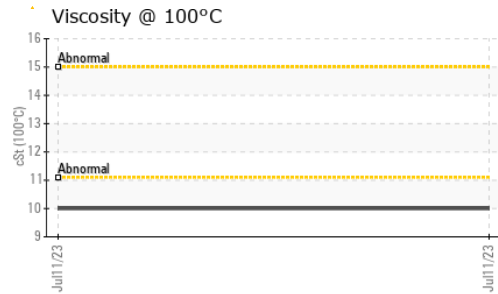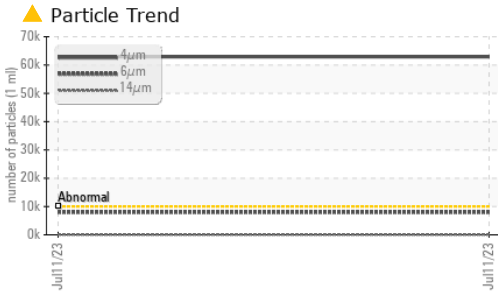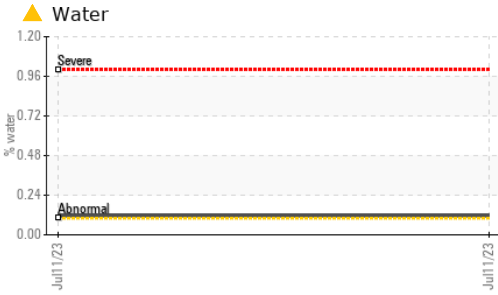



VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	---
Precipitate	scalar	*Visual	NONE	NONE	---
Silt	scalar	*Visual	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---
Free Water	scalar	*Visual		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	57.3	---	---
Visc @ 100°C	cSt	ASTM D445	10.0	---	---
Viscosity Index (VI)	Scale	ASTM D2270	162	---	---

SAMPLE IMAGES	method	limit/base	current	history1	history2
---------------	--------	------------	---------	----------	----------

Color		no image	no image
Bottom		no image	no image

## GRAPHS

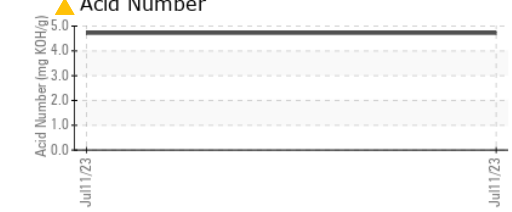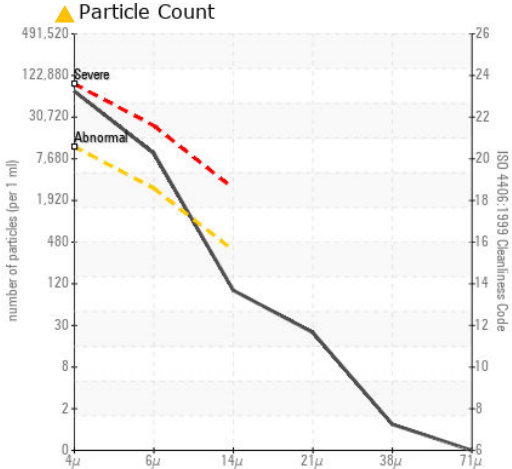

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : WC0843161 **Received** : 22 Aug 2023  
**Lab Number** : 05931530 **Diagnosed** : 25 Aug 2023  
**Unique Number** : 10616801 **Diagnostician** : Jonathan Hester  
**Test Package** : MOB 2 ( Additional Tests: KF, KV100, PrtCount, VI )

**BASF - GIANNA CREDAROLI**  
 500 WHITE PLAINS RD  
 TARRYTOWN, NY  
 US 10591  
 Contact: GIANNA CREDAROLI  
 gianna.credaroli@basf.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.  
 \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.  
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)