




PROBLEM SUMMARY

Sample Rating Trend

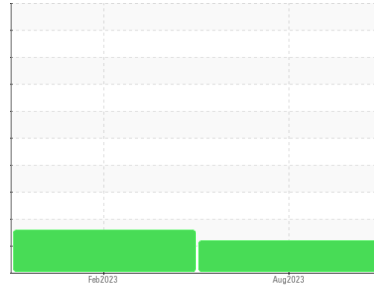


DEGRADATION



Machine Id
8327912
 Component
Diesel Engine
 Fluid
NOT GIVEN (--- GAL)

COMPONENT CONDITION SUMMARY

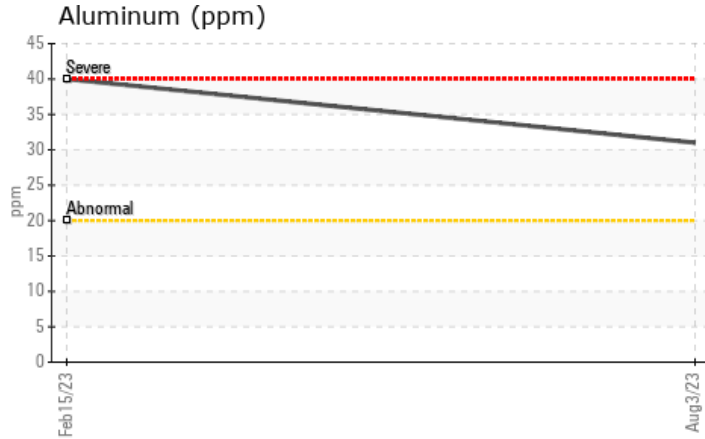

RECOMMENDATION

The oil is near the end of its useful service life, recommend schedule an oil change. Resample at the next service interval to monitor.

PROBLEMATIC TEST RESULTS

Sample Status	ABNORMAL	ABNORMAL	---
Base Number (BN)	mg KOH/g	ASTM D2896	---
	▲ 3.7	6.5	---

Customer Id: IDETAMFL
 Sample No.: IL05934648
 Lab Number: 05934648
 Test Package: FLEET



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Jonathan Hester +1 919-379-4092 x4092
jhester@wearcheckusa.com

To change component or sample information:
 Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Service/change Fluid	---	---	?	The oil is near the end of it's useful service life, recommend schedule an oil change.

HISTORICAL DIAGNOSIS

15 Feb 2023 Diag: Don Baldrige

DIRT



No corrective action is recommended at this time. Resample at the next service interval to monitor. Please specify the brand, type, and viscosity of the oil on your next sample. All component wear rates are normal. Fuel content negligible. Elemental level of silicon (Si) above normal indicating ingress of seal material. Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

view report






OIL ANALYSIS REPORT

Sample Rating Trend

DEGRADATION

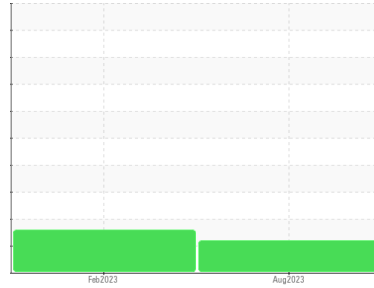

Machine Id
8327912
 Component
Diesel Engine
 Fluid
NOT GIVEN (--- GAL)

DIAGNOSIS

▲ Recommendation

The oil is near the end of its useful service life, recommend schedule an oil change. Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

▲ Fluid Condition

The BN level is low. The condition of the oil is acceptable for the time in service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		IL05934648	IL05782811	---
Sample Date	Client Info		03 Aug 2023	15 Feb 2023	---
Machine Age	mls	Client Info	77404	30969	---
Oil Age	mls	Client Info	0	0	---
Oil Changed	Client Info		N/A	N/A	---
Sample Status			ABNORMAL	ABNORMAL	---

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<1.0	0.4	---
Glycol	WC Method		NEG	NEG	---

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >100	51	41	---
Chromium	ppm	ASTM D5185m >20	5	2	---
Nickel	ppm	ASTM D5185m >4	<1	0	---
Titanium	ppm	ASTM D5185m	0	0	---
Silver	ppm	ASTM D5185m >3	0	<1	---
Aluminum	ppm	ASTM D5185m >20	31	40	---
Lead	ppm	ASTM D5185m >40	9	4	---
Copper	ppm	ASTM D5185m >330	8	22	---
Tin	ppm	ASTM D5185m >15	3	2	---
Vanadium	ppm	ASTM D5185m	<1	0	---
Cadmium	ppm	ASTM D5185m	0	0	---

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	14	38	---
Barium	ppm	ASTM D5185m	0	4	---
Molybdenum	ppm	ASTM D5185m	56	63	---
Manganese	ppm	ASTM D5185m	2	6	---
Magnesium	ppm	ASTM D5185m	758	438	---
Calcium	ppm	ASTM D5185m	1373	1789	---
Phosphorus	ppm	ASTM D5185m	792	923	---
Zinc	ppm	ASTM D5185m	998	1192	---
Sulfur	ppm	ASTM D5185m	2780	3148	---

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	15	▲ 34	---
Sodium	ppm	ASTM D5185m	6	4	---
Potassium	ppm	ASTM D5185m >20	82	109	---

INFRA-RED




	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >3	0.6	0.3	---
Nitration	Abs/cm	*ASTM D7624 >20	12.5	9.4	---
Sulfation	Abs/.1mm	*ASTM D7415 >30	26.3	22.4	---

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	27.7	19.5	---
Base Number (BN)	mg KOH/g	ASTM D2896	▲ 3.7	6.5	---







OIL ANALYSIS REPORT

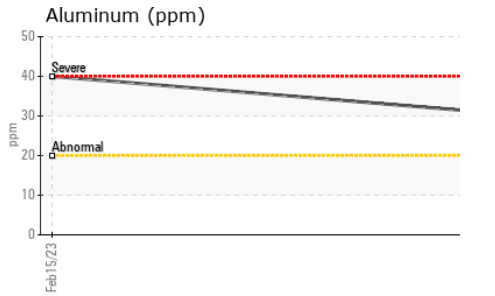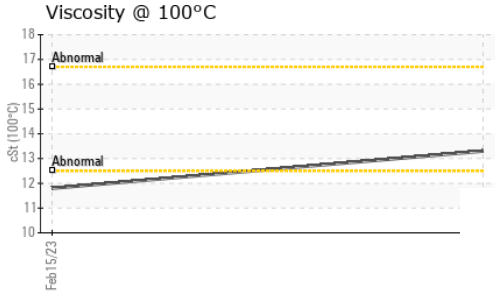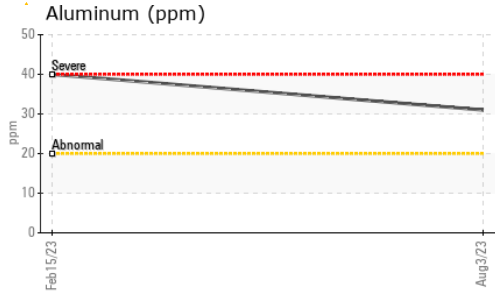

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	---
Precipitate	scalar	*Visual	NONE	NONE	---
Silt	scalar	*Visual	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---
Free Water	scalar	*Visual		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	13.3	11.8	---

GRAPHS

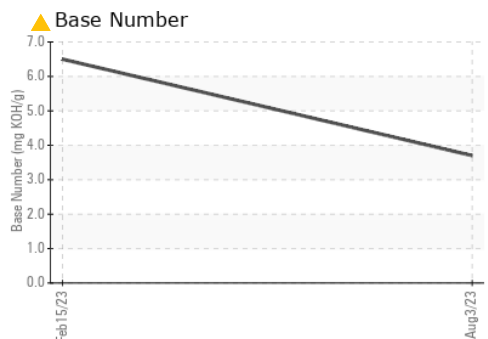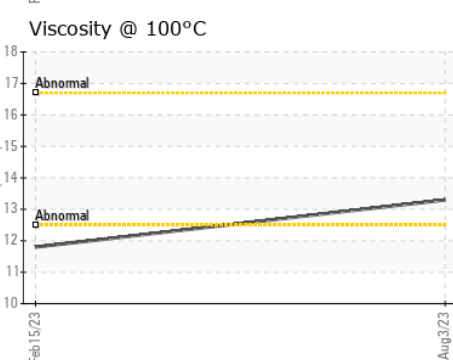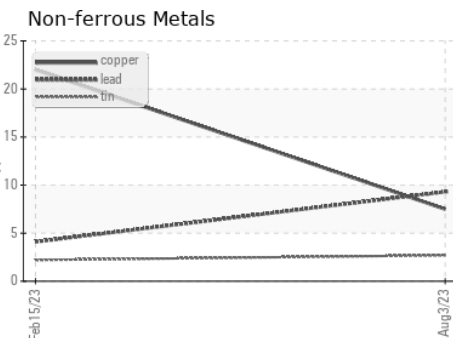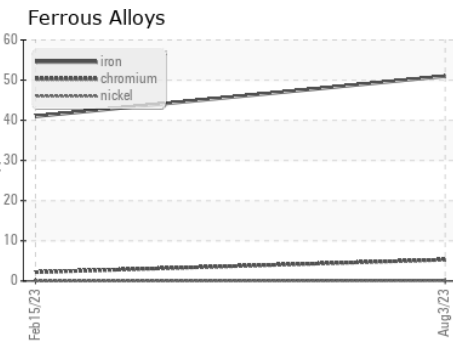

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : IL05934648 **Received** : 25 Aug 2023
Lab Number : **05934648** **Diagnosed** : 29 Aug 2023
Unique Number : 10619919 **Diagnostician** : Jonathan Hester
Test Package : FLEET

TAMPA IDEALEASE
 5951 ORIENT ROAD
 TAMPA, FL
 US 33610-9565
 Contact: Russ Cook
 russcook@idealease.com
 T: (813)626-9285
 F: (844)270-1356

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)