


Machine Id
Press #6 Press #6

Component
Hydraulic System

Fluid
KLUBER KLUBEROIL 4 UH1-46 N (220 GAL)

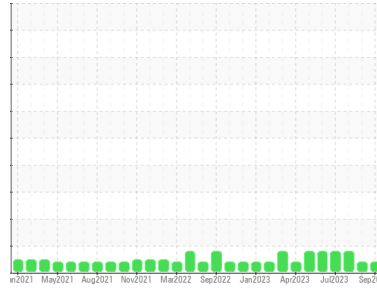

DIAGNOSIS

Recommendation

No corrective action is recommended at this time. The filter change at the time of sampling has been noted. Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

MPC (Membrane Patch Colorimetry) test indicates a light concentration of varnish present. The amount and size of particulates present in the system are acceptable.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		PTK0004798	PTK0004795	PTK0004614
Sample Date	Client Info		19 Sep 2023	06 Sep 2023	21 Aug 2023
Machine Age	hrs	Client Info	18881	18641	18266
Oil Age	hrs	Client Info	615	375	0
Oil Changed	Client Info		Not Chngd	Not Chngd	Changed
Sample Status			MARGINAL	MARGINAL	SEVERE

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >20	3	3	<1
Chromium	ppm	ASTM D5185m >10	0	<1	<1
Nickel	ppm	ASTM D5185m >10	<1	0	0
Titanium	ppm	ASTM D5185m	0	<1	<1
Silver	ppm	ASTM D5185m	0	0	0
Aluminum	ppm	ASTM D5185m >10	0	<1	0
Lead	ppm	ASTM D5185m >10	0	0	<1
Copper	ppm	ASTM D5185m >75	<1	<1	<1
Tin	ppm	ASTM D5185m >10	0	<1	<1
Vanadium	ppm	ASTM D5185m	0	<1	<1
Cadmium	ppm	ASTM D5185m	0	<1	<1

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	0	0	0
Barium	ppm	ASTM D5185m	0	0	0
Molybdenum	ppm	ASTM D5185m	0	0	0
Manganese	ppm	ASTM D5185m	<1	<1	<1
Magnesium	ppm	ASTM D5185m	1	<1	6
Calcium	ppm	ASTM D5185m	6	1	0
Phosphorus	ppm	ASTM D5185m	116	127	136
Zinc	ppm	ASTM D5185m	13	12	19
Sulfur	ppm	ASTM D5185m	3	31	0

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >20	2	2	2
Sodium	ppm	ASTM D5185m	0	1	1
Potassium	ppm	ASTM D5185m >20	1	4	3

FLUID CLEANLINESS


	method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>5000	134	392	525
Particles >6µm	ASTM D7647	>1300	35	75	177
Particles >14µm	ASTM D7647	>160	6	9	17
Particles >21µm	ASTM D7647	>40	2	3	6
Particles >38µm	ASTM D7647	>10	1	0	0
Particles >71µm	ASTM D7647	>3	0	0	0
Oil Cleanliness	ISO 4406 (c)	>19/17/14	14/12/10	16/13/10	16/15/11

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	0.43	0.41	0.359
MPC Varnish Potential	Scale	ASTM D7843 >15	▲ 15	▲ 21	● 40


OIL ANALYSIS REPORT

▲ Varnish Potential

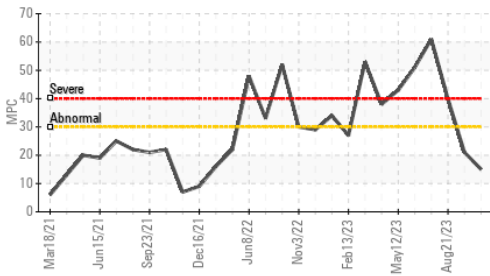

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG

Particle Trend

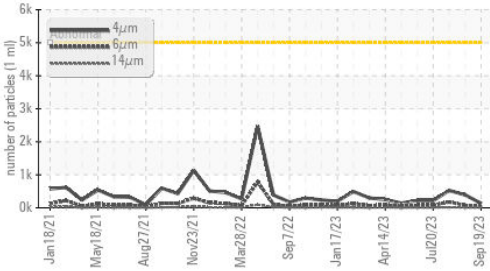


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D445	46	45.6	46.0


SAMPLE IMAGES

method	limit/base	current	history1	history2
Color				
Bottom				
MPC				

Acid Number

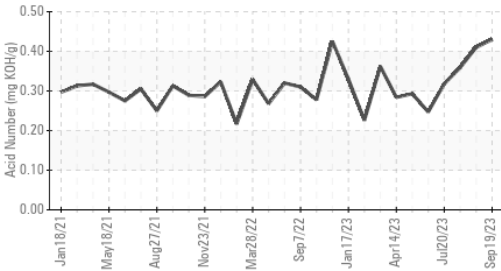

Viscosity @ 40°C

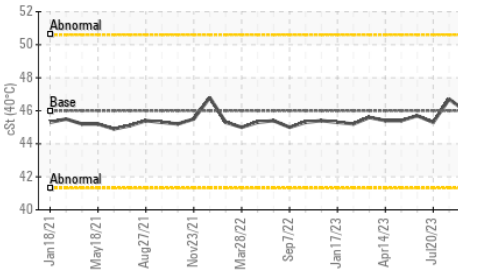

GRAPHS

<h4>Ferrous Alloys</h4>	<h4>Particle Count</h4>
<h4>Non-ferrous Metals</h4>	<h4>Acid Number</h4>
<h4>Viscosity @ 40°C</h4>	



Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : PTK0004798 **Received** : 02 Oct 2023
Lab Number : 05966228 **Diagnosed** : 10 Oct 2023
Unique Number : 10672779 **Diagnostician** : Doug Bogart
Test Package : MOB 2 (Additional Tests: MPC)

NIAGARA BOTTLING
 11031 88TH AVE
 PLEASANT PRAIRIE, WI
 US 53158
 Contact: AJ

To discuss this sample report, contact Customer Service at 1-800-237-1369.


* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (909)239-7599

F:

MPC (Varnish Test)

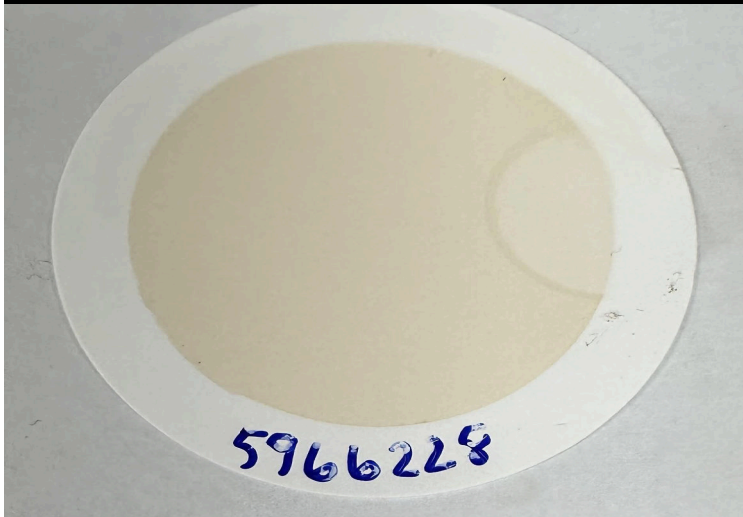

Sample Color & Clarity



This page left intentionally blank