



Machine Id
RAT M ROLLER
 Component
Lower Grease
 Fluid
NOT GIVEN (--- GAL)

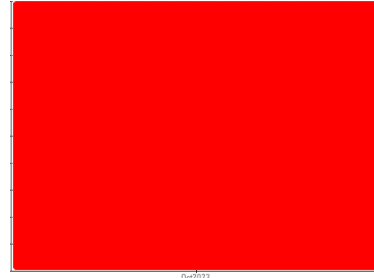

COMPONENT CONDITION SUMMARY

Ferrous Alloys

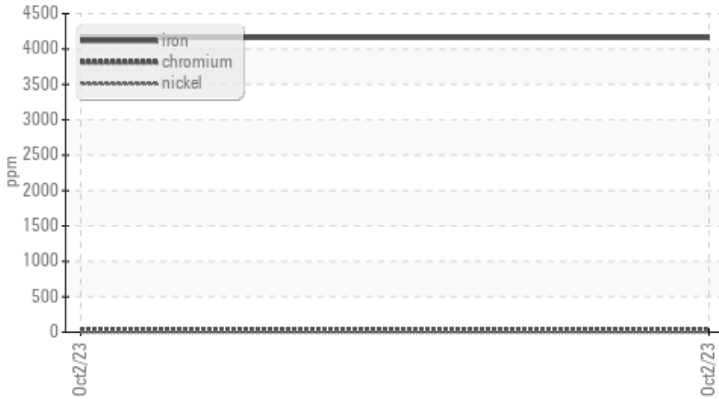

RECOMMENDATION

We recommend that you purge the grease in this component if this has not already been done. We recommend an early resample to monitor this condition. Analytical Ferrography: Results suggests no severe wear modes are present, however, there is an excessive amount of rubbing wear debris that should be cleared as early as possible. The contamination and wear suggests this system may need to have the re-grease interval adjusted as the wear present is consistent with a low oil bleed value - both meaning the grease was low on lubricant content and the system was suffering wear as a result.

PROBLEMATIC TEST RESULTS

Sample Status	SEVERE	---	---
Iron ppm ASTM D5185m >250	4160	---	---
Chromium ppm ASTM D5185m >10	36	---	---
Ferrous Rubbing Scale 0-10 *ASTM D7684	5		
Other Scale 0-10 *ASTM D7684	5		

Customer Id: LIEGIL
Sample No.: LH05968192
Lab Number: 05968192
Test Package: GRS 3



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Aaron Black +1
aaron.black@wearcheck.com


To change component or sample information:
 Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Resample	---	---	?	We recommend an early resample to monitor this condition.

HISTORICAL DIAGNOSIS

Machine Id
RAT M ROLLER
 Component
Lower Grease
 Fluid
NOT GIVEN (--- GAL)

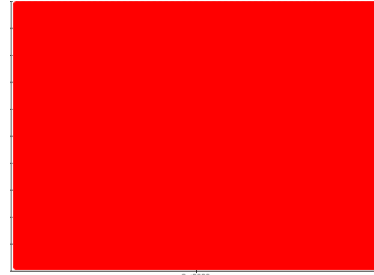

DIAGNOSIS

Recommendation

We recommend that you purge the grease in this component if this has not already been done. We recommend an early resample to monitor this condition. Analytical Ferrography: Results suggests no severe wear modes are present, however, there is an excessive amount of rubbing wear debris that should be cleared as early as possible. The contamination and wear suggests this system may need to have the re-grease interval adjusted as the wear present is consistent with a low oil bleed value - both meaning the grease was low on lubricant content and the system was suffering wear as a result.

Wear

Chromium and iron ppm levels are severe. Wear particle analysis indicates that the ferrous rubbing particles are abnormal.

Grease Condition

The grease is no longer serviceable due to the presence of contaminants. Oil bleed is low, suggesting low lubricant content.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		LH05968192	---	---
Sample Date	Client Info		02 Oct 2023	---	---
Machine Age	hrs	Client Info	0	---	---
Grease Age	hrs	Client Info	0	---	---
Grease Serviced	Client Info		N/A	---	---
Sample Status			SEVERE	---	---

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >250	4160	---	---
Chromium	ppm	ASTM D5185m >10	36	---	---
Nickel	ppm	ASTM D5185m >5	4	---	---
Cadmium	ppm	ASTM D5185m	0	---	---
Titanium	ppm	ASTM D5185m	2	---	---
Vanadium	ppm	ASTM D5185m	<1	---	---
Lead	ppm	ASTM D5185m >25	2	---	---
Copper	ppm	ASTM D5185m >75	14	---	---
Tin	ppm	ASTM D5185m >5	0	---	---
Silver	ppm	ASTM D5185m >5	0	---	---

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	162	---	---
Magnesium	ppm	ASTM D5185m	6	---	---
Manganese	ppm	ASTM D5185m	42	---	---
Molybdenum	ppm	ASTM D5185m	1872	---	---
Phosphorus	ppm	ASTM D5185m	256	---	---
Zinc	ppm	ASTM D5185m	142	---	---

THICKENER/SOAP

	method	limit/base	current	history1	history2
Aluminum	ppm	ASTM D5185m	16	---	---
Barium	ppm	ASTM D5185m	4	---	---
Calcium	ppm	ASTM D5185m	1384	---	---
Sodium	ppm	ASTM D5185m	22	---	---
Lithium	ppm	ASTM D5185m	194	---	---
Sulfur	ppm	ASTM D5185m	4754	---	---


CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >150	84	---	---
Potassium	ppm	ASTM D5185m	14	---	---
Water	%	ASTM D6304 >0.1	0.146	---	---
ppm Water	ppm	ASTM D6304 >1000	1466.4	---	---

GREASE CONDITION






	method	limit/base	current	history1	history2
Grease Color	*Visual		Grey	---	---
Texture	*In-house		Tacky	---	---
NLGI Consistency	NLGI Scale *SKF Method		4-5	---	---

GREASE ANALYSIS

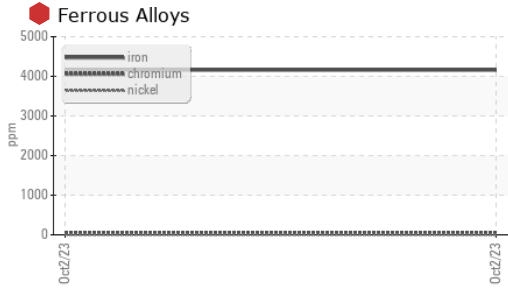

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color				no image	no image
Bottom				no image	no image

GRAPHS

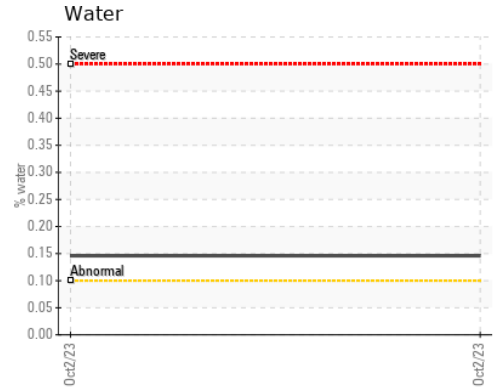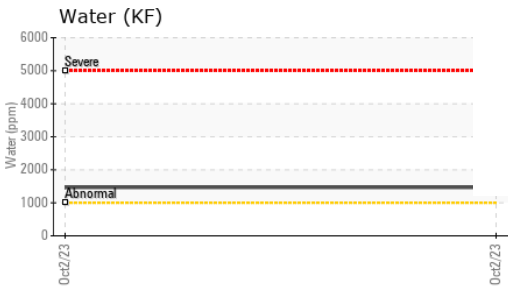
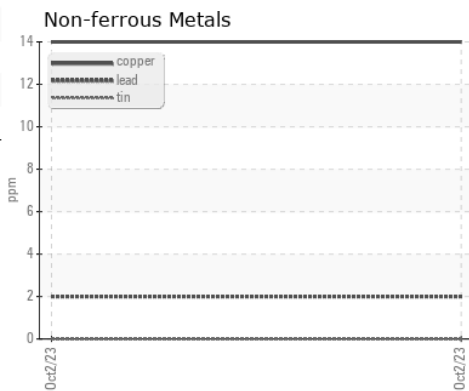
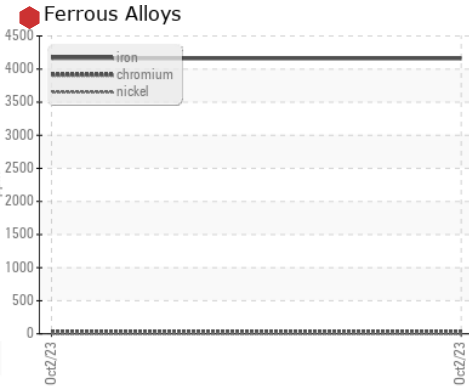
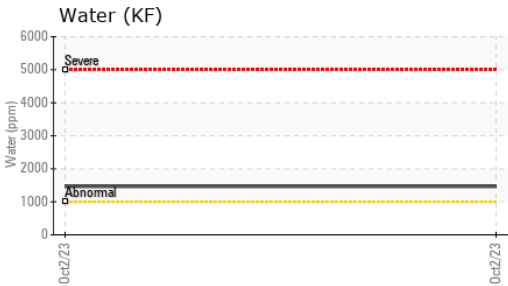


Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : LH05968192 **Received** : 03 Oct 2023
Lab Number : 05968192 **Diagnosed** : 23 Oct 2023
Unique Number : 10674743 **Diagnostician** : Aaron Black
Test Package : GRS 3 (Additional Tests: SCREEN)

LIEBHERR MINING EQUIPMENT CO
 5800 S DOUGLAS HWY
 GILLETTE, WY
 US 82718
 Contact: DUSTIN HARDEN
 DUSTIN.HARDEN@LIEBHERR.COM
 T: (307)660-8763
 F:

Certificate L2367
 To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

Machine Id
RAT M ROLLER
 Component
Lower Grease
 Fluid
NOT GIVEN (--- GAL)

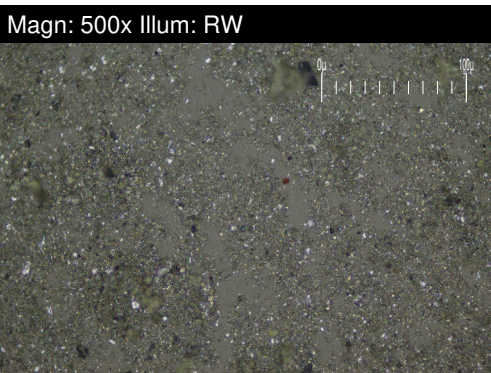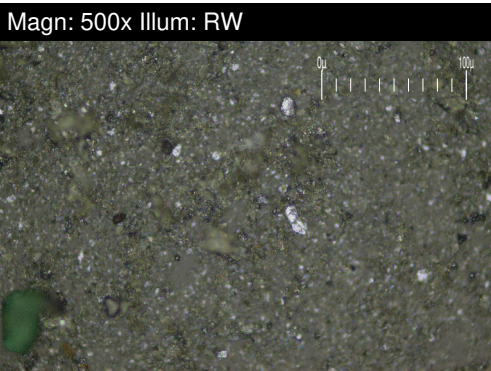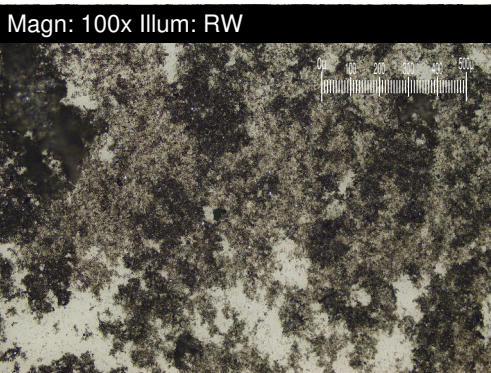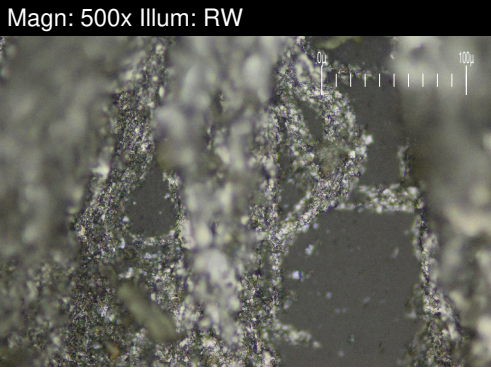

FERROGRAPHY		method	limit/base	current	history1	history2
Ferrous Rubbing	Scale 0-10	*ASTM D7684		▲ 5		
Ferrous Sliding	Scale 0-10	*ASTM D7684		■ 2		
Ferrous Cutting	Scale 0-10	*ASTM D7684				
Ferrous Rolling	Scale 0-10	*ASTM D7684				
Ferrous Break-in	Scale 0-10	*ASTM D7684				
Ferrous Spheres	Scale 0-10	*ASTM D7684				
Ferrous Black Oxides	Scale 0-10	*ASTM D7684				
Ferrous Red Oxides	Scale 0-10	*ASTM D7684				
Ferrous Corrosive	Scale 0-10	*ASTM D7684				
Ferrous Other	Scale 0-10	*ASTM D7684				
Nonferrous Rubbing	Scale 0-10	*ASTM D7684				
Nonferrous Sliding	Scale 0-10	*ASTM D7684				
Nonferrous Cutting	Scale 0-10	*ASTM D7684				
Nonferrous Rolling	Scale 0-10	*ASTM D7684				
Nonferrous Other	Scale 0-10	*ASTM D7684				
Carbonaceous Material	Scale 0-10	*ASTM D7684				
Lubricant Degradation	Scale 0-10	*ASTM D7684				
Sand/Dirt	Scale 0-10	ASTM D7684				
Fibres	Scale 0-10	*ASTM D7684				
Spheres	Scale 0-10	*ASTM D7684				
Other	Scale 0-10	*ASTM D7684		▲ 5		

WEAR

Chromium and iron ppm levels are severe. Wear particle analysis indicates that the ferrous rubbing particles are abnormal.

This page left intentionally blank