

PROBLEM SUMMARY

Sample Rating Trend



ISO




Machine Id
MAIN TEST STAND

Component
Hydraulic System

Fluid
AW HYDRAULIC OIL ISO 46 (200 GAL)

COMPONENT CONDITION SUMMARY

▲ Particle Trend

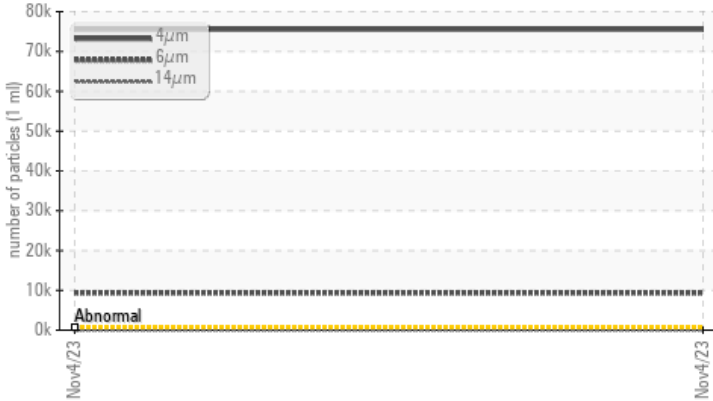

RECOMMENDATION

We recommend you service the filters on this component. Resample at the next service interval to monitor.

PROBLEMATIC TEST RESULTS

Sample Status	ASTM D7647	ISO 4406 (c)	ABNORMAL	---	---
Particles >4µm	>640	▲ 75524	---	---	---
Particles >6µm	>160	▲ 9330	---	---	---
Particles >14µm	>40	▲ 50	---	---	---
Oil Cleanliness	>16/14/12	▲ 23/20/13	---	---	---

Customer Id: HYDPACWA
Sample No.: PE0000722
Lab Number: 05999786
Test Package: PLANT



To manage this report scan the QR code


To discuss the diagnosis or test data:
Doug Bogart +1 (800)237-1369 x4016
dougb@wearcheckusa.com

To change component or sample information:
Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Filter	---	---	?	We recommend you service the filters on this component.

HISTORICAL DIAGNOSIS

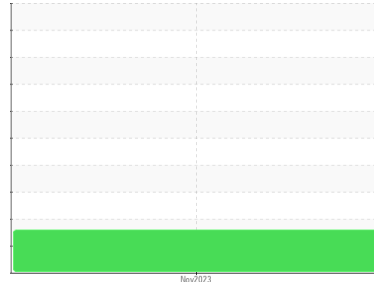

Machine Id
MAIN TEST STAND

Component
Hydraulic System

Fluid
AW HYDRAULIC OIL ISO 46 (200 GAL)

DIAGNOSIS

Recommendation

We recommend you service the filters on this component. Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is a high amount of particulates present in the oil. Elemental level of silicon (Si) above normal.

Fluid Condition

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			PE0000722	---	---
Sample Date	Client Info			04 Nov 2023	---	---
Machine Age	hrs	Client Info		0	---	---
Oil Age	hrs	Client Info		0	---	---
Oil Changed	Client Info			N/A	---	---
Sample Status				ABNORMAL	---	---

WEAR METALS		method	limit/base	current	history1	history2
PQ		ASTM D8184		10	---	---
Iron	ppm	ASTM D5185m	>20	0	---	---
Chromium	ppm	ASTM D5185m	>20	0	---	---
Nickel	ppm	ASTM D5185m	>20	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>20	0	---	---
Lead	ppm	ASTM D5185m	>20	0	---	---
Copper	ppm	ASTM D5185m	>20	1	---	---
Tin	ppm	ASTM D5185m	>20	0	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
Cadmium	ppm	ASTM D5185m		0	---	---






ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m	5	0	---	---
Barium	ppm	ASTM D5185m	5	0	---	---
Molybdenum	ppm	ASTM D5185m	5	0	---	---
Manganese	ppm	ASTM D5185m		0	---	---
Magnesium	ppm	ASTM D5185m	25	<1	---	---
Calcium	ppm	ASTM D5185m	200	51	---	---
Phosphorus	ppm	ASTM D5185m	300	309	---	---
Zinc	ppm	ASTM D5185m	370	377	---	---
Sulfur	ppm	ASTM D5185m	2500	890	---	---

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m	>15	17	---	---
Sodium	ppm	ASTM D5185m		<1	---	---
Potassium	ppm	ASTM D5185m	>20	0	---	---

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>640	▲ 75524	---	---
Particles >6µm		ASTM D7647	>160	▲ 9330	---	---
Particles >14µm		ASTM D7647	>40	▲ 50	---	---
Particles >21µm		ASTM D7647	>10	4	---	---
Particles >38µm		ASTM D7647	>3	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>16/14/12	▲ 23/20/13	---	---

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D8045	0.57	0.32	---	---

OIL ANALYSIS REPORT

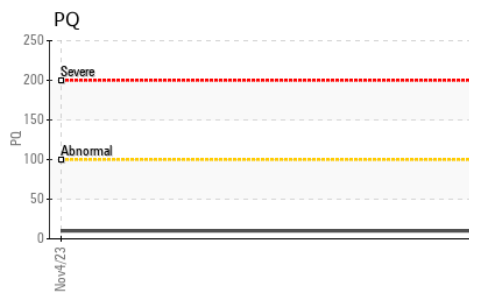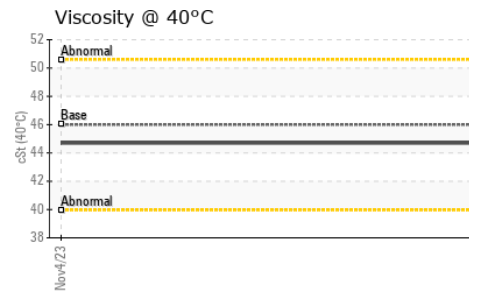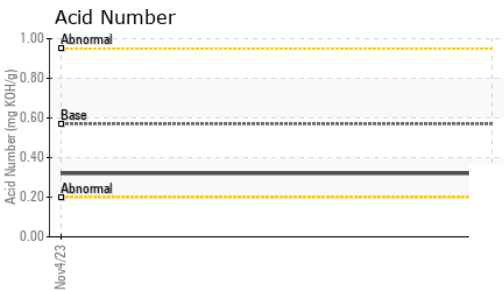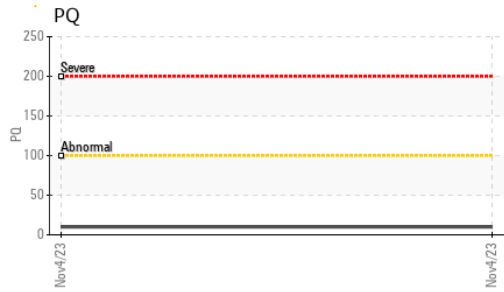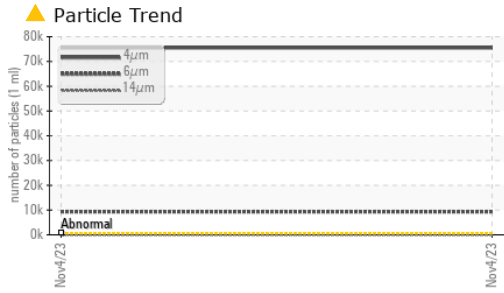






VISUAL	method	limit/base	current	history1	history2	
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---
Precipitate	scalar	*Visual	NONE	NONE	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.05	NEG	---	---
Free Water	scalar	*Visual		NEG	---	---

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 40°C	cSt	ASTM D445	46	44.7	---	---

SAMPLE IMAGES	method	limit/base	current	history1	history2
---------------	--------	------------	---------	----------	----------

Color				no image	no image
Bottom				no image	no image

GRAPHS

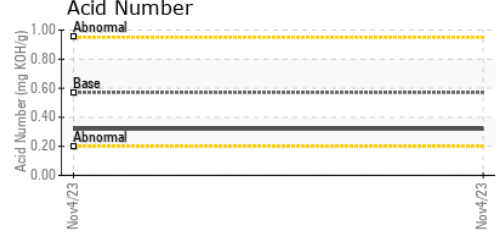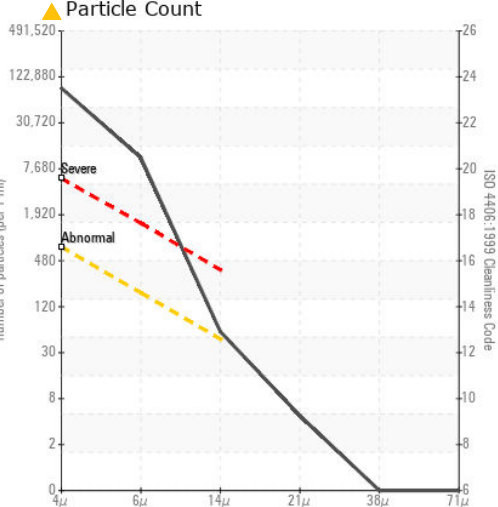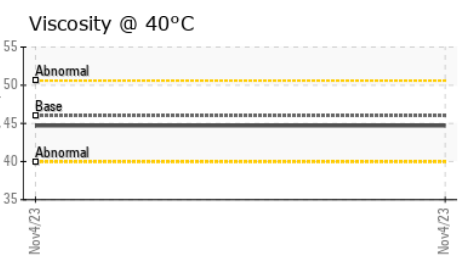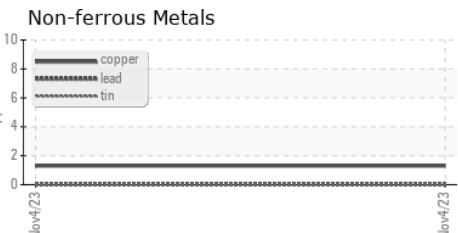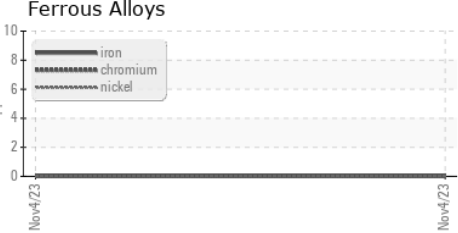

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : PE0000722 **Received** : 06 Nov 2023
Lab Number : 05999786 **Diagnosed** : 09 Nov 2023
Unique Number : 10728146 **Diagnostician** : Doug Bogart
Test Package : PLANT (Additional Tests: ICP, KV40, PQ, PRTCOUNT, SCREEN)

HYDRAULIC INDUSTRIES INC
 219 FRONTAGE RD N SUITE A
 PACIFIC, WA
 US 98047
 Contact: TODD GROTTING
 todd@hydraulic-industries-inc.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)